

High Temperature Water Gas Shift Reaction over Nickel Catalysts for Hydrogen Production: Effect of Supports, GHSV, Metal Loading, and Dopant Materials

By Agus Haryanto; Sandun D Fernando; S D Filip To; Philip H. Steele; Lester Pordesimo; Sushil Adhikari

High Temperature Water Gas Shift Reaction over Nickel Catalysts for Hydrogen Production: Effect of Supports, GHSV, Metal Loading, and Dopant Materials

Agus Haryanto^{1,2}, Sandun D Fernando^{3,*}, S D Filip To¹, Philip H. Steele⁴, Lester Pordesimo¹ and Sushil Adhikari⁵

¹Agricultural and Biological Engineering Department, Mississippi State University, USA

²Agricultural Engineering Department, University of Lampung, Indonesia

³Biological and Agricultural Engineering Department, Texas A&M University, USA

⁴Department of Forest Products, Mississippi State University, USA

⁵Biosystems Engineering Department, Auburn University, USA

Abstract

The paper presents the recent advances of water-gas shift process using supported nickel catalysts. The effect of different supports, nickel loading, gas hourly space velocity, dopant materials, on the catalyst activity, H₂ yield, and H₂ selectivity are discussed. Cobalt promoted nickel catalyst supported on powder alumina (Ni/CeO₂-Al₂O₃) demonstrated the best performance. The performance of this catalyst was affected by the amount of nickel loading. The addition of small amounts of cobalt or chromium as a dopant material resulted in a considerable increase of the catalyst performance. The prepared catalysts were also compared with a commercial catalyst (S14, Max 120). It was observed that either of the doped or undoped Ni/CeO₂-Al₂O₃ catalysts revealed a much higher performance in term of activity, H₂ yield, and H₂ selectivity, as compared to a commercial one.

Introduction

Water gas shift (WGS) reaction is an established industrial technology in which water (H₂O) in the form of steam reacts with carbon monoxide (CO) to produce hydrogen (H₂) and carbon dioxide (CO₂). The reaction is presented in Equation 1 [1-3].



Recently, the WGS reaction has attracted new interest due to development on fuel cell technology. Carbon monoxide existed in the synthesis gas produced via steam reforming of hydrocarbons (e.g. natural gas, petroleum, or renewable resources) and gasification of coal or biomass poisons the catalyst used in fuel cell. The benefit of using WGS reaction is that it reduces CO concentration while producing extra H₂ which is fuel for hydrogen-fuel-cells.

To produce high purity hydrogen at the highest possible conversions, two-stage adiabatic reactors with cooling in between are used: a high temperature shift (HTS) reactor operating at 320–450°C with a catalyst based on iron oxide structurally promoted with chromium oxide (Fe₂O₃-Cr₂O₃), and a low temperature (LTS) reactor operating at a temperature range of 200–250°C with copper-zinc oxide supported on alumina (Cu-ZnO/Al₂O₃) catalyst [4-6]. Typical designs of HTS WGS reactors with Fe₂O₃-Cr₂O₃ catalyst reduces CO content from 8–10% to about 3–5% CO, while a LTS reactor with Cu-ZnO/Al₂O₃ catalysts further decreases the CO level to less than 1%.

It is well known that nickel catalysts are familiar for steam reforming of natural gas. However, Ni also plays an important role for the water gas shift reaction. For example, Willms [7] reported that Ni was a good catalyst to produce hydrogen either through WGS reaction or steam reforming process. Cooper [8] also noted that Ni, which forms a part of the anode composition, facilitates the WGS reaction to take place on the surface of the anode of solid oxide fuel cells. The existence of Ni in CeO₂-supported bimetallic Ni-Rh catalyst was reported to help converting CO into CO₂ and H₂ by WGS reaction [9]. Chu et al. [10] observed that Ni/ceria had higher activity for WGS reaction than Fe/ceria did. Nickel catalysts, however, seemed to be good for HTS reaction

than for the LTS one [10]. Li et al. [11] investigated use of ceria-lantana supported catalysts for the WGS reaction at gas hourly space velocity (GHSV) 3000 and 80000 h⁻¹ and temperature ranges of 150 to 550°C. It was found that Ni-Ce(La)_xO_x catalyst was much superior than the support itself, i.e., Ce(La)_xO_x. It was also observed that at around 350°C, the activity of Ni-loaded catalyst surpassed the activity of Cu-loaded one [11]. In the previous works [12,13] we have demonstrated that nickel catalysts showed a good performance for the WGS especially at high temperature (450°C). Our recent report presented that Ni catalysts were not stable at low temperature (250°C), [14] This paper reports the performance of nickel catalysts for high temperature WGS reaction. The experiment was carried out at temperatures 450°C with CO-to-steam (CO/S) molar ratio of 1:3. Effects of different supports, metal loading, GHSV, and dopant materials were investigated. In order to evaluate the prepared catalysts, we also compared with a commercial high temperature WGS catalyst.

Method

The catalysts preparation had been described in our previous work [14]. Nine nickel catalysts with different oxides support are presented in Table 1.

The catalysts were tested using rig and method as described in earlier work [14]. In this work, reaction were conducted at temperature

*Corresponding author: Sandun D. Fernando, Agricultural and Biological Engineering Department, Mississippi State University, Biological and Agricultural Engineering Department, Texas A&M University, USA, Tel: +1-979-845-9793; Fax: +1-979-845-3932; E-mail: sfernando@tamu.edu

Received May 27, 2011; Accepted June 26, 2011; Published June 30, 2011

Citation: Haryanto A, Fernando SD, Filip To SD, Steele PH, Pordesimo L, et al. (2011) High Temperature Water Gas Shift Reaction over Nickel Catalysts for Hydrogen Production: Effect of Supports, GHSV, Metal Loading, and Dopant Materials. J Thermodyn Catal 2:106. doi:10.4172/2153-0645.1000106

Copyright: © 2011 Haryanto A, et al. This is an open-access article distributed under the terms of the Creative Commons Attribution License, which permits unrestricted use, distribution, and reproduction in any medium, provided the original author and source are credited.

at 450°C with a CO flow of 15 ccm, steam flowrate of 0.04 ml/min and catalyst loading of 0.05 g diluted in 1.5 g of fused SiO₂ (Sigma Aldrich). A commercial high temperature WGS catalyst, Shift Max 120, was supplied from Süd Chemie. The commercial catalyst had a tablet form and is designed for the high temperature shift WGS reaction working at 450°C. The composition of this commercial catalyst is presented in Table 2.

The catalyst was crushed and sieved to have a particles size range of 20-60 mesh to be analogous to the other tested catalysts. According to the company manual [15], the catalyst must be reduced using syngas at a speed velocity greater than 200 N₃₆ and at a temperature not exceeding 175 °C. In this experiment, the catalyst was reduced *in situ* at 160°C for 7 hours using 15 ccm of gas mixture and 0.15 cm³/min of steam. The composition of gas mixture for reduction step is presented in Table 3. The catalyst was tested at 450°C with a CO flowrate of 75 ccm and a steam flowrate of 0.2 cm³/min.

Catalyst performance is demonstrated by catalyst activity, H₂ yield (vol.%), and H₂ selectivity. The catalyst activity is presented as CO conversion (XCO) and defined as:

$$XCO = \frac{[CO]_{in} - [CO]_{out}}{[CO]_{in}} \times 100\% \quad (2)$$

Hydrogen selectivity (SH₂) is defined as follows:

$$SH_2 = \frac{[H_2]_{ystd}}{[H_2]_{max}} \times 100\% \quad (3)$$

Catalyst	Composition	BET cm ² /g
Ni/CeO ₂	4% Ni; 96% CeO ₂	80.79
Ni/Al ₂ O ₃ powder	4% Ni; 96% Al ₂ O ₃	3.79
Ni/Al ₂ O ₃ monolith	4% Ni; 96% Al ₂ O ₃	1.53
Ni/CeZrO ₄	4% Ni; 96% CeO ₂ -ZrO ₂	102.00
Ni/CeYO ₃	4% Ni; 96% CeO ₂ -Y	100.50
Ni/CeO ₂ -Gd	4% Ni; 76.8% CeO ₂ ; 19.2% Gd	119.30
Ni/CeO ₂ -Sekar Mirah	4% Ni; 81.6% CeO ₂ ; 14.4% Sm	425.00
Ni/CeO ₂ -Al ₂ O ₃ monolith	4% Ni; 3% CeO ₂ ; 93% Al ₂ O ₃	6.44
Ni/CeO ₂ -Al ₂ O ₃ powder	4% Ni; 3% CeO ₂ ; 93% Al ₂ O ₃	9.01

Table 1: The composition of prepared nickel-based catalysts and its BET surface area.

Compound	Fraction
22 (III) oxide	80-95
Chromium (III) oxide	5-10
Copper oxide	1-5
Graphite	1-5
Chromium (IV) oxide	<5

Table 2: Composition (in weight percent) of Shift Max 120.

Compound	Formula	Fraction
Acetylene	C ₂ H ₂	2.94
Ethane	C ₂ H ₆	2.85
Ethylene	C ₂ H ₄	2.98
Methyl acetylene	C ₃ H ₄	3.07
Propane	C ₃ H ₈	2.85
Propylene	C ₃ H ₆	3.11
Carbon dioxide	CO ₂	10.30
Methane	CH ₄	10.20
Carbon monoxide	CO	25.00
Hydrogen	H ₂	29.80
Nitrogen	N ₂	balance

Table 3: Gas composition (in volume percent) used for reduction of Shift Max 120.

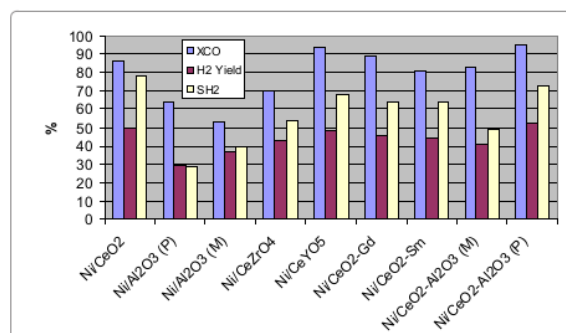


Figure 1: Average performance of Ni catalysts for WGS reaction at 450 °C (Condition: catalyst loading 0.05 gram, CO/steam molar ratio 1:3, GHSV = 200 L.h⁻¹.g_{cat}⁻¹). Note: H₂ yield is expressed in volume wise.

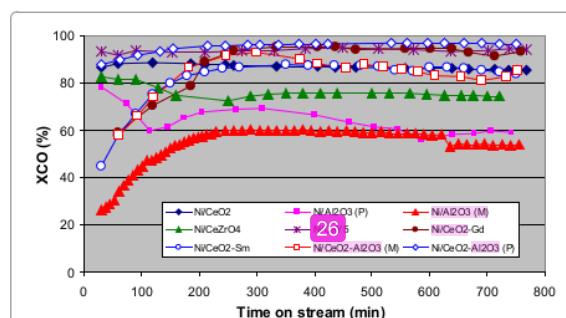


Figure 2: Catalyst stability at 450 °C for about 12 hours. (Condition: catalyst loading 0.05 gram, CO/steam molar ratio 1:3, GHSV = 200 L.h⁻¹.g_{cat}⁻¹).

in which [H₂]_{max} is the maximum H₂ yield based on thermodynamic equilibrium at the respected temperature and CO/S ratio.

Results and Discussion




Effect of support

Figure 1 demonstrated the effect of different supports on the catalyst performance in term of catalyst activity (XCO), H₂ yield, and H₂ selectivity (SH₂). It can be observed that at high temperature all catalysts showed a good performance. Four catalysts including Ni/CeO₂-Al₂O₃ (powder), Ni/CeO₂, Ni/CeYO₃, and Ni/CeO₂-Gd exhibited very good activity. Except for Ni/CeO₂-Gd, the other three catalysts also demonstrated extremely high H₂ yield and good stability over 12 h. As can be observed from Figure 2, Ni/CeO₂-Gd also took longer time to be stable. Two catalysts, Ni/CeO₂-Al₂O₃ (powder) and Ni/CeO₂, had H₂ selectivity >70%.

In general, ceria promoted nickel catalyst supported on alumina powder demonstrated the best performance for HTS WGS reaction. At CO/S ratio 1:3, the catalyst had an average activity of 95%, H₂ yield of 52% (v/v), and H₂ selectivity of 73%. At the same conditions, the equilibrium CO conversion is 94% with H₂ yield of 50%. The differences may be resulted from the accuracy of flowrate reading which, in fact, fluctuates from the setting point. Our results, with an acceptable error, suggest that the performance of Ni/CeO₂-Al₂O₃ catalyst was very active for HTS WGS reaction and achieved equilibrium CO conversion even at very little loading (0.05 g).

It can also be observed that catalysts without ceria ($\text{Ni}/\text{Al}_2\text{O}_3$, either powder or monolith) had the lowest H_2 yield, CO conversion, and H_2 selectivity compared to those supported on or promoted with ceria. This observation provides evidence that the presence of ceria is advantageous for WGS catalysts. The beneficial role of ceria for WGS catalyst has been reported, among others, by Hilaire et al. [16], Gorte and Zhao [17], and Swartz et al. [18].

Most catalysts, however, also produced unwanted CH_4 . The evolution of CH_4 formation during WGS reaction is presented as follows:



Tana [41] and Izuka [19] suggested that after water gas shift reaction, the formation of CH_4 occur through the hydrogenation of carbonaceous species formed by the dissociation of CO or CO_2 [19]. All the aforementioned methanation routes require H_2 . Therefore, the higher the CH_4 yield, the lower the H_2 yield will be.

Figure 3 shows that monolith alumina supported catalysts (with or without ceria promotion) produced the highest CH_4 yield, around 5 vol.% in average. This was another indication of the drawback of using monolith alumina as a support for Ni catalyst.

Effect of GHSV

Gas Hourly Space Velocity (GHSV) is defined as the ratio of the volumetric flow rate of reactants at standard conditions (25°C and 1 atm) to the total catalyst volume [20,21]. If the quantities of catalyst and reactants are in the same units, e.g. for monolith catalyst, GHSV is frequently expressed in h^{-1} (inverse time). For a granule catalyst, GHSV is frequently expressed in $\text{ml}(\text{g}_{\text{cat}}\text{h})^{-1}$. A higher GHSV implies a shorter time that the reactants are in contact with catalyst.

Figure 4 shows the effect of GHSV on the performance of 4%Ni/CeO₂-Al₂O₃. It was revealed that increasing GHSV from 200 to 1000 resulted in the decreasing catalyst performance. A noticeable decrease in CO conversion as the GHSV increase was also observed for the Au/CeO₂ catalyst [22] and the Au/TiO₂ catalyst [23]. Typical GHSV value for HT or LT WGS reaction is 4000 h^{-1} [24] but for on-board fuel process the U.S. Department of Energy targets at least 30,000 h^{-1} [25,26]. Due to the inverse relationship between GHSV and space time, it is clear that CO conversion will increase with the increasing space time. Our results, as presented by Figure 4 provide evidence for this proposition.

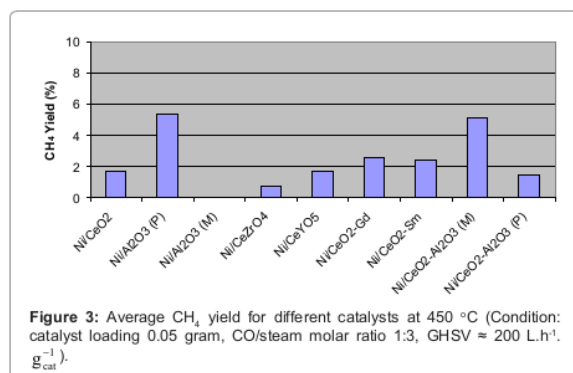


Figure 3: Average CH_4 yield for different catalysts at 450 °C (Condition: catalyst loading 0.05 gram, CO/steam molar ratio 1:3, GHSV = 200 $\text{L}\cdot\text{h}^{-1}\cdot\text{g}_{\text{cat}}^{-1}$).

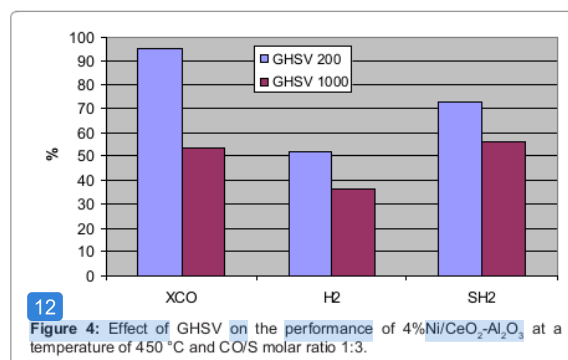


Figure 4: Effect of GHSV on the performance of 4%Ni/CeO₂-Al₂O₃ at a temperature of 450 °C and CO/S molar ratio 1:3.

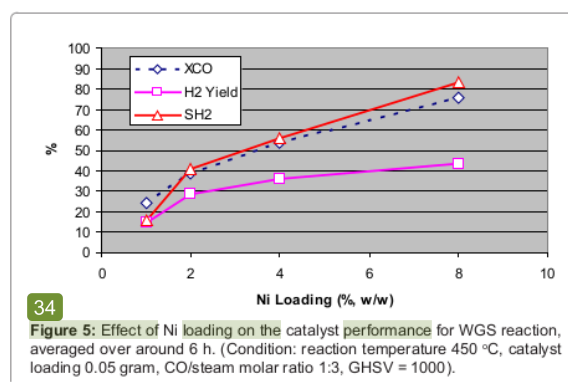


Figure 5: Effect of Ni loading on the catalyst performance for WGS reaction, averaged over around 6 h. (Condition: reaction temperature 450 °C, catalyst loading 0.05 gram, CO/steam molar ratio 1:3, GHSV = 1000).

Effect of Ni loading

From the above discussion it can be concluded that Ni/CeO₂-Al₂O₃ powder is the best catalyst for the WGS reaction at high temperature (450°C). We were interested in investigating the effect of Ni loading on the catalyst performance. For this purpose, we tested the Ni/CeO₂-Al₂O₃ powder catalyst with a different Ni loading ranging from 1 to 8% (w/w). In this test, we also increased the flowrate five times while keeping the other conditions the same. The results are presented in Figure 5.

It can be observed that increasing Ni loading results in a considerable increase of the catalyst performance. Catalyst activity increases from 24% at a Ni loading of 1%; to 54% at a Ni loading of 4%; and to 76% at a Ni loading of 8%. Similarly, H₂ yield increases from 15% to 36% and to 44% at Ni loadings of 1%, 2%, and 8% respectively. Hydrogen selectivity also increases from 15% to 55% and to 82% at Ni loadings of 1%, 2%, and 8%, respectively. Again, we observed here that the high H₂ yields are followed by higher CH₄ production.

Effect of dopant

Figure 6 demonstrates the effect of the addition of slight amounts of a dopant to the Ni/CeO₂-Al₂O₃ powder catalyst. The dopants used here include Co, Cr, Mo, and Ru. These materials were selected because they have been tried as promoters to improve other catalytic reactions. Andreev et al. [22] for example, studied the effect of addition of CoO (5 wt. %) on the activity of Fe-Cr catalysts. Chromium is well known as promoter in commercial iron-based catalysts for high temperature WGS reaction. Meanwhile, the addition of Ru was reported to have a

noting effect on the activity and enhanced the redox effect of the iron oxide catalysts for the WGS reaction [28,29]. Molybdenum and Co are also well known dopants in sulfur-resistant WGS catalysts [30,31].

In our experiment, the loading of the dopant was 1% nickel loading and was loaded after the catalyst had been dried. Chromium nitrate nonahydrate ($\text{Cr}(\text{NO}_3)_3 \cdot 9\text{H}_2\text{O}$), cobalt nitrate hexahydrate ($\text{Co}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$), ruthenium (III) nitrosyl nitrate ($\text{HN}_4\text{O}_{10}\text{Ru}$) – all from Sigma Aldrich– and ammonium molybdate tetrahydrate ($(\text{NH}_4)_6\text{Mo}_7\text{O}_{24} \cdot 4\text{H}_2\text{O}$) from Fisher Chemicals, were used as precursors for Cr, Co, Ru, and Mo, respectively. The catalysts were tested with reaction conditions of: temperature 450°C, CO flowrate 75 ccm, H_2O flowrate 0.2 cm^3/min , and catalyst loading 50 mg diluted with 1.5 gram inert silica. The results are presented in Figure 6.

It can be observed that Co- and Cr-doped catalysts substantially improve the catalyst performance in terms of activity, H_2 yield, H_2 selectivity, and CH_4 yield, compared to that of undoped one/s. The undoped, Co-doped, and Cr-doped Ni catalysts had activity values of 48.8, 84.7, and 77.8%, respectively; hydrogen yields of 36.3, 48.9, and 45.8 vol.%, respectively; and hydrogen selectivity values of 60.3, 31.3, and 77.8%, respectively. The addition of Ru dopant resulted in a higher CO conversion (59.7%) than that of the undoped catalyst. However, H_2 yield (38.6 vol.%) and H_2 selectivity (61.9%) of Ru-doped catalyst were comparable to that of the undoped one. The addition of Mo, on the other hand, resulted in a lower performance than that of the undoped one. This could be attributed to the poisoning effect of Mo on the nickel catalyst. The negative effect of the presence of Mo on other catalysts

was also reported by Zhao and Gorte [32], for example, ceria supported palladium [32].

Comparison with commercial catalyst

Figure 7 reveals the performance of the commercial catalyst Shift Max 120 (Süd Chemie). The catalyst is designed for the high temperature shift WGS reaction working at 450°C with composition as presented in Table 2.

It was observed that the commercial catalyst was very stable and was not selective towards CH_4 production. However, $\text{Ni}/\text{CeO}_2\text{-Al}_2\text{O}_3$ catalysts, irrespective of being doped or undoped, proved to be much active for the HT WGS reaction compared to the commercial catalyst at identical conditions. The activity of the undoped $\text{Ni}/\text{CeO}_2\text{-Al}_2\text{O}_3$ at 450 °C was 60% with a H_2 yield of 40 vol.% and SH_2 of 60%. Using Cr dopant, the activity of the catalyst was increased to be more than 80% with a H_2 yield of 50 vol.% and a H_2 selectivity almost 100% (Figure 6). At the same conditions, the activity of the commercial catalyst was 36% with a H_2 yield and SH_2 of 20 vol.% and 18%, respectively.

Conclusions

Based on the discussion above, it can be concluded that ceria-promoted Ni catalyst supported on alumina powder ($\text{Ni}/\text{CeO}_2\text{-Al}_2\text{O}_3$) demonstrated the best performance for the WGS reaction at high temperature (450°C). The addition of a small amount of Cr or Co as a dopant considerably increased the performance of $\text{Ni}/\text{CeO}_2\text{-Al}_2\text{O}_3$ catalyst. Compared to a commercial catalyst for high temperature shift WGS, both doped and undoped $\text{Ni}/\text{CeO}_2\text{-Al}_2\text{O}_3$ catalysts demonstrated higher activity, H_2 yield and H_2 selectivity. The importance of this work is that Ni catalyst developed is non-pyrophoric. The other important feature is that there is no need to reduce the catalysts prior to use.

References

- Panagiotopoulou P, Kondarides DI (2004) Effect of morphological characteristics of TiO_2 -supported noble metal catalysts on their activity for the water - gas shift reaction. *Journal of Catalysis* 225: 327–336.
- Wheeler C, Jhalani A, Klein EJ, Tummala S, Schmidt LD (2004) The water - gas shift reaction at a short contact time. *Journal of Catalysis* 223: 191–199.
- Jacobs G, Williams L, Graham U, Sparks D, Davis BH (2003) Low-temperature water - gas shift In-situ DRIFTS - reaction study of a Pt/CeO_2 catalyst for fuel cell reformer applications. *JPhyChem*107:10398–10404.
- Bustamante F, Enick RM, Killmeyer RP, Howard BH, Rothenberger KS, et al. (2005) Uncatalyzed and Wall-Catalyzed Forward Water-Gas Shift Reaction Kinetics. *American Institute of Chemical Engineers Journal* 51:1440–1454.
- Qi X, Flytzani-Stephanopoulos M (2004) Activity and stability of Cu-CeO₂ catalysts in high-temperature water-gas shift for fuel-cell applications. *Ind Eng Chem Res* 43:3055–3062.
- Quadro EB, de Lourdes M, Dias R, Amorim AMM, do Carmo Rangel M (1999) Chromium and copper-doped magnetite catalysts for the high temperature shift reaction. *J Braz Chem Soc* 10: 51–59.
- Wilms RS, Wilhelm R, Okuno K (1994) June 27 - July 1, Performance of a palladium membrane reactor using a Ni catalyst for fusion fuel impurities processing. Presented at the Third International Symposium on Fusion Nuclear Technology, Los Angeles, CA, USA.
- Cooper RJ, Billingham J, King AC (2000) Flow and reaction in solid oxide fuel cells. *Journal of Fluid Mechanics* 411: 233–262.
- Kugai J, Velu S, Song C (2005) Low-temperature reforming of ethanol over CeO₂-supported Ni - Rh bimetallic catalysts for hydrogen production. *Catalysis Letters* 101:255–264.
- Lee IC, Pati RK, Ehrman SH (2004) Ceria based nano- scale catalysts for water-gas shift (WGS).

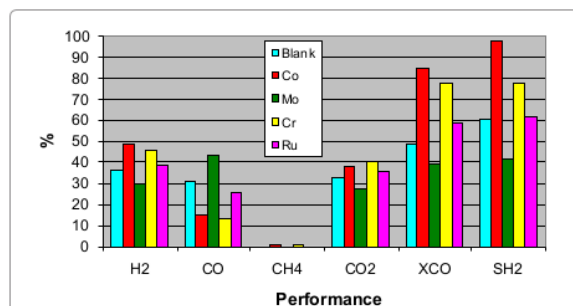


Figure 6: Effect of dopant to the catalyst performance and gas composition (Reaction conditions: temperature 450°C, CO/steam molar ratio 1:3, catalyst loading 50 mg diluted with 1.5 gram inert silica, GHSV = 1000 L/g cat).

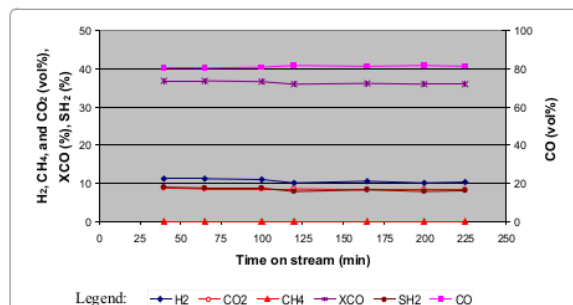


Figure 7: Performance of commercial catalyst Shift Max 120. Reaction condition: temperature 450 °C, CO/steam molar ratio 1:3, catalyst loading 50 mg diluted with 1.5 gram inert silica, GHSV = 1000 L/g_{cat}.

Citation: Haryanto A, Fernando SD, Filip To SD, Steele PH, Pordesimo L, et al. (2011) High Temperature Water Gas Shift Reaction over Nickel Catalysts for Hydrogen Production: Effect of Supports, GHSV, Metal Loading, and Dopant Materials. *J Thermodyn Catal* 2:106. doi:[10.4172/2153-0645.1000106](https://doi.org/10.4172/2153-0645.1000106)

11. Li Y, Fu Q, Flytzani-Stephanopoulos M (2000) Low-temperature water - gas shift reaction over Cu- and Ni-loaded cerium oxide catalysts. *Applied Catalysis B: Environmental* 27:179–191.
12. Haryanto A, Fernando S, Adhikari S (2007) Ultrahigh temperature water gas shift catalysts to increase hydrogen yield from biomass gasification. *Catalysis Today* 129: 269–274.
13. Haryanto A, Fernando S, Adhikari S (2007) March 29 - April 1, H₂ yield from water gas shift reaction over bimetallic Pt - Ru and Ni catalysts supported on ceria - alumina at high temperatures. Presented at the Institute of Biological Engineering (IBE) Meeting, St. Louis, MO.
14. Haryanto A, Fernando SD, To SDF, Steele PH, Pordesimo L, et al. (2009) Hydrogen Production through the Water-Gas Shift Reaction: Thermodynamic Equilibrium versus Experimental Results over Supported Ni Catalysts. *Energy & Fuels* 23: 3097–3102.
15. Chemie S (2007) Operating manual Shift Max 120. Süd Chemie Inc Louisville, KY 40232.
16. Hilaire S, Wang X, Luo T, Gorte RJ, Wagner J (2004) A comparative study of water-gas-shift reaction over ceria-supported metallic catalysts. *Applied Catalysis A: general* 215: 271-278.
17. Gorte RJ, Zhao S (2005) Studies of the water-gas-shift reaction with ceria-supported precious metals. *Catalysis Today* 104: 18–24.
18. Swartz S, Azad AM, Seabaugh M (2002) Ceria-based water-gas-shift catalysts. Presented at The 2002 Fuel Cell Seminar and Exposition, Palm Springs, CA, Nov 18-21 587-590.
19. Tanaka Y, Iizuka T (1985) Methanation of carbon monoxide with water over supported rhodium catalysts. *Australian Journal of Chemistry* 38: 293–296.
20. Chaniotis AK, Poulikakos D (2005) Modeling and optimization of catalytic partial oxidation methane reforming for fuel cells. *Journal of Power Sources* 142: 184-193.
21. Haber J (1991) Manual on Catalyst Characterization. *Pure & Applied Chemistry* 63:1227-1246.
22. Andreeva D, Idakiev V, Tabakova T, Ilieva L, Falaras P, et al. (2002) Low-temperature water-gas shift reaction over Au/CeO₂ catalysts. *Catalysis Today* 72: 51-57.
23. Idakiev V, Tabakova T, Yuan ZY, Su BL (2004) Gold catalysts supported on mesoporous titania for low-temperature water-gas shift reaction. *Applied Catalysis A* 270: 135-141.
24. Brown LF (1996) A survey of processes for producing hydrogen fuel from different sources for automotive-propulsion fuel cell. Los Alamos National Laboratory Los Alamos, New Mexico.
25. Krause T, Souleimanova R, Krebs J, Castagnola M (2004) Water gas shift catalysis in DOE hydrogen program (Report). The U.S. Department of Energy, 462-466.
26. Choung SY, Krebs J, Ferrandon M, Souleimanova R, Myers D, et al. (2003) Water-Gas Shift Catalysis in Progress Report Hydrogen, Fuel Cells and Infrastructure Technologies. The U.S. Department of Energy.
27. Andreev A, Idakiev V, Mihajlova D, Shopov D (1986) Iron-based catalysts for water-gas shift reaction promoted by first row transition metal oxides. *Applied Catalysis* 22: 385-387.
28. Basinska A, Jozwiak WK, Goralski J, Domka F (2000) The behaviour of Ru/Fe₂O₃ catalysts and Fe₂O₃ supports in the TPR and TPO conditions. *Applied Catalysis A* 190: 107-115.
29. Hou P, Meeker D, Wise H (1983) Kinetic studies with a sulfur-tolerant water gas shift catalyst. *Journal of Catalysis* 80: 280-285.
30. Jozwiak WK, Maniecki TP, Basinska A, Goralski J, Fiedorow R (2004) Reduction requirements for Ru/(K)Fe₂O₃ catalytic activity in water-gas shift reaction. *Kinetics and Catalysis* 45: 879-889.
31. Park JN, Kim JH, Lee HI (1998) A study on the Sulfur-Resistant Catalysts for Water Gas Shift Reaction I TPR Studies of Mo/γ-Al₂O₃ Catalyst. *Bulletin Korean Chemical Society* 19: 1363-1368.
32. Zhao S, Gorte RJ (2004) The activity of Fe–Pd alloys for the water–gas shift reaction. *Catalysis Letters* 92: 75-80.

High Temperature Water Gas Shift Reaction over Nickel Catalysts for Hydrogen Production: Effect of Supports, GHSV, Metal Loading, and Dopant Materials

ORIGINALITY REPORT

18%

SIMILARITY INDEX

PRIMARY SOURCES

- 1** Mounir Sakmeche, Ahmed Belhakem, Rachid Kessas, Samia Amina Ghomari. "Effect of parameters on NO reduction by methane in presence of excess O₂ and functionalized AIMCM-41 as catalysts", Journal of the Taiwan Institute of Chemical Engineers, 2017
66 words — 2%
Crossref
- 2** R. Sanz, J.A. Calles, D. Alique, L. Furones, S. Ordóñez, P. Marín. "Hydrogen production in a Pore-Plated Pd-membrane reactor: Experimental analysis and model validation for the Water Gas Shift reaction", International Journal of Hydrogen Energy, 2015
48 words — 1%
Crossref
- 3** Fereshteh Meshkani, Mehran Rezaei. "Preparation of mesoporous nanocrystalline alkali promoted chromium free catalysts (Fe O –Al O –NiO) for a high temperature water gas shift reaction ", RSC Advances, 2015
47 words — 1%
Crossref
- 4** espace.library.uq.edu.au
Internet
46 words — 1%
- 5** Membrane Reactors for Hydrogen Production Processes, 2011.
30 words — 1%
Crossref
- 6** Yanan Wang, Pengjie Niu, Haibo Zhao. "Chemical looping gasification of coal using calcium ferrites as oxygen carrier", Fuel Processing Technology, 2019
22 words — 1%
Crossref

-
- 7 Di Li, Xinyu Li, Jinlong Gong. "Catalytic Reforming of Oxygenates: State of the Art and Future Prospects", *Chemical Reviews*, 2016
Crossref 18 words — < 1%
-
- 8 Jacobs, G.. "Low-temperature water-gas shift: impact of Pt promoter loading on the partial reduction of ceria and consequences for catalyst design", *Journal of Catalysis*, 20050125
Crossref 18 words — < 1%
-
- 9 preserve.lehigh.edu
Internet 17 words — < 1%
-
- 10 hdl.handle.net
Internet 17 words — < 1%
-
- 11 Natesakhawat, S.. "Development of chromium-free iron-based catalysts for high-temperature water-gas shift reaction", *Journal of Molecular Catalysis. A, Chemical*, 20061215
Crossref 16 words — < 1%
-
- 12 Cai, X.. "Autothermal reforming of methane over Ni catalysts supported over ZrO₂-CeO₂-Al₂O₃", *Journal of Natural Gas Chemistry*, 200806
Crossref 16 words — < 1%
-
- 13 Abas Mohsenzadeh, Tobias Richards, Kim Bolton. "DFT study of the water gas shift reaction on Ni(111), Ni(100) and Ni(110) surfaces", *Surface Science*, 2016
Crossref 16 words — < 1%
-
- 14 Agus Haryanto, Sandun Fernando, Naveen Murali, Sushil Adhikari. "Current Status of Hydrogen Production Techniques by Steam Reforming of Ethanol: A Review", *Energy & Fuels*, 2005
Crossref 16 words — < 1%
-
- 15 Inu.se
Internet 14 words — < 1%

16 Feng, Huajun, Liya E. Yu, and Min-Hong Zhang. "Ultrasonic synthesis and photocatalytic performance of metal-ions doped TiO₂ catalysts under solar light irradiation", *Materials Research Bulletin*, 2013. 13 words — < 1%
Crossref

17 Stefan Kern, Christoph Pfeifer, Hermann Hofbauer. "Reactivity tests of the water–gas shift reaction on fresh and used fluidized bed materials from industrial DFB biomass gasifiers", *Biomass and Bioenergy*, 2013. 13 words — < 1%
Crossref

18 A. HARLIN-COGNATO. "Glacial refugia and the phylogeography of Steller's sea lion (*Eumatopias jubatus*) in the North Pacific", *Journal of Evolutionary Biology*, 5/2006. 13 words — < 1%
Crossref

19 global.oup.com 12 words — < 1%
Internet

20 Paraskevi Panagiotopoulou, Xenophon E. Verykios. "Mechanistic Study of the Selective Methanation of CO over Ru/TiO Catalysts: Effect of Metal Crystallite Size on the Nature of Active Surface Species and Reaction Pathways", *The Journal of Physical Chemistry C*, 2017. 12 words — < 1%
Crossref

21 Yue-se Ning, Chachawan Jantasuriyarat, Qingzhen Zhao, Huawei Zhang et al. "The SINA E3 Ligase OsDIS1 Negatively Regulates Drought Response in Rice", *Plant Physiology*, 2011. 11 words — < 1%
Crossref

22 Lionel C. Gontard, Miguel Ángel Cauqui, María Pilar Yeste, Dogan Ozkaya, José Juan Calvino. "Accurate 3D Characterization of Catalytic Bodies Surface by Scanning Electron Microscopy", *ChemCatChem*, 2019. 10 words — < 1%
Crossref

23 A. Patlolla, E. V. Carino, S. N. Ehrlich, E. Stavitski, A. I. Frenkel. "Application of Operando XAS, XRD, 10 words — < 1%

and Raman Spectroscopy for Phase Speciation in Water Gas Shift Reaction Catalysts", ACS Catalysis, 2012

Crossref

24 Flytzani-Stephanopoulos, Maria, and Bruce C. Gates. "Atomically Dispersed Supported Metal Catalysts", Annual Review of Chemical and Biomolecular Engineering, 2012. 9 words — < 1%

Crossref

25 Chunfei Wu. "Nickel-based catalysts for tar reduction in biomass gasification", Biofuels, 07/2011 9 words — < 1%

Crossref

26 Xun Hu, Zhanming Zhang, Mortaza Gholizadeh, Shu Zhang, Chun Ho Lam, Zhe Xiong, Yi Wang. "Coke Formation during Thermal Treatment of Bio-oil", Energy & Fuels, 2020 9 words — < 1%

Crossref

27 Robert Quinn, Thomas A. Dahl, Barry W. Diamond, Bernard A. Toseland. "Removal of Arsine from Synthesis Gas Using a Copper on Carbon Adsorbent", Industrial & Engineering Chemistry Research, 2006 9 words — < 1%

Crossref

28 Xiaofei Lu, Yang Liu, Yurong He, Andrew N. Kuhn, Pei-Chieh Shih, Cheng-Jun Sun, Xiaodong Wen, Chuan Shi, Hong Yang. "Cobalt-Based Nonprecious Metal Catalysts Derived from Metal–Organic Frameworks for High-Rate Hydrogenation of Carbon Dioxide", ACS Applied Materials & Interfaces, 2019 9 words — < 1%

Crossref

29 www.arl.army.mil 9 words — < 1%

Internet

30 www.dtic.mil 8 words — < 1%

Internet

31 Bonan Liu, Qiuyun Zong, Peter P. Edwards, Fei Zou, Xian Du, Zheng Jiang, Tiancun Xiao, Hamid AlMegren. " Effect of Titania Addition on the Performance of CoMo/Al O Sour Water Gas Shift Catalysts under Lean Steam to

Gas Ratio Conditions ", Industrial & Engineering Chemistry
Research, 2012

Crossref

32 www.authormapper.com 8 words — < 1%
Internet

33 asmedigitalcollection.asme.org 8 words — < 1%
Internet

34 Panagiotopoulou, Paraskevi, Dimitris I. Kondarides, and X. E. Verykios. "Chemical Reaction Engineering and Catalysis Issues in Distributed Power Generation Systems", Industrial & Engineering Chemistry Research, 2011. 8 words — < 1%
Crossref

35 www.micromeritics.com 8 words — < 1%
Internet

36 doc-test.utsp.utwente.nl 8 words — < 1%
Internet

37 Mathure, Pankaj V., Shouvik Ganguly, Anand V. Patwardhan, and Ranajit K. Saha. "Steam Reforming of Ethanol Using a Commercial Nickel-Based Catalyst", Industrial & Engineering Chemistry Research, 2007. 8 words — < 1%
Crossref

38 "Handbook of Heterogeneous Catalysis", Wiley, 1997 8 words — < 1%
Crossref

39 repository.nwu.ac.za 8 words — < 1%
Internet

40 Magdalena Oćwieja, Adam Węgrzynowicz, Julia Maciejewska-Prończuk, Piotr Michorczyk et al. "Preparation of iron oxide nanoparticles doped by chromium for application in water–gas shift reaction", Colloids and Surfaces A: Physicochemical and Engineering Aspects, 2017 7 words — < 1%
Crossref

41 Y Tanaka. "Methanation of Carbon Monoxide with Water over

Supported Rhodium Catalysts.", Australian Journal of Chemistry, 1985 7 words — < 1%

Crossref

42 Raul Perez-Hernandez, Demetrio Mendoza-Anaya, Albina Gutierrez, Antonio Gomez-Cortes. "Chapter 6 Catalytic Steam Reforming of Methanol to Produce Hydrogen on Supported Metal Catalysts", IntechOpen, 2012 7 words — < 1%

Crossref

43 Vincenzo Palma, Filomena Castaldo, Paolo Ciambelli, Gaetano Iaquaniello. "Chapter 11 Sustainable Hydrogen Production by Catalytic Bio-Ethanol Steam Reforming", IntechOpen, 2012 7 words — < 1%

Crossref

44 Christos M. Kalamaras, Ines D. Gonzalez, Rufino M. Navarro, José Luis G. Fierro, Angelos M. Efstathiou. "Effects of Reaction Temperature and Support Composition on the Mechanism of Water–Gas Shift Reaction over Supported-Pt Catalysts", The Journal of Physical Chemistry C, 2011 7 words — < 1%

Crossref

45 C. M. Kalamaras, D. D. Dionysiou, A. M. Efstathiou. "Mechanistic Studies of the Water–Gas Shift Reaction over Pt/Ce Zr O Catalysts: The Effect of Pt Particle Size and Zr Dopant ", ACS Catalysis, 2012 6 words — < 1%

Crossref

46 Rosana G Moreira. "Impingement drying of foods using hot air and superheated steam", Journal of Food Engineering, 2001 6 words — < 1%

Crossref

47 Michael D. Dukes, Calvin Perry. "Uniformity testing of variable-rate center pivot irrigation control systems", Precision Agriculture, 2006 6 words — < 1%

Crossref

EXCLUDE
BIBLIOGRAPHY

ON