

PAPER • OPEN ACCESS

13th Joint Conference on Chemistry (13th JCC)

To cite this article: 2019 *IOP Conf. Ser.: Mater. Sci. Eng.* **509** 011001


View the [article online](#) for updates and enhancements.



IOP | ebooks™

Bringing you innovative digital publishing with leading voices to create your essential collection of books in STEM research.

Start exploring the collection - download the first chapter of every title for free.

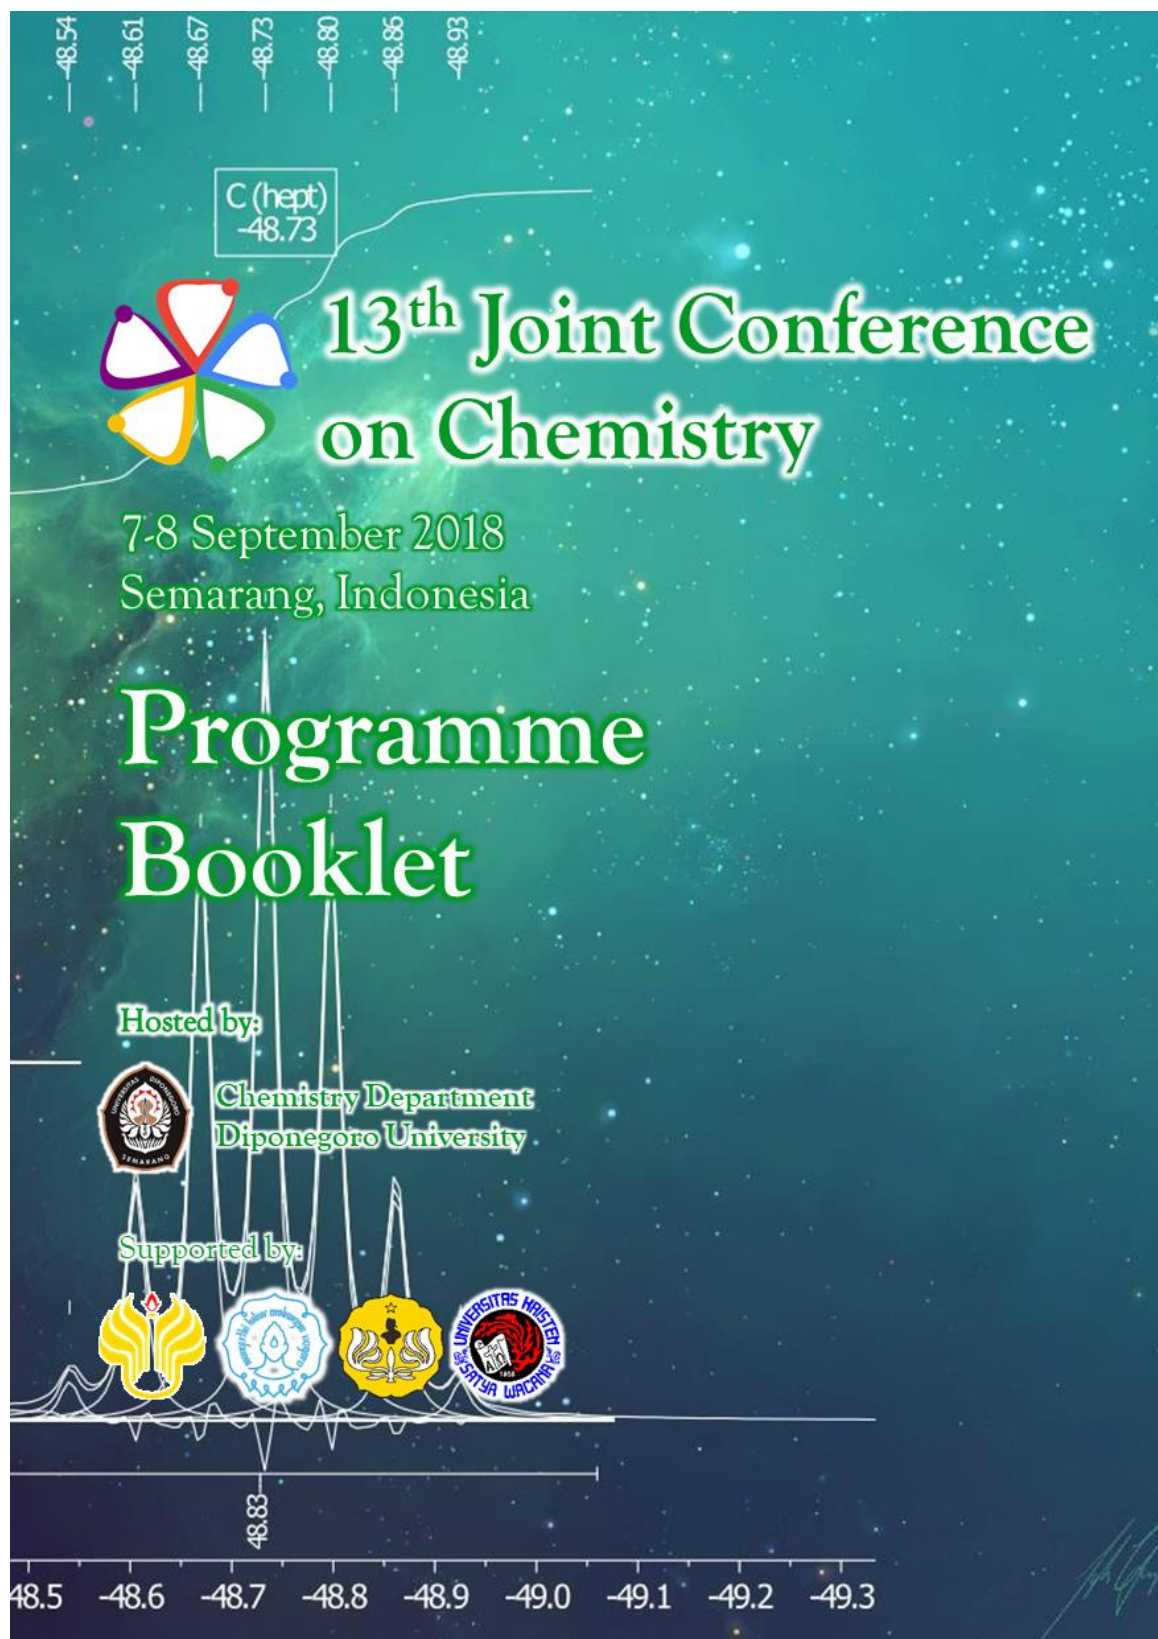



13th Joint Conference on Chemistry

7-8 September 2018
Semarang, Indonesia

Preface

On behalf of the Consortium of Chemistry Department in Central Java, Indonesia and the JCC Committee, I would like to thank you for your participation in the 13th Joint Conference on Chemistry which to be held from 7-8th September 2018 in Semarang, Indonesia. The Joint Conference on Chemistry is an annual conference organized by the consortium of Chemistry Department of five universities in Central Java: Diponegoro University (UNDIP), State University of Semarang (UNNES), Sebelas Maret University (UNS), Jenderal Soedirman University (UNSOED) and Satya Wacana Christian University (UKSW). The JCC has been held since 2006.

This conference provides an interactive international forum to provide for sharing and exchange information on the latest research on Chemistry and related sciences, to enhance the capacities for creating innovation system, to contribute in the formulation of global strategies in advancing science role as well as developing policy initiatives in community, to stimulate future collaborations among industries, researchers, governments and other stakeholders who apply science and technology for better live. The speakers and participants of the 13th JCC are up to 250 coming from various countries extending from Indonesia, Malaysia, Philippine, Australia, South Korea, Japan, Iran, Nigeria, UK and India.

We received nearly 200 papers submitted to be included in the proceedings of this conference and after the review and revision process we finally got 158 papers to be published

I would like to thank for the endeavour of committee from Chemistry Department - UNDIP and the consortium member. In addition, the conference committee acknowledges the technical and financial support from Diponegoro University.

Adi Darmawan, Ph.D

The Chair of 13th Joint Conference of Chemistry

Chemistry Department, Faculty of Science and Mathematics, Diponegoro University

Committee


- Chairman : Adi Darmawan, PhD (Diponegoro University, Semarang, Indonesia)
Secretary : Yayuk Astuti, M.Si (Diponegoro University, Semarang, Indonesia)
Treasurer : Dr. Choiril Azmiyawati, M.Si (Diponegoro University, Semarang, Indonesia)
Program : Dr. Agustina L. N. Aminin, M.Si (Diponegoro University, Semarang, Indonesia)
Nor Basid Adiwibawa Prasetya, Ph.D (Diponegoro University, Semarang, Indonesia)
Scientific : M. Alauhdin, PhD (Universitas Negeri Semarang, Indonesia)
Hartiwi Diastuti, S.Si., M.Si (Universitas Jenderal Soedirman, Indonesia)
Dr. Soerya Dewi Marliyana, S.Si.,M.Si. (Sebelas Maret University, Indonesia)
November Rianto Aminu, S.Si., M.Sc (Universitas Kristen Satyawa Wacana, Indonesia)

Advisory Board

1. Dr. Lidija Siller (Newcastle University, UK)
2. Dr. Mehrorang Ghaedi (Yasouj University, Iran)
3. Dr. Ratna Balgis (Hiroshima University, Japan)
4. Dr. Simon Kane Smart (The University of Queensland, Australia)
5. Prof. Eiji Osawa (NanoCarbon Research Institute, Japan)
6. Prof. Fadzilah Adibah Abdul Majid (Universiti Malaysia Terengganu, Malaysia)
7. Prof. Insung S. Choi (KAIST - Korea Advanced Institute of Science and Technology, Korea)
8. Prof. Rizwan Hasan Khan (Aligarh Muslim University, Aligarh, India)
9. Dr. Dwi Hudyanti, M.Sc (Diponegoro University, Semarang, Indonesia)
10. Dr. Ismiyanto (Diponegoro University, Semarang, Indonesia)
11. Dr. Khairul Anam (Diponegoro University, Semarang, Indonesia)

Documentation



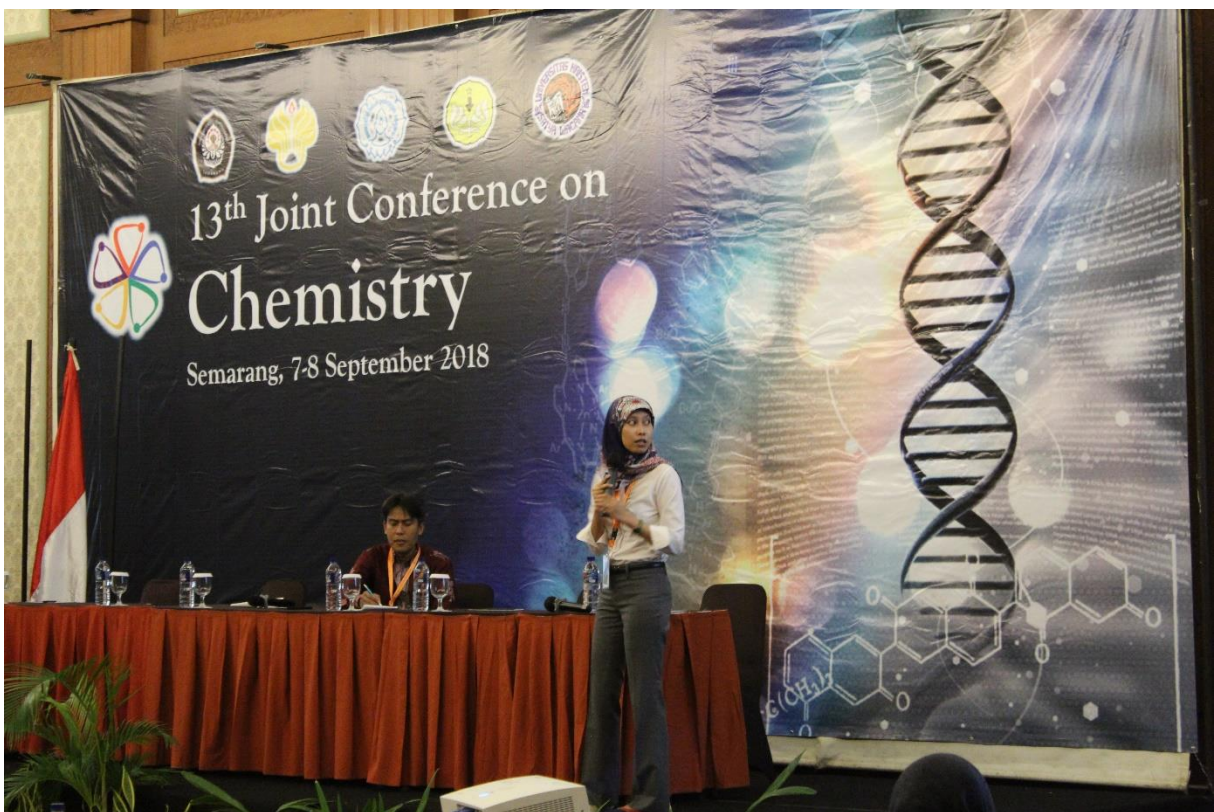

PAPER • OPEN ACCESS

Peer review statement

To cite this article: 2019 *IOP Conf. Ser.: Mater. Sci. Eng.* **509** 011002

View the [article online](#) for updates and enhancements.



IOP | ebooksTM

Bringing you innovative digital publishing with leading voices to create your essential collection of books in STEM research.

Start exploring the collection - download the first chapter of every title for free.

Peer review statement

All papers published in this volume of *IOP Conference Series: Materials Science and Engineering* have been peer reviewed through processes administered by the proceedings Editors. Reviews were conducted by expert referees to the professional and scientific standards expected of a proceedings journal published by IOP Publishing.



**SJR**

Scimago Journal & Country Rank

Enter Journal Title, ISSN or Publisher Name

[Home](#)[Journal Rankings](#)[Country Rankings](#)[Viz Tools](#)[Help](#)[About Us](#)

IOP Conference Series: Materials Science and Engineering

Country[United Kingdom](#) - [SJR Ranking of United Kingdom](#)**Subject Area and Category**[Engineering](#)
[Engineering \(miscellaneous\)](#)[Materials Science](#)
[Materials Science \(miscellaneous\)](#)**Publisher****Publication type**[Conferences and Proceedings](#)**ISSN**

17578981, 1757899X

Coverage

2009-ongoing

Scope

The open access IOP Conference Series provides a fast, versatile and cost-effective proceedings publication service for your conference. Key publishing subject areas include: physics, materials science, environmental science, bioscience, engineering, computational science and mathematics.

[Homepage](#)[How to publish in this journal](#)[Contact](#)[Join the conversation about this journal](#)

24







H Index

SJR



Citations per document



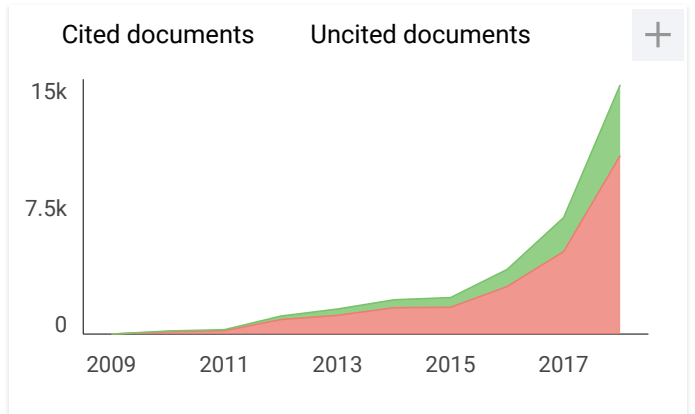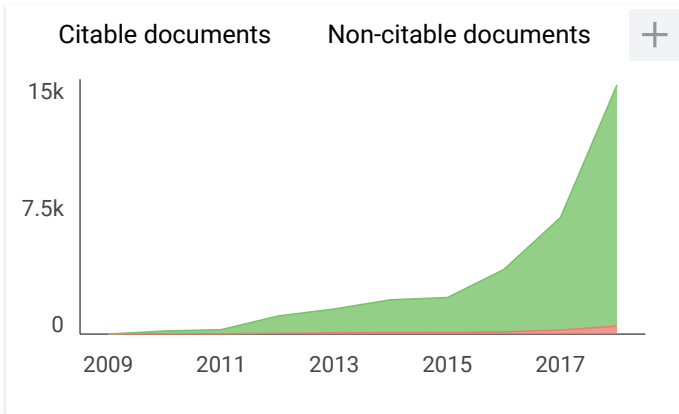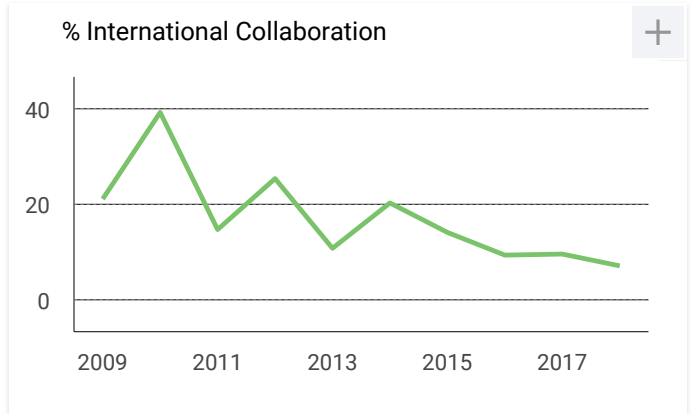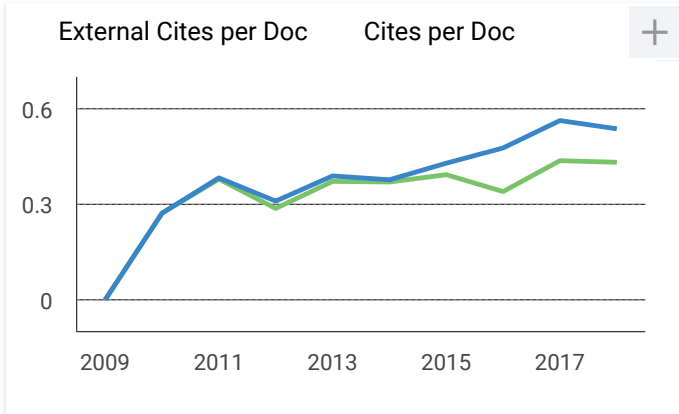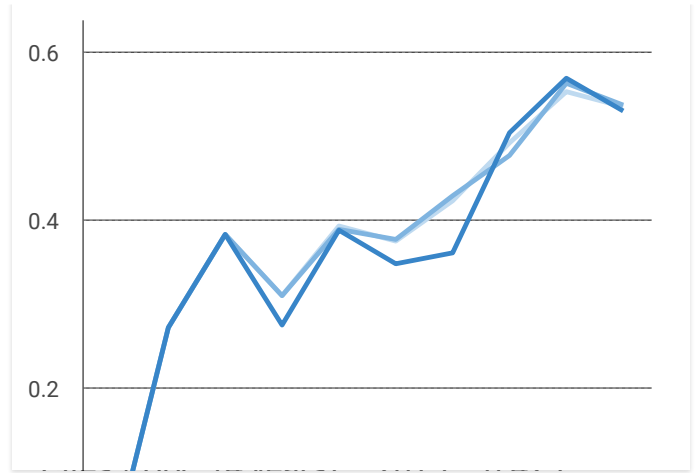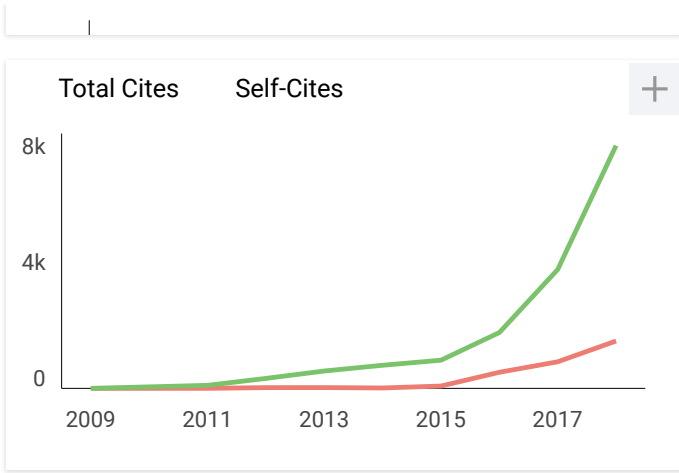

IOP Conference Series: Materials Science and...

Not yet assigned quartile

SJR 2018
0.19

powered by scimagojr.com

← Show this widget in your own website

Just copy the code below and paste within your html code:

```
<a href="https://www.scimaç
```

P **PARU** 1 month ago

IOP CONFERENCE SERIES A BOOK OR JOURNAL.

reply



Source details

IOP Conference Series: Materials Science and Engineering

Scopus coverage years: from 2009 to 2019

ISSN: 1757-8981 E-ISSN: 1757-899X

Subject area: [Engineering: General Engineering](#) [Materials Science: General Materials Science](#)

[View all documents >](#)

[Set document alert](#)

[Save to source list](#) [Journal Homepage](#)

CiteScore 2018

0.53



SJR 2018

0.192



SNIP 2018

0.531



[CiteScore](#) [CiteScore rank & trend](#) [CiteScore presets](#) [Scopus content coverage](#)

CiteScore 2018 ▼

Calculated using data from 30 April, 2019

CiteScore rank ⓘ

$$0.53 = \frac{\text{Citation Count 2018}}{\text{Documents 2015 - 2017*}} = \frac{7,820 \text{ Citations } >}{14,668 \text{ Documents } >}$$

*CiteScore includes all available document types

[View CiteScore methodology >](#)

[CiteScore FAQ >](#)

Category	Rank	Percentile
Engineering		
General Engineering	#171/275	38th
Materials Science		
General Materials Science	#305/438	30th

CiteScoreTracker 2019 ⓘ

Last updated on 06 February, 2020
Updated monthly

$$0.54 = \frac{\text{Citation Count 2019}}{\text{Documents 2016 - 2018}} = \frac{15,355 \text{ Citations to date } >}{28,226 \text{ Documents to date } >}$$

[View CiteScore trends >](#)

[Add CiteScore to your site ↗](#)

Metrics displaying this icon are compiled according to Snowball Metrics ↗, a collaboration between industry and academia.

About Scopus

- [What is Scopus](#)
- [Content coverage](#)
- [Scopus blog](#)
- [Scopus API](#)
- [Privacy matters](#)

Language

- [日本語に切り替える](#)
- [切换到简体中文](#)
- [切换到繁體中文](#)
- [Русский язык](#)

Customer Service

- [Help](#)
- [Contact us](#)

This site uses cookies. By continuing to use this site you agree to our use of cookies. To find out more, see our Privacy and Cookies policy.



⚠ NOTICE: Our engineering team is currently investigating significant increases in our website traffic. As they do so, it is possible that you will experience a degraded performance on IOPscience. We appreciate your patience as we work to resolve this situation

Table of contents

Volume 509

2019

[◀ Previous issue](#) [Next issue ▶](#)

13th Joint Conference on Chemistry (13th JCC) 7–8 September 2018, Semarang, Indonesia

Accepted papers received: 08 March 2019

Published online: 03 May 2019

[View all abstracts](#)

Preface

OPEN ACCESS

011001

13th Joint Conference on Chemistry (13th JCC)

[+ View abstract](#)

[View article](#)

[PDF](#)

OPEN ACCESS

011002

Peer review statement

[+ View abstract](#)

[View article](#)

[PDF](#)

Mechanical properties improvement in silica-filled natural rubber composites using stearyl alcohol

Indra Surya, Mimpin Ginting and Vivi Purwandari

[+](#) [View abstract](#) [View article](#) [PDF](#)

OPEN ACCESS

012055

Synthesis and antibacterial activity test of 3-(3-(4-hydroxy-3-methylphenyl)akriloil) coumarin compounds

Ismiyarto, Fida Hidayatul Rafi'ah, Novianita Rizky, Nor Basid Adiwibawa Prasetya, Purbowatiningrum Ria Sarjono and N gadiwiyana

[+](#) [View abstract](#) [View article](#) [PDF](#)

OPEN ACCESS

012056

Synthesis of polymer hybrid latex polystyrene methylmethacrylate-co-butylacrylate with organo-montmorillonite as filler through miniemulsion polymerization for barrier paper application

Johannes Chanra, Emil Budianto and Bambang Soegijono

[+](#) [View abstract](#) [View article](#) [PDF](#)

OPEN ACCESS

012057

Surface modification of montmorillonite by the use of organic cations via conventional ion exchange method

Johannes Chanra, Emil Budianto and Bambang Soegijono

[+](#) [View abstract](#) [View article](#) [PDF](#)

OPEN ACCESS

012058

Capability of immobilised glucoamylase on mesostructured cellular foam silica to hydrolyse tapioca starch

Joni Agustian and Lilis Hermida

[+](#) [View abstract](#) [View article](#) [PDF](#)

OPEN ACCESS

012059

Mesostructured cellular foam MCF-(9.2T-3D) silica as support for free α -amylase in liquefaction of tapioca starch

Joni Agustian and Lilis Hermida

PAPER • OPEN ACCESS

Capability of immobilised glucoamylase on mesostructured cellular foam silica to hydrolyse tapioca starch

To cite this article: Joni Agustian and Lilis Hermida 2019 *IOP Conf. Ser.: Mater. Sci. Eng.* **509** 012058

View the [article online](#) for updates and enhancements.



IOP | ebooks™

Bringing you innovative digital publishing with leading voices to create your essential collection of books in STEM research.

Start exploring the collection - download the first chapter of every title for free.

Capability of immobilised glucoamylase on mesostructured cellular foam silica to hydrolyse tapioca starch

Joni Agustian^{1,a}, Lilis Hermida^{1,b}

¹ Department of Chemical Engineering, Universitas Lampung, Jl. S. Brodjonegoro No. 1, Gedung Meneng, Rajabasa, Bandar Lampung 35145, Lampung, Indonesia. Email: ^a joni.agustian@eng.unila.ac.id; ^b lilis.hermida@eng.unila.ac.id

Abstract. Mesoporous size siliceous-based materials have been associated with immobilisation of free glucoamylase and soluble starches hydrolysis. As ethanol and other chemicals can be produced from insoluble feed such as tapioca, understanding of glucoamylase immobilised on mesostructured cellular foam (MCF) silica to hydrolyse the starch is required. To get the knowledge on this process for development of a large-scale operation, free glucoamylase SQzyme AGP was immobilised on MCF silica (9.2T-3D) by direct adsorption and used the product to hydrolyse tapioca. The free enzyme was able to be immobilised onto the carrier with the efficiencies of 39.20-84.84% where the operational factors of temperature, agitation speed and pH affected the immobilisation process highly. During the enzymatic hydrolysis, effects of temperature and agitation speed were high. The dextrose equivalent (DE) values of 1.21-81.70% were obtained. The optimum temperature and agitation speed were 70°C and 140 rpm. Other factors such as buffer pH, starch concentration and enzyme unit activity showed low effects on the hydrolysis process. Excellent DE were obtained at the conditions of pH, tapioca concentration and enzyme unit activity of 4.6, 3 mg mL⁻¹ and 2351 U, respectively.

Keywords: Silica-based support; Enzyme immobilisation; Tapioca hydrolysis

1. Introduction

Various insoluble supports were developed for free glucoamylase via different methodologies. Nano-magnetic materials, carbon, cellulose beads, montmorillonite, polymers, gelatine, and alginate had been used to support the enzyme via adsorption, covalent bonding, entrapment or encapsulation [1-7]. The resulted immobilised glucoamylase showed better thermal and pH stability than the free type.

One of the supports having mesoporous sizes is siliceous-based materials. Mesoporous silica particles prepared from tetraethoxysilane and phenyltriethoxysilane encapsulated free glucoamylase successfully where the product could be used for many cycles in a soluble starch hydrolysis process [8]. Ordered mesoporous silicas were employed to support free glucoamylase capable of hydrolysing soluble starch highly [9, 10]. Szymańska *et al.* [11] immobilised free glucoamylase on mesostructured cellular foam silica where the immobilised glucoamylase showed higher enzymatic activity in hydrolysing a soluble starch.

Since only soluble starches were hydrolysed in order to examine capability of glucoamylase immobilised on siliceous-based supports, a study on tapioca saccharification using glucoamylase immobilised on mesostructured cellular foam (MCF) silica is considered important as knowledge on this process is needed to develop large-scale operations. Therefore, a report on this process is herewith presented to observe characteristics of the factors during the enzymatic hydrolysis.



2. Experimental Method

2.1. Chemicals and Biochemical

Pluronic® P123 (435465), mesitylene (>98%), tetraethylorthosilicate (>99%) and sodium acetate (>98%) were purchased from Sigma via local suppliers. Ammonium fluoride (>98%), HCl (37%), disodium hydrogen phosphate dodecahydrate (>99%), D(+)-glucose monohydrate (>99%) and potassium dihydrogen phosphate (>99%) were supplied by Merck Glucoamylase SQzyme AGP (150,000 U g⁻¹) were provided by a local importer. Tapioca starch (Rose brand) was bought from a local supermarket.

2.2. Synthesis of MCF Silica (9.2T-3D)

Method developed by Hermida *et al.* [12] was used. Pluronic (4 g) was dissolved in 70 mL HCl (1.6 M) at ambient temperature in a flask. Mesitylene (3.4 mL) was added. This mixture was stirred at 750 rpm and 40°C for 2 hours. After 9.2 mL tetraethyl orthosilicate was poured, it was stirred at 1,000 rpm for 5 minutes and later kept in water bath for 20 hours at 40°C. NH₄F (5 mL, 46 mg per 5 mL) was pipetted under slow stirring. It was kept in water bath for 72 hours at 80°C and then cooled to ambient temperature. After the filtration process, the crystals were dried at 100°C for 12 hours. They were calcined at 300°C for 30 minutes and continued at 500°C for 6 hours to give the MCF silica.

2.3. Immobilisation Process

The process was conducted via adsorption of free glucoamylase onto MCF silica (9.2T-3D) surfaces. The free enzyme (30-150 mg) was dissolved in some Sorensen phosphate buffer 100 mM (pH of 5-7). Then, 500 mg MCF silica was added in. The mixture was placed in water bath shaker (Medline BS-31) and shaken (80-140 rpm). Various shaker temperatures were employed (30-50°C). After 5 hours, the mixture was filtered (Whatman#42 filter paper). The filtrate was kept in refrigerator before protein analysis was conducted, whilst residue was washed with Sorensen buffer (3x50 mL) based on pH of the immobilisation process. The residue was dried at temperature of 35-40°C overnight and after that kept in desiccator. The filtrate from the washing process was also kept in refrigerator before analysing the protein content. The dried immobilised enzyme was stored in a refrigerator. Amount of free enzyme on support was calculated as follow:

$$\text{Immobilised Enzyme (\%)} = \frac{(C_0 - C_t)}{C_0} \times V \times 100 \quad (1)$$

$$q = \frac{(C_0 - C_t) \times V}{W} \quad (2)$$

where C₀ is initial free enzyme concentration (mg mL⁻¹), C_t is final free enzyme concentration (mg mL⁻¹), V is reactor working volume (mL), q is amount of enzyme onto MCF silica (mg g⁻¹) and W is weight of support (g). Buffer pH, temperature, agitation speed and enzyme concentration were varied using one-factor-at-a-time (OFAT) design.

2.4. Batch studies on hydrolysis of tapioca starch using immobilized α-amylase

OFAT was used to study activity of the immobilised glucoamylase in tapioca starch hydrolysis. Sodium acetate buffer (30 mL, 100 mM, pH 4.0-6.0) was poured into some 100 mL Erlenmeyer. Tapioca powder was added at concentration of 3-16 mg mL⁻¹. The immobilised glucoamylase (2351-7053 U) was mixed with the starch solution. The solution was shaken in water bath shaker at constant speed (140 rpm) for 24 hours at a certain temperature (35-60°C). Samples were withdrawn at certain interval times and then observed their reducing sugar. To compare the immobilised enzyme, the tapioca hydrolysis using free glucoamylase were also conducted under the same conditions.

2.5. Estimation of protein and glucose

Pierce™ BCA protein assay kit was used to estimate protein content by using the standard method provided by the kit manufacturer. Hydrolysis of starch to glucose was determined by the DNSA

(dinitrosalicylic acid) method. The enzyme contents and glucose samples were observed using spectrometer Shimadzu UV-VIS 1800.

2.6. Characterization (FTIR, SEM, EDX)

Nitrogen adsorption-desorption isotherm data were obtained using a Quanta-chrome Autosorb 1C automated gas sorption analyser operated at liquid nitrogen temperature to estimate average cell pore size, average window pore size, specific pore volume and specific surface area (S_{BET}). Average cell pore size was evaluated using Barrett-Joyner-Halenda (BJH) method from the adsorption branch of the isotherm data. Average window pore size was evaluated using BJH method from the desorption branch. S_{BET} was calculated using Brunauer-Emmett-Teller (BET) method. Samples (support and enzyme) were analysed using Zeiss EVO field emission scanning electron microscope (SEM), equipped with an Oxford INCA X act, energy dispersive X-ray (EDX) microanalysis system, to obtain SEM images and chemical compositions. Samples were also observed by Frontier Perkin Elmer FTIR.

3. Results and Discussion

Textural properties of MCF silica (9.2T-3D) matrix are shown in **Table 1**. The average window pore and cell sizes of it were 158 Å and 235 Å, respectively, confirming the mesoporous structure of the matrix. The window pores and cell sizes should allow favourable conditions for access and immobilization of the glucoamylase enzyme due to the enzyme size (usually 80 Å) is lower than the support size. Adsorption of the enzyme onto the support surfaces was confirmed by SEM (**Fig. 1**). The figure indicated that the support was in the form of spherical particles with smooth surfaces. Immobilization of the free enzyme on the support resulted in rough surfaces on the spherical material (**Fig. 1-B**). Such morphological changes could be due to the organic material of the enzyme that was adsorbed on these surfaces. The adsorption of the enzyme was also determined by FT-IR.

Table 1. Nitrogen adsorption-desorption result.

S_{BET} ($\text{m}^2 \text{g}^{-1}$)	V_{pore} ($\text{cm}^3 \text{g}^{-1}$)	d_{cell} (Å)	d_{window} (Å)
378	2.12	235	158

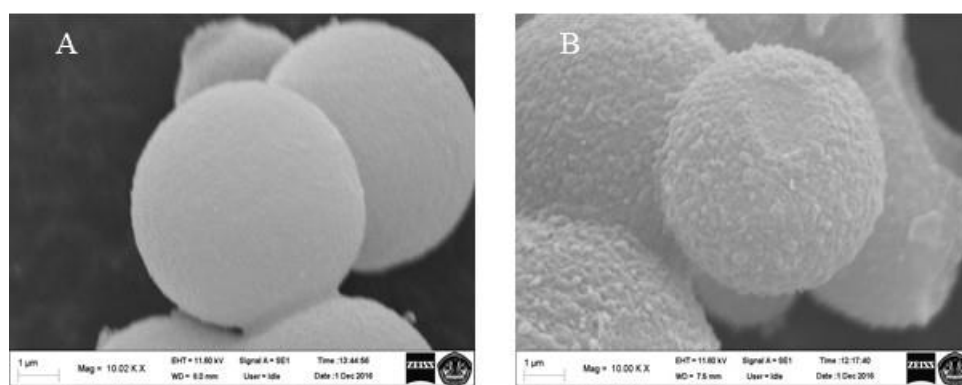


Figure 1. SEM images: A. MCF (9.2T-3D) silica, B. Glucoamylase on support.

FT-IR spectrum of the immobilized glucoamylase was compared with that of original support (**Fig. 2**). The spectrum of the support showed its vibrations at 1300 cm^{-1} and 850 cm^{-1} with peak at 1061 cm^{-1} to indicate Si–O–Si stretching vibrations. The vibrations were also observed on the immobilized glucoamylase, but additional vibrations at 2020 cm^{-1} , 1962 cm^{-1} and 1900 cm^{-1} were found, which were not noticed on the support. Based-on the reference, the vibration at 1962 cm^{-1} confirmed the C≡N or C≡C bounds [13]. As glucoamylase is a protein consisting amino acids, this vibration indicated the presence of amino acid on the support. EDX analysis on the support verified that it contained Si and O

elements at 1.75 keV and 0.35 keV, respectively (**Fig. 3**). However, the immobilized enzyme showed elements of C and K besides Si and O. Based on both spectra, a successful glucoamylase immobilization was obtained.

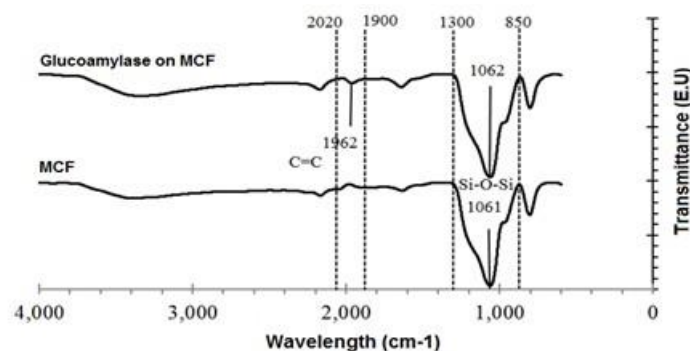


Figure. 2. FTIR spectra of support and glucoamylase.

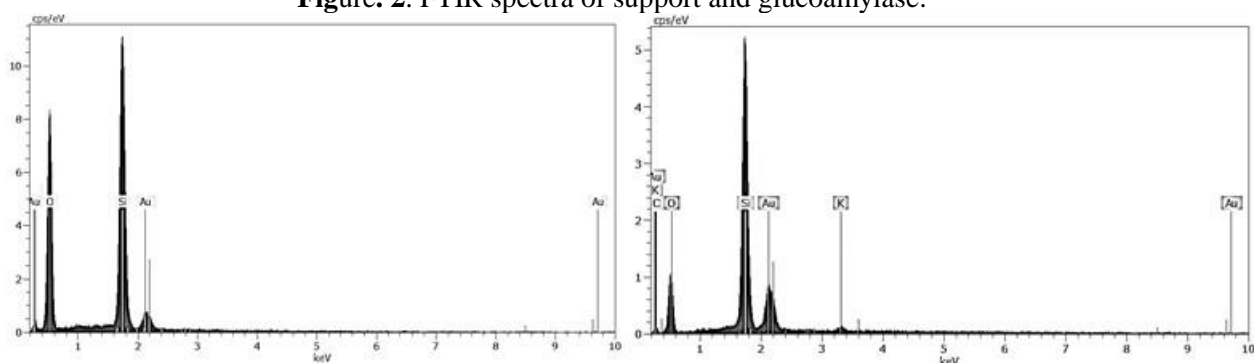


Figure. 3. EDX spectra (*left*: MCF (9.2T-3D); *right*: glucoamylase on support).

3.1. Immobilisation of glucoamylase

All immobilisation factors show high effects on the process as shown in **Table 2** where the efficiency varied highly. The increase of pH tended to decrease the result. The optimum efficiency was achieved at pH 5.5 to result 84.84% (101.81 mg g^{-1}). The optimum pH is in agreement with the previous observations that used the acetate buffer pH 5.5 to obtain high immobilised glucoamylase [2, 14] When the free glucoamylase concentrations were arranged at $0.5\text{--}3 \text{ mg mL}^{-1}$, the efficiencies were found at 26.26–84.84% where the optimum value was given by the initial concentration of 2.0 mg mL^{-1} . The initial concentrations of 2.0–2.5 were frequently used to immobilise this enzyme on carbon or a magnetic support [2, 15]. The efficiency decreased when the temperature was increased. The best result was found at 30°C where 84.84% ($\sim 102 \text{ mg g}^{-1}$) of free enzyme was adsorbed. High temperatures tended to give low results. At temperatures of 40°C , the result only differed slightly with the highest value ($< 6\%$), so that the process could be run at this temperature if it is difficult to operate the process at 30°C . Generally, the highest efficiencies of free glucoamylase immobilisation on inorganic supports were obtained at 30°C [2, 9]. The optimum result from various agitation speeds was obtained at 100 rpm. High agitation speeds reduce the efficiency. Although high contact between free enzyme and the MCF silica could occur at high speeds, as the process was based-on the direct adsorption that frequently has weak bonds, high speeds could disrupt the attached free enzymes and move them away from the support. Similarly, at low speeds, low contacts occurred, hence the free enzyme was difficult to land on the support, which resulted low efficiencies. Previous works used speed of 200 rpm. George *et al.* [9] and George and Sugunan [10] employed this speed to immobilise free glucoamylase on amino functionalised mesoporous silica compounds such SBA-15 and MPS where the free glucoamylase bonded covalently onto the supports.

Table 2. Immobilization efficiency and enzyme loading.

Operational Factors	Immobilisation Efficiency (%)	Enzyme Loading (mg g ⁻¹)
Temperature ^a	30°C	84.84
	35°C	78.80
	40°C	77.67
	45°C	66.00
	50°C	56.73
Agitation Speed ^b	80 rpm	58.91
	100 rpm	84.84
	120 rpm	58.08
	140 rpm	59.21
Buffer pH ^c	5.0	62.91
	5.5	84.84
	6.0	57.22
	6.5	47.47
	7.0	39.21
Enzyme Concentration ^d	0.5 mg mL ⁻¹	26.60
	1.0 mg mL ⁻¹	67.43
	2.0 mg mL ⁻¹	84.84
	3.0 mg mL ⁻¹	54.73

^a: agitation speed: 100 rpm, buffer pH: 5.5, enzyme concentration: 2 mg mL⁻¹; ^b: temperature: 30°C, buffer pH: 5.5, enzyme concentration: 2 mg mL⁻¹; ^c: temperature: 30°C, agitation speed: 100 rpm, enzyme concentration: 2 mg mL⁻¹; ^d: temperature: 30°C, agitation speed: 100 rpm, buffer pH: 5.5

3.2. The enzymatic hydrolysis of tapioca starch

Direct conversions of tapioca into glucose molecules using glucoamylase immobilised on the MCF silica (9.2T-3D) working under various Sorensen phosphate buffer pHs are shown in **Fig.4-a**. Dextrose Equivalent results (DE) were low. The highest DE was 20.11% obtained at pH 4.6. The DE increase of < 10% was developed when the reaction time was changed from 5 hours to 24 hours. Better results were found at pH ≤ 5.0; hence increasing buffer pH would decrease tapioca conversion (the optimum pH for glucoamylase enzyme is 4.5-5.0. The maximum DE given by the immobilised enzyme was less than half of the conversion produced by free enzyme that resulted DE as high as 57.36%. During the glucoamylase immobilisation via adsorption, the random immobilisation caused all enzyme catalytic sites may not be available for the substrate [16] that cause in low activity of the enzyme [17] as their active sites may be blocked from substrate accessibility, multiple point-binding may occur, or the enzyme may be denatured [18] or the glucoamylase gets inactivated partially [10]. The optimum pH found in the experiments differed slightly with the previous observations. Hydrolysis of 30% (w/w) cassava maltodextrin using glucoamylase immobilised on chicken bone was conducted in 50 mM sodium acetate buffer pH 4.5 [19]. Kovalenko *et al.* [15] and Kovalenko and Perminova [4] used 50 mM acetate buffer pH of 4.5-5.0 in hydrolysis of dextrin using glucoamylase immobilised on inorganic supports.

Tapioca concentration had low effects on DE for both glucoamylase forms (**Fig. 4-left**). The immobilised enzyme still produced lower DE than its opponent. DE values resulted by it were 9.29-19.39%, whilst free enzyme gave DE of 23.79-56.80%. These results indicated that activity of the immobilised glucoamylase in direct hydrolysis of tapioca flour (meaning no gelatinisation was conducted previously) decreased after immobilisation. But, both enzymes showed the same phenomenon: reductions of conversion were observed when tapioca concentrations were increased. Maximum DE given by the immobilised enzyme was developed by the lowest tapioca concentration (3 mg mL⁻¹), but the free enzyme developed high DE at the starch concentration of ≤ 5 mg mL⁻¹. The DE were almost constant when high tapioca concentrations were used (8-16 mg mL⁻¹), although small changes were observed. Previous experiments had indicated effects of substrate concentrations on activity of immobilised glucoamylase. High reaction rate of hydrolysis of soluble starch increased rapidly at low starch concentrations [1, 5, 20].

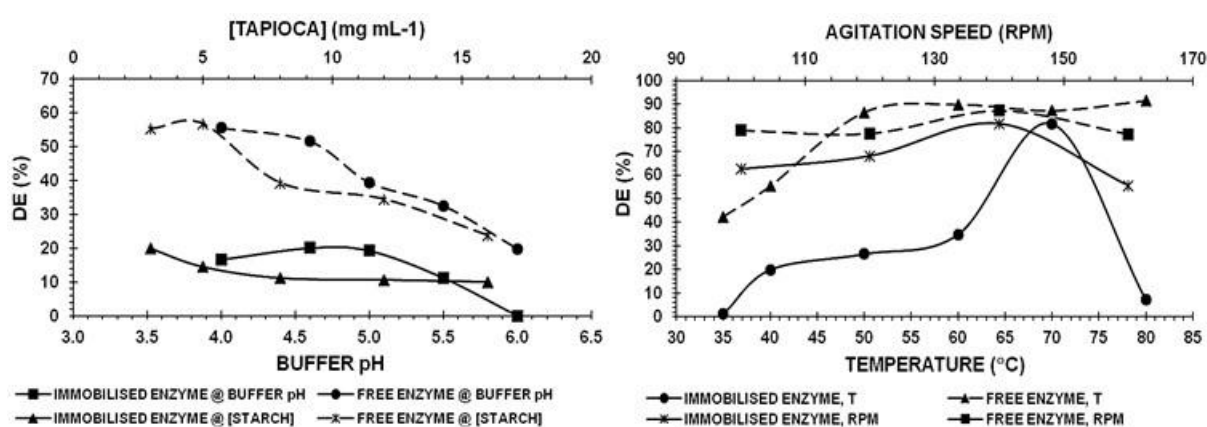


Figure 4. Effects of hydrolysis parameters after 24 hours: **pH** (T: 40°C, agitation: 140 rpm, immobilised enzyme: 2351 U, free enzyme: 7053 U), **starch concentration** (T: 40°C, agitation: 140 rpm, buffer: 100 mM pH 4.6, immobilised enzyme: 2351 U, free enzyme: 7053 U), **temperature** (agitation: 140 rpm, buffer: 100 mM pH 4.6, tapioca: 3 mg mL⁻¹, immobilised enzyme: 2351 U, free enzyme: 7053 U), **agitation speed** (T: 70°C, buffer: 100 mM pH 4.6, tapioca: 3 mg mL⁻¹, immobilised enzyme: 2351 U, free enzyme: 7053 U).

The agitation speed showed quite high effect on the hydrolysis process using immobilised glucoamylase (**Fig. 4-right**). The highest DE was 81.70% obtained at the speed of 140 rpm. Activity of the immobilised glucoamylase was still lower than its free enzyme. Temperature affected the process highly. DE changed sharply when temperature was increased where the highest DE was found at temperature of 70°C (81.70%). Higher temperatures than the optimum value caused denaturation of the immobilised enzyme as DE dropped to below 10% at 80°C. The optimum DE produced by the immobilised enzyme closed to the free enzyme results, which had conversions of 86.61-91.51% at temperatures of 50-80°C. The optimum temperature for the immobilised glucoamylase found in the experiments differed slightly with the previous observations. George *et al.* [9] found the optimum temperatures of 30-40°C after evaluating performance of free glucoamylase immobilised onto silica materials via covalent method on soluble starch. Zhao *et al.*³ concluded the activity of immobilised glucoamylase on metal-ligand functionalized magnetic FeSBA-15 during hydrolysis of soluble starch was higher at temperatures of 55-65°C. Tardioli *et al.* [21] observed thermal inactivation of the glucoamylase immobilised onto highly activated glyoxyl-agarose supports covalently occurred at the temperatures of > 45°C.

Variation of initial enzyme concentrations resulted DE values of 9.59-19.58% (**Fig. 5**). Better DE were produced by the concentrations of 2351-4702 U. They increased rapidly using the free enzyme, but the immobilised glucoamylase showed low growth.

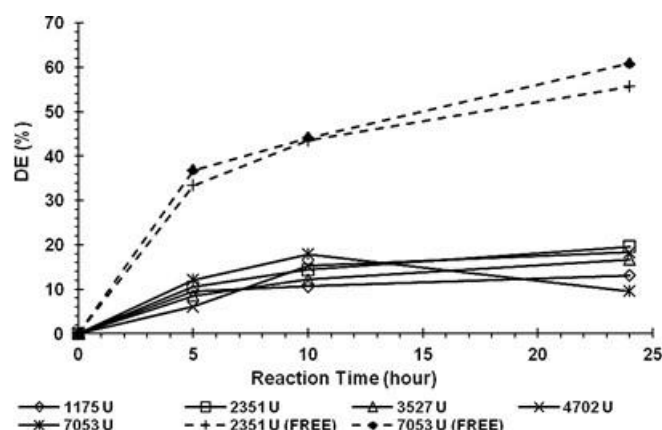


Figure 5. Values of DE at some enzyme concentrations (T: 40°C, agitation: 140 rpm, buffer: 100 mM pH 4.6, tapioca: 3 mg mL⁻¹).

4. Conclusions

The efficiencies of immobilisation of free glucoamylase on MCF silica (9.2T-3D) were found in the range of 39.20-84.84%. Factors of temperature, agitation speed and buffer pH showed high effects on this process. The optimum immobilisation temperature, agitation speed and buffer phosphate Sorensen pH were 30°C, 100 rpm and 5.5, respectively. The immobilised enzyme hydrolysed the tapioca starch, but its activity was lower than the free enzyme. From five factors studied during the enzymatic hydrolysis using immobilised glucoamylase, temperature and agitation speed gave high effects. The optimum buffer pH, tapioca flour and enzyme concentration, temperature and agitation speed were 4.6, 3 mg mL⁻¹, 2351 U, 70°C and 140 rpm.

Acknowledgements

Financial support provided by Ministry of Research, Technology and Higher Education of Indonesia through Fundamental Research Grant No. 76/UN26/8/LPPM/2016 is deeply acknowledged. Appreciation is directed to the Integrated Laboratory and Centre of Technology Innovation (UPT LTSIT) Universitas Lampung for the SEM and EDX analyses.

References

- [1] Wu Z, Qi W, Wang M, Wang Y, Su R and He Z 2013 Chelate immobilization of amylase on metal ceramic powder: Preparation, characterization and application *Biochem. Eng. J.* **77** 190-7
- [2] Chen G, Ma Y, Su P and Fang B 2012 Direct binding glucoamylase onto carboxyl-functionalized magnetic nanoparticles *Biochem. Eng. J.* **67** 120-5
- [3] Zhao G, Wang J, Li Y, Huang H and Chen X 2012 Reversible immobilization of glucoamylase onto metal-ligand functionalized magnetic FeSBA-15 *Biochem. Eng. J.* **68** 159-66
- [4] Kovalenko G A and Perminova L V 2008 Immobilization of glucoamylase by adsorption on carbon supports and its application for heterogeneous hydrolysis of dextrin *Carbohydr. Res.* **343** 7 1202-11
- [5] Kamal H, Sabry G M, Lotfy S, Abdallah N M, Rosiak J and Hegazy E s A 2007 Immobilization of glucoamylase on polypropylene fibers modified by radiation induced graft copolymerization *J. Macromol. Sci. Part A Pure Appl. Chem.* **45** 1 65-75
- [6] Tanriseven A and Ölçer Z 2008 A novel method for the immobilization of glucoamylase onto polyglutaraldehyde-activated gelatin *Biochem. Eng. J.* **39** 3 430-4
- [7] Rahim A, Noraida S, Sulaiman A, Ku Hamid K H, Rodhi M, Najwa M, Mohibah M, Hamzah F and Edama N A 2013 Nanoclay supporting materials for enzymes immobilization: kinetics investigation of free and immobilized system *Appl. Mech. Mater.* **393** 115-20

- [8] Vlad-Oros B, Preda G, Dudas Z, Dragomirescu M and Chiriac A 2007 Entrapment of glucoamylase by sol-gel technique in PhTES/TEOS hybrid matrixes *Process. Appl. Ceram.* **1** 1-2 63-7
- [9] George R, Gopinath S and Sugunan S 2013 Improved Stabilities of Immobilized Glucoamylase on Functionalized Mesoporous Silica Synthesised using Decane as Swelling Agent *Bull. Chem. React. Eng. Catal.* **8** 1 70-6
- [10] George R and Sugunan S 2014 Kinetic and thermodynamic parameters of immobilized glucoamylase on different mesoporous silica for starch hydrolysis: A comparative study *J. Mol. Catal. B Enzym.* **106** 81-9
- [11] Szymańska K, Bryjak J, Mrowiec-Białoń J and Jarzębski A B 2007 Application and properties of siliceous mesostructured cellular foams as enzymes carriers to obtain efficient biocatalysts *Microporous Mesoporous Mater.* **99** 1-2 167-75
- [12] Hermida L, Abdullah A and Mohamed A 2013 Synthesis and Characterization of Mesostructured Cellular Foam (MCF) Silica Loaded with Nickel Nanoparticles as a Novel Catalyst *Materials Sciences and Applications* **4** 1 52-62
- [13] Fayer M D 2013 *Ultrafast infrared vibrational spectroscopy*: CRC Press)
- [14] Park D, Haam S, Jang K, Ahn I-S and Kim W-S 2005 Immobilization of starch-converting enzymes on surface-modified carriers using single and co-immobilized systems: properties and application to starch hydrolysis *Process Biochem.* **40** 1 53-61
- [15] Kovalenko G, Perminova L, Plaksin G, Chuenko T, Komova O and Rudina N 2006 Immobilized glucoamylase: A biocatalyst of dextrin hydrolysis *Appl. Biochem. Microbiol.* **42** 2 145-9
- [16] Vishwanath S, Bhattacharyya D, Huang W and Bachas L 1995 Site-directed and random enzyme immobilization on functionalized membranes: kinetic studies and models *J. Memb. Sci.* **108** 1-2 1-13
- [17] Viswanath S, Wang J, Bachas L, Butterfield D and Bhattacharyya D 1998 Site-directed and random immobilization of subtilisin on functionalized membranes: Activity determination in aqueous and organic media *Biotechnol. Bioeng.* **60** 5 608-16
- [18] Butterfield D A, Bhattacharyya D, Daunert S and Bachas L 2001 Catalytic biofunctional membranes containing site-specifically immobilized enzyme arrays: a review *J. Memb. Sci.* **181** 1 29-37
- [19] Carpio C, Escobar F, Batista-Viera F and Ruales J 2011 Bone-bound glucoamylase as a biocatalyst in bench-scale production of glucose syrups from liquefied cassava starch *Food Bioprocess Tech.* **4** 4 566-77
- [20] Tanriseven A, Uludağ Y B and Doğan Ş 2002 A novel method for the immobilization of glucoamylase to produce glucose from maltodextrin *Enzyme Microb. Technol.* **30** 3 406-9
- [21] Tardioli P W, Vieira M F, Vieira A M S, Zanin G M, Betancor L, Mateo C, Fernández-Lorente G and Guisán J M 2011 Immobilization–stabilization of glucoamylase: Chemical modification of the enzyme surface followed by covalent attachment on highly activated glyoxyl-agarose supports *Process Biochem.* **46** 1 409-12



JONI AGUSTIAN <joni.agustian@eng.unila.ac.id>

Abstract Acceptance Letter

1 message

The 13th Joint Conference on Chemistry

<jcc@live.undip.ac.id>

To: joni.agustian@eng.unila.ac.id

Sat, Jun 23, 2018 at 7:17

PM

Dear Sir/Madam,

Please kindly find the enclosed file of abstract acceptance letter.

Looking forward to seeing you in the venue.

Regards,

Yayuk

Yayuk Astuti

Secretary of the 13th Joint Conference on Chemistry

email: jcc@live.undip.ac.id



 **111_Acceptance letter-Joni Agustian.pdf**
259K



JONI AGUSTIAN <joni.agustian@eng.unila.ac.id>

Final program - the 13th Joint Conference on Chemistry

1 message

The 13th Joint Conference on Chemistry

<jcc@live.undip.ac.id>

To: joni.agustian@eng.unila.ac.id

Mon, Aug 27, 2018 at 10:30

AM

Dear Bapak Joni Agustian

We would like to notify you some information regarding the 13th Joint Conference on Chemistry. Please note in detail:

1. Conference Program

We have uploaded the conference program details to the conference website. You can get information about your presentation schedule in the program booklet, as well as abstracts from keynote speakers and presenters. The program is final hence we cannot serve requests for changes of the presentation schedule.

2. Preparing posters Guidelines

For participants who will make poster presentations, please prepare a poster in A1 size with a free layout design. The committee provides stick boards and pin for attachment. Please print on a paper instead of Metromedia Technologies (MMT) cloth

3. Full paper submission deadline

For participants who have not sent a full paper for publication, we need to say that the final deadline is 5th September 2018 and there is no further extension. For those who want to revise the manuscripts, we can still receive them until that date. Please use the replace full paper facility in submission site if you want to revise your manuscripts.

4. Open Chemistry and Journal of Renewable Materials

The journal editor of the Open Chemistry and the Journal of Renewable Materials requested that the submission should be carried out directly by the author and not by the 13th JCC organizer. For this reason, for submission in Open Chemistry and Journal of Renewable Materials, please inform us as the committee hence we can organise with the journal editors. Keep in mind that there is an additional fee of € 260 for each paper accepted at Open Chemistry. For authors who will submit their papers to JRM, please ensure that your manuscripts is in accordance with the scope of the journal

5. Workshop on Materials

Accompanying the 13th JCC there is a Workshop on Materials which will be held on

Thursday, 6th September 2018 from 08.00 WIB - 15.00 WIB at the ICT Center - Diponegoro University. For participants who at the time of registration have not clicked to attend the workshop, you can attend the workshop by filling out the link listed at the workshop flyer attached in this email.

6. Sending the presentation files

To facilitate the organization of presentations, please upload your presentation files via submission site in the form of ppt, pptx or PDF. We have prepared a feature to upload presentation files there. This feature only appears if you have uploaded your full papers

7. Three minutes of presentation

For poster presenters, the best poster selection will be held. Five presenters with the highest scores based on jury and participant input, will be asked to present the results of their research within 3 minutes. Five presenters will get awards

8. Special price in Santika Premiere Hotel for the 13th JCC participants

Hotel Santika Premiere provides special prices for participants of the 13th JCC at a price of Rp.550,000 / nett for Deluxe Room. Please book directly to Santika Premiere Hotel by contacting Mr. Wahyu Pramudito for reservation. Email: wahyupramudito@semarangpremiere.santika.com or +62 856-0037-5438. Please quote that you are the participant of the 13th Joint Conference on Chemistry, 7-8th September 2018 in your communication with him

9. Conference Dinner

A conference dinner will be held on Friday, 7 September 2018 at the Santika Premiere Hotel Ballroom. We invite all participants to attend

10. Trip to Borobudur

On Saturday, 9th September 2018, a trip to Borobudur will be held and some other tourist sites. This excursion will be reserved for keynote speakers and participants who have registered.

Regards

Adi Darmawan

Chair of the 13th Joint Conference on Chemistry

email: jcc@live.undip.ac.id





JONI AGUSTIAN <joni.agustian@eng.unila.ac.id>

Review results for your paper - 13th JCC

3 messages

The 13th Joint Conference on Chemistry

Thu, Oct 11, 2018 at 11:33

<jcc@live.undip.ac.id>

AM

To: JCC - Joni Agustian <joni.agustian@eng.unila.ac.id>

Dear **Bapak Joni Agustian**

Herewith, we send the feedback from reviewers. Please revise your paper according to feedback from the reviewers and email it back to us no later than 1 week from now.

Regards

Adi Darmawan

Chair of the 13th Joint Conference on Chemistry

email: jcc@live.undip.ac.id

 [The 13th Joint Conference on Chemistry](#)

5 attachments

 **Peer Review Form - Joni Agustian - 2 - NB.docx**
14K

 **Joni Agustian - 2 - Peer Review Form - YA.docx**
30K

 **Joni Agustian - 2 - NB.doc**
1302K

 **Joni Agustian - 2 - YA.docx**
3290K

 **Joni Agustian - 2 - turnitin.pdf**
3194K

JONI AGUSTIAN <joni.agustian@eng.unila.ac.id>

Mon, Nov 5, 2018 at 6:11 AM

To: jcc@live.undip.ac.id

Dear Dr. Adi Darmawan,

Please find on the attached documents, the rebuttal and revised manuscript.

Thank you for your kind attention.

We hope it will bring a good result.

Sincerely yours,

Dr. Joni Agustian, M.Sc.
Department of Chemical Engineering, Universitas Lampung
Lampung - Indonesia

[Quoted text hidden]

2 attachments

 **Joni Agustian JOC 02 FINAL.docx**
3253K

 **Answers to reviewers 01.docx**
18K

The 13th Joint Conference on Chemistry

Tue, Nov 6, 2018 at 2:08

<jcc@live.undip.ac.id>

PM

To: JCC - Joni Agustian <joni.agustian@eng.unila.ac.id>

Dear Bapak Joni Agustian

Thank you for sending us the revised manuscript

Regards

Adi Darmawan

Chair of the 13th Joint Conference on Chemistry

email: jcc@live.undip.ac.id

 [The 13th Joint Conference on Chemistry](#)

[Quoted text hidden]



JONI AGUSTIAN <joni.agustian@eng.unila.ac.id>

13th JCC proceeding has been published

1 message

The 13th Joint Conference on Chemistry

<jcc@live.undip.ac.id>

Mon, May 6, 2019 at 11:15

AM

To: JCC - Joni Agustian <joni.agustian@eng.unila.ac.id>

Dear **Bapak Joni Agustian**

We hereby inform you that the proceeding of the 13th Joint Conference on Chemistry which held on September 7-8, 2018 in Semarang has been published in the IOP Conference series: Materials Science and Engineering volume 509.

<https://iopscience.iop.org/issue/1757-899X/509/1>

We apologize for the delay in publishing this proceeding for up to eight months from the conference day. We received 175 articles and after the review and revision process, finally there are 158 articles published. The review process ran for four months, two months for layouting and the production process in IOP itself for two months.

We thank you for your participation in the 13th Joint Conference on Chemistry in Semarang, and we hope you will also attend the next JCC series, the 14th Joint Conference on Chemistry to be held September 10-11, 2019 in Surakarta Indonesia. The 14th JCC website is <https://jcc.uns.ac.id/>

Regards

Adi Darmawan

Chair of the 13th Joint Conference on Chemistry

email: jcc@live.undip.ac.id