

Characterization of Carboxymethyl Cellulose (CMC) Synthesized from Microcellulose of Cassava Peel

By Sripto D Yuwono

Characterization of Carboxymethyl Cellulose (CMC) Synthesized from Microcellulose of Cassava Peel

SURIPTO D. YUWONO¹, ENDAH WAHYUNINGSIH^{2,3}, NOVIANY¹, AGUNG A.

ISWANDONO¹, WASINTON SIMANJUNTAK¹ AND SUTOPO HADI¹

¹ Department of Chemistry, Faculty of Mathematics and Natural Sciences, Universitas Lampung, Bandar Lampung, Indonesia

² Master Student of Chemistry, Department of Chemistry, Faculty of Mathematics and Natural Sciences, University of Lampung, Bandar Lampung, Indonesia

³ Present address: Chemistry teacher at Senior High School 1 Metro, Lampung, Indonesia

Abstract: In this study, carboxymethyl cellulose (CMC) was synthesized from the cellulose of cassava peel using alkalization and etherification reaction, and it was subsequently characterized with various techniques. Microcellulose was obtained by hydrolyzing α -cellulose from cassava peel using H_2SO_4 with concentrations of 45%, 47%, and 49%. The experimental results indicate that the varying concentrations of acid affect the particle size of the cellulose, with 49% H_2SO_4 solution producing a cellulose with particle size of around 0.45–2.42 μm and relative percentage of 11.3% according to PSA analysis. Further analyses conducted included determination of substitution degrees, DTG/DTA/TGA, FTIR, SEM, and XRD. The value of the substitution degree was determined at 0.27. TGA decomposition thermograms at a temperature of 150 °C–320 °C of 19.60 % indicate CMC compounds. DTA thermograms show that these CMC compounds have endothermic properties at 140 °C and exothermic properties at 260 °C. FTIR spectra show the presence of absorption band at wavenumber 1605 cm^{-1} , which is a characteristic absorption of carbonyl group bound to cellulose. The results of SEM analysis indicate that the CMC has a tenuous surface morphology, and the XRD diffractograms are marked by the presence of weak peak at $2\theta = 20^\circ$, implying the existence of CMC as mostly amorphous.

Keywords: cassava peel, α -cellulose, carboxymethyl cellulose

1. Introduction

Food is a basic need of every human being. Currently, Indonesia's population is around 265 million [1], making the country as the fourth most populated in the world. Having such a large number, it is no surprise that the food industry is experiencing rapid development. In addition, modern lifestyles have put food products on demand. It has become a challenge that food products not only meet the quantity needed but also the quality standard desired by its consumers. In improving food quality, various additives are used in the production process, and one of the most popular is carboxymethyl cellulose (CMC) [2].

CMC is an ionic polysaccharide derived from cellulose, which has a linear long chain and is soluble in water [3]. Currently CMC has been considered as one of the most popular additives because it is inexpensive and easy to use in many applications [4–9]. One main reason for its popularity is the availability of its raw material, since cellulose is considered to be the most abundant organic compound found naturally. Cellulose is known to contribute about 33 % of plant material, and therefore, many types of agricultural waste are potential sources of cellulose. One of them is cassava peel, which can be found in large amounts in Indonesia, but its use is very limited due to its cyanide content. Cassava peel is an attractive raw material for CMC production because this agricultural residue is known to contain 37.9% cellulose, together with hemicellulose (37%) and lignin (7.5%) [10].

Degree of substitution (DS) and molecular weight are important usability parameters of CMC. The DS is the average number of hydroxyl groups found in the cellulose structure substituted by carboxymethyl and sodium carboxymethyl groups on C-2, C-3, and C-6.

* Corresponding author: suripto.dwi@fmipa.unila.ac.id

Increasing the DS will make it more compatible with other components such as salt or other solvents, which can affect its viscosity [11].

In this study, the cellulose obtained from cassava peel was converted into microcellulose in an attempt to increase the DS of CMC produced. This procedure was adopted from a study by Arup [12], who reported the synthesis of microcellulose in four steps: acid hydrolysis, centrifugation, ultrasonication, and freeze-drying. In this research, acid hydrolysis was performed using sulfuric acid, with concentrations at 45%, 47%, and 49%. The microcellulose obtained was then used to synthesize CMC, by alkalization and etherification with NaOH concentration at 25%, in accordance with the procedure reported in the previous study [13]. In this regard, the objectives of this study were the isolation of α -cellulose from cassava peel by delignification method, determination of the concentration of H₂SO₄ which produced optimum conversion of α -cellulose into microcellulose, synthesis of CMC using the microcellulose, and characterization of CMC produced. The results of this study are expected to provide information about the potential of cassava peel as an alternative source of cellulose for CMC production, which could also alleviate environmental problems associated with this agricultural waste.

2

2. Materials and Methods

2.1. Materials

The main materials used are cassava peel obtained from local industry in the City of Metro, Lampung, Indonesia which produces cassava chips and fermented cassava (locally known as tape). HNO₃, NaNO₂, H₂O₂, Na₂SO₃, NaOCl, H₂O₂, sodium monochloro acetate (NaMCA), K₂Cr₂O₇, ferroin indicator, ferrous ammonium sulfate [(NH₄)₂Fe(SO₄)₂·6H₂O] and H₂SO₄ were obtained from Sigma-Aldrich, isopropyl alcohol, ethanol, universal indicator were obtained from J.T. Baker, all these chemicals are pro analysis reagents and used as received.

2.2. Instrumentations

The IR spectra were recorded on FTIR Prestige Shimadzu with KBr discs in the range of 4000-400 cm⁻¹. Microcellulose was characterized using the Fritsch PSA device, Analysette 22 series, to determine the particle-size distribution. A number of samples were fed into the water-filled chamber in the wet dispersion unit until the indicator displays the numbers 10–12 (green). SEM analysis was conducted using SEM ZEISS EVO MA 10. Before the analysis, the sample was prepared by coated gold metal so it was conductor. Next, the sample was inserted into the specimen. The intensity of the electron fired against the sample was regulated by using the condenser-objective lens. The electron reflection of the sample was captured by the detector, the image of which was displayed. The A/DTA was determined using EXSTAR TG/DTA7300. The measurements were performed using nitrogen with flow rate of 20 mL·min⁻¹. The samples were heated at temperatures of 30 - 800 °C with a heating speed of 20 °C min⁻¹. The measurement of crystallinity in microcellulose was carried out by powder X-Ray Diffractometry (XRD) using Phillips xpert, Netherlands based on the procedure in the literature [14]

2.3. Research procedure

2.3.1. Sample preparation

Cassava peels were obtained from a local food industry operating in the city metro, which products include cassava chips and fermented cassava (locally known as tape). After removing its epidermis layer, the peel was washed with clean water and then blended into smooth slurry. The slurry was washed with clean water until the filtrate was clear, and it is dried into powder by oven drying at 60 °C.

2.3.2. Isolation of α -cellulose from cassava peel

Around 75 g of cassava peel powder was placed in a beaker glass, and then 1 L mixture of 3.5% HNO₃ and 10 mg NaNO₂ was added; the sample was heated on a hot plate at 90 °C for 2 hours. The

sample was filtered, and the pulp was rinsed with distilled water until the filtrate became neutral. Then the pulp was refluxed with 750 mL solution containing 2% NaOH and 2% Na_2SO_3 at 50 °C for 1 hour, and then it was filtered and washed until it became neutral. The pulp was bleached with 250 mL of 1.75% NaOCl solution at boiling temperature for 0.5 hours and then filtered and washed until the filtrate reached neutral pH. The α -cellulose produced was purified by soaking in 500 mL of 17.5% NaOH solution at 80 °C for 0.5 hours. The sample was filtered and washed to remove the NaOH and then bleached with 10% H_2O_2 at room temperature for 1 hour. Finally, the pulp of α -cellulose was dried at 60 °C for 1 hour.

2.3.3. Determination of α -cellulose content

Determination of α -cellulose was conducted in accordance with the Indonesian National Standard Test Method SNI 0444: 2009 [15]. A sample of 1.5 ± 0.1 g α -cellulose was transferred into a 300 mL tall cup, followed by the addition of 75 mL of 17.5% sodium hydroxide solution. The time when sodium hydroxide solution was added was recorded, and then the temperature of the mixture was adjusted to $25 \text{ °C} \pm 0.2 \text{ °C}$. The mixture was stirred carefully to avoid the formation of air bubbles, until the pulp was completely dispersed. After completing the stirring process, the stirrer was taken from the cup, and then washed with 25 mL of 17.5% sodium hydroxide solution, which was then added to the cup glass; the needed volume of the pulp suspension in the cup was 100 mL. The pulp suspension was stirred using the stirring rod and stored in a bath at $25 \text{ °C} \pm 0.2 \text{ °C}$. After 30 minutes from the first addition of sodium hydroxide solution, 100 mL of distilled water with temperature of $25 \text{ °C} \pm 0.2 \text{ °C}$ was added into the pulp suspension and was stirred immediately using the stirring rod. The cup was placed in the bath for another 30 minutes so that the total extraction time is around 60 minutes ± 5 minutes.

The suspension was stirred again using stirring rod before it was transferred into the drain funnel. The first 10 mL to 20 mL of the filtrate was discharged, and the next 100 mL was collected in a dry clean flask, and 25 mL of this collected filtrate was transferred into a 250 mL flask; 10 mL of 0.5 N potassium dichromate solution was also added. An aliquot of 50 mL of concentrated sulfuric acid was carefully added, and the mixture was gently shaken. The mixture was heated to a temperature of 125 °C – 135 °C for 15 minutes, and 50 mL of distilled water is added, and it was finally allowed to cool to ambient temperature. Into the solution, two to four drops of ferroin indicator were added and then titrated with 0.1 N ferrous ammonium sulfate solution until it becomes purple in color. At high pulp solubility (low α -cellulose content), with back titration of dichromate less than 10 mL, the volume of filtrate is reduced to 10 mL, and sulfuric acid to 30 mL is added. Blank titration was performed by replacing the pulp filtrate with 12.5 mL of 17.5% sodium hydroxide solution and 12.5 mL of distilled water. The α -cellulose content was calculated using the formula as in Equation 1:

$$X = 100 - \frac{6,85(V_1 - V_2) \times N \times 20}{A \times W} \quad (1)$$

where

X = α -cellulose (%)

V_1 = the volume of blank titration (mL)

V_2 = the volume of pulp filtration titration (mL)

N = normality of ferrous ammonium sulfate solution

A = the volume of pulp filtrate analyzed (mL)

W = the mass of dry pulp used (gram)

2.3.4. Synthesis of microcellulose

Around 5 grams of sample was placed in a 1000 mL round flask, and 100 mL of H_2SO_4 with specified concentration (45%, 47%, and 49%) was added. The mixture was refluxed for 40 minutes at 60 °C under stirring, and 100 mL of distilled water was added. The mixture was allowed to cool, and it was centrifuged at 9000 rpm for 15 minutes, before finally washing with distilled water. The colloidal suspension formed was subjected to ultrasonication for 5 minutes in ice bath and then freeze-dried.

2.3.5. Synthesis of CMC

The procedure for CMC preparation from α -cellulose was adopted from the method used by other researchers [13]. To commence the preparation, 5 grams of α -cellulose was put into a cup, followed by the addition of 150 mL isopropyl alcohol. The sample was stirred using a magnetic stirrer while 15 mL NaOH 25% was added. The sample was continuously stirred for another 1 hour at room temperature. Into the solution, 6 grams of solid sodium monochloroacetic acid was added, the mixture was stirred for 1.5 hours and then wrapped with aluminum foil and heated in an oven at 60 °C for 3.5 hours. After that, the sample was immersed into 100 mL of methanol for one night. The next day, the sample was neutralized with 90% acetic acid until the pH was neutral and filtered. The final product was washed with ethanol three times by immersing it into 50 mL ethanol for 10 minutes and then with 100 mL absolute ethanol. The produced CMC was dried in an oven at 60 °C until a constant weight was obtained.

3.5.6. Determination of DS

The DS of the CMC prepared was determined in accordance with the method available in the literature [16]. Around 4 grams of CMC was dissolved in 75 mL of 95% ethanol, followed by the addition of 5 mL of 1 M nitric acid. The solution was put into boil while it is stirred for 10 minutes, and then the sample was washed with 20 mL 80% ethanol at 60 °C five times and washed again with anhydrous methanol. Then the sample was filtered and dried in an oven at 105 °C for 3.5 hours and cooled in a desiccator for 30 minutes. Around 0.5 g of dry CMC was dissolved in 100 mL of distilled water and stirred, then 25 mL of 0.3 M NaOH solution was added, and the mixture was boiled for 15 minutes. The sample was added with PP indicator and titrated with 0.3 M HCl solution. The determination of the DS was conducted using Equation 2 and 3 [15]:

$$\%CM = \frac{[V_0 - V_n] \times M \times 0,059 \times 100}{m} \quad (2)$$

$$DS = \frac{162 \times \%CM}{[5900 - (58 \times \%CM)]} \quad (3)$$

where:

DS = degree of substitution

% CM = oxymethyl content

V_0 = the volume of blank titration (mL)

V_n = volume of sample titration (mL)

M = molarity of HCl

m = mass of sample (gram)

3. Results and Discussions

3.1. Determination of α -cellulose content

The principle of determining α -cellulose is to measure the amount of α -cellulose which is insoluble and does not decompose by NaOH solution [17, 18]. The α -cellulose content of the sample prepared in this study is 92.33%. The result obtained in this study is lower than the result reported by others [18], in which the sample prepared from empty bunches of palm oil was reported to contain 97.04% α -cellulose. Since the method applied in this study is practically similar to that applied for the work of Yuwono et al. [18], the differing results in the two studies are most likely due to different raw materials used.

3.2. PSA of microcellulose

Based on the results of the PSA (Figure 1), for every concentration variation of H_2SO_4 used, the particle sizes of microcellulose obtained also varied but not surprisingly the highest population obtained for every H_2SO_4 concentration was the same i.e. belong to particle size of 1.83 μm .

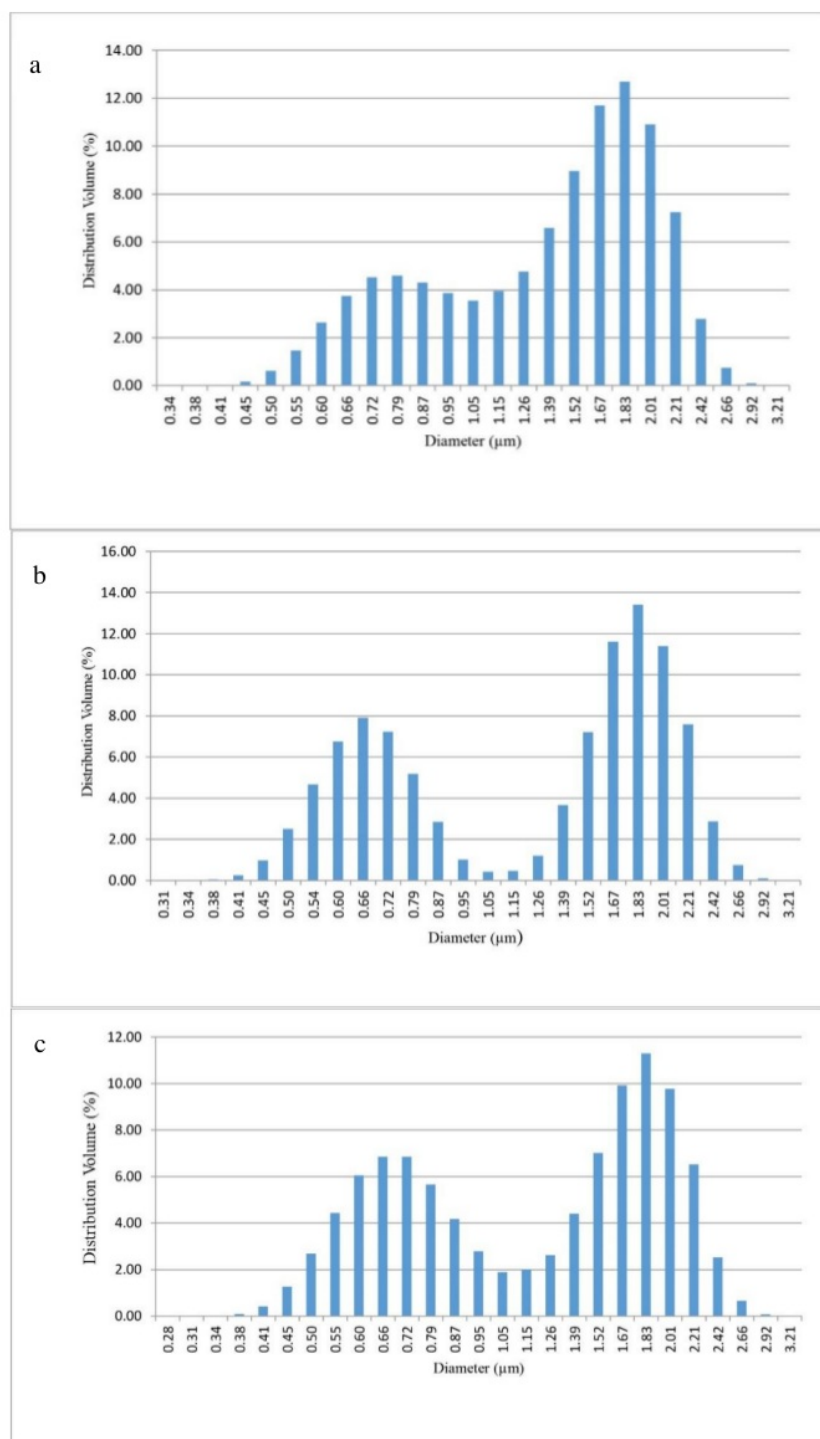


Figure 1. The result of PSA: (a) H₂SO₄ concentration 45%, (b) H₂SO₄ concentration 47%, (c) H₂SO₄ concentration 49%.

At a concentration of H₂SO₄ 45%, the particle size of microcellulose was in the range 0.50–2.66 μm, with the highest population of 12.7% belong to particle size of 1.83 μm; in H₂SO₄ 47%, the size was

in the range of 0.45–2.42 μm and particle size of 1.83 μm was the highest population with total amount of 13.4%; and in H_2SO_4 49%, the particle size was in the range of 0.41–2.66 μm with the highest population of 11.3% belong to particle size of 1.83 μm . These data indicated that the cellulose obtained was like microparticles; thus microcellulose was obtained as the final product. The results obtained are in line with the result reported in other paper [19] which states that the microparticles are formed when the size is less than or equal to 100 μm .

3.3. Determination of CMC DS

The value of the substitution degree of the sample obtained in this study was 0.27 which indicated that the CMC product obtained was slightly soluble in water. The magnitude of the DS in this study is not much different from other works [11, 13] which is equal to 0.25. In this work, there are two factors affecting this DS value, namely, alkalization and carboxymethylation. In alkalization, the activation of OH groups on cellulose takes place, and upon this process causing the cellulose structure to expand; thus it makes the carboxymethylation reagent easy to diffuse in cellulose molecules. The carboxymethylation process is the most important step in the process of CMC synthesis [2, 11].

3.4. DTA/TGA CMC analysis

The derivative of DTA/TGA CMC has two phases of degradation (Figure 2). The first phase is the evaporation of volatile molecules, and the second phase is CMC degradation. The evaporation phase of volatile compounds occurred at 140 $^{\circ}\text{C}$ of 0.368 mg/min and the degradation phase of CMC occurred at 260 $^{\circ}\text{C}$ of 0.472 mg/min. This result is in accordance with the results obtained by Taghizadeh and Sabouri which explains that CMC degradation occurs at temperatures of 250 $^{\circ}\text{C}$ –360 $^{\circ}\text{C}$ [20].

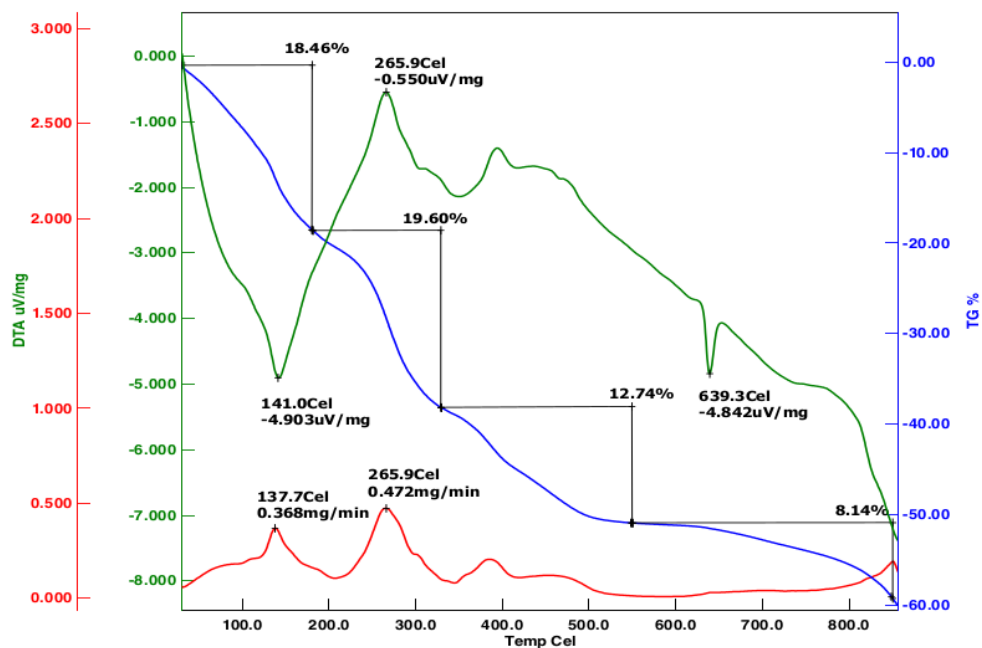


Figure 2. DTA/TGA thermogram of CMC.

The DTA/TGA thermogram of CMC is shown in Figure 2. Based on this thermogram, the CMC has endothermic and exothermic properties. The endothermic properties were observed at 140 $^{\circ}\text{C}$ to decrease in 4.9 μV due to water molecules. Exothermic properties were observed at 260 $^{\circ}\text{C}$ at $-0.55 \mu\text{V}$ due to CMC decomposition. Based on Figure 2, CMC has four decomposition phases. The

first phase was water decomposition with mass reduction of 18.46% [21], the second phase was CMC decomposition with mass reduction of 19.60% [22], and the third phase was decomposition to cross-link bonds in CMC [21]. In the third and fourth phases, there was a mass reduction of 12.74%. The value of mass reduction in the study was smaller when compared to the reported result conducted by others [21, 22]. This is in accordance with the results of Sadeghi [20] which states that CMC compounds with more substitution will have higher thermal stability. As a result, many substituent CMC decomposition processes require higher temperatures than CMC with fewer substituents. Thus, at the same temperature, CMC decomposition which has many substituents results in a smaller mass reduction value than CMC which has little substituents.

3.5. FTIR analysis of carboxymethyl cellulose

The result of FTIR analysis (Figure 3) indicated that α -cellulose has a broad peak at 3418 cm^{-1} showing the present of hydroxy ($-\text{OH}$) band, a peak with moderate intensity at 2901 cm^{-1} as from the methylene ($-\text{CH}_2-$) stretching band, sharp peak with moderate intensity at 1628 cm^{-1} from stretching of the carbonyl group ($\text{C}=\text{O}$) from the glucose monomer, the peak with moderate shift at 1427 cm^{-1} from the band of the methylene group ($-\text{CH}_2-$), and strong band at 1057 cm^{-1} from the ether group absorption (COC).

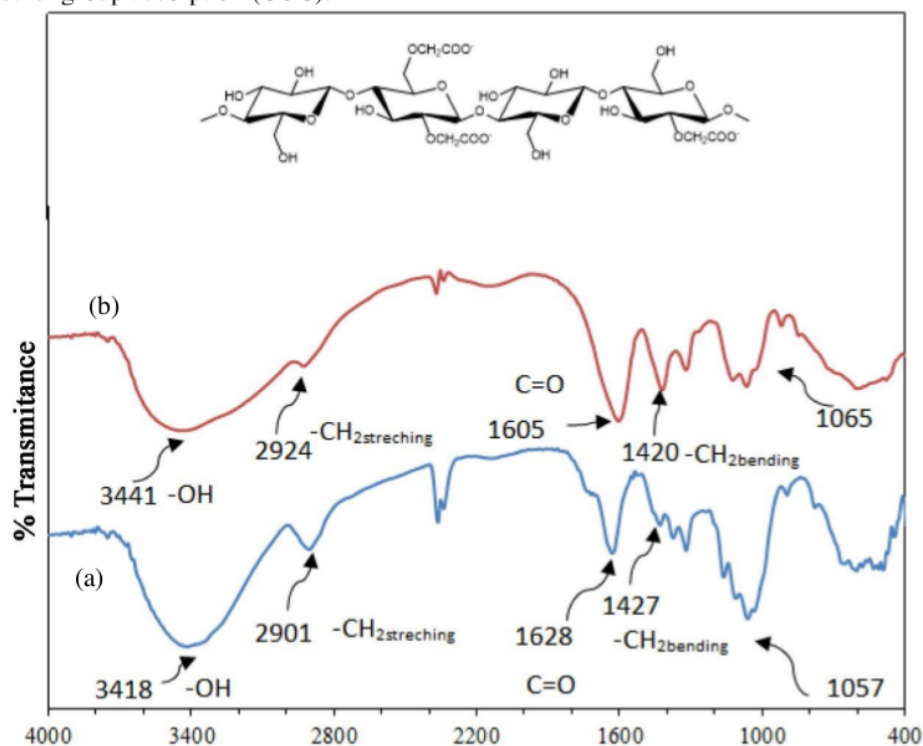


Figure 3. Infrared spectra of (a) α -cellulose and (b) CMC.

In comparing with IR spectrum of α -cellulose, the IR spectrum of CMC was slightly different. It has a broad peak at 3441 cm^{-1} from the hydroxy ($-\text{OH}$), the peak of moderate intensity was at 2924 cm^{-1} was from the vibration of the methylene group ($-\text{CH}_2-$), sharp peak with moderate intensity was at 1605 cm^{-1} of stretch absorption from carbonyl group ($\text{C}=\text{O}$) of glucose monomers, peak with moderate absorption at 1420 cm^{-1} from the band of the methylene ($-\text{CH}_2-$) group and strong band at 1065 cm^{-1} from ether group (COC).

Adel et al. [21] have reported that the results of FTIR analysis of CMC compounds for OH band were seen in wave numbers 3400 cm^{-1} , CH_2 vibrations were seen in wave numbers 2900 and 1424 cm^{-1} , and absorption of carbonyl groups seen in wave number 1720 cm^{-1} . The vibration of the hydroxyl group at CMC is at a larger wave number because of the stronger hydrogen bond due to the addition of the carboxylic acid group at CMC. The vibration of the carbonyl group in CMC appears at the lower wave numbers because the COO-H group in CMC is more easily dissociated. Dissociation of protons in carboxylic acid groups will cause possible electron resonance in carboxylic anions so that the electron density in the carbonyl group is lower.

Table 1 shows that almost all FTIR vibrations of functional groups from CMC compounds between the results of the study and reference are not of much difference, except for the absorption of carbonyl groups. The wave number of the carbonyl group from the results of this study is 1605 cm^{-1} , while the wave number of the reference carbonyl group is 1720 cm^{-1} . This is due to differences in the reagents used. This study uses NaMCA reagents, while research conducted by Adel et al. [21] uses MCA. The carbonyl compound of the CMC compound from this study binds to sodium metal. So the wave number of the carbonyl group results of this study is lower than the carbonyl group wave number that has been reported by Adel et al. [21]. On the other hand, the value of the carbonyl group wave number from the results of this study is closer to the value of the carbonyl group wave number from the research conducted by Eliza et al. [23] which uses the same reagent, which is 1589 cm^{-1} .

Table 1. Comparison of CMC FTIR absorption from research results with references [21].

No	Bond	FTIR vibration of The product in this work (cm^{-1})	References (cm^{-1}) [21]
1	-OH	3441	3400
2	- CH_2 - (<i>stretching</i>)	2924	2900
	- CH_2 - (<i>bending</i>)	1420	1425
3	-C=O	1605	1720

3.2. CMC SEM analysis

SEM analysis was used to determine the morphological changes of cellulose compounds to CMC. The results of SEM analysis of cellulose and SEM results of CMC compounds from the results of this study are presented in Figure 4. The results of SEM (Figure 4) indicated that there is a difference in density between cellulose and CMC compounds. CMC compounds have a morphology that is more tenuous than cellulose compounds. This is consistent with the study of Najafpour et al. [24] which explains that CMC compounds have been methylated due to carboxymethyl groups substituted on cellulose molecules so that the morphology of CMC is increasingly insignificant and the distance between molecules is greater.

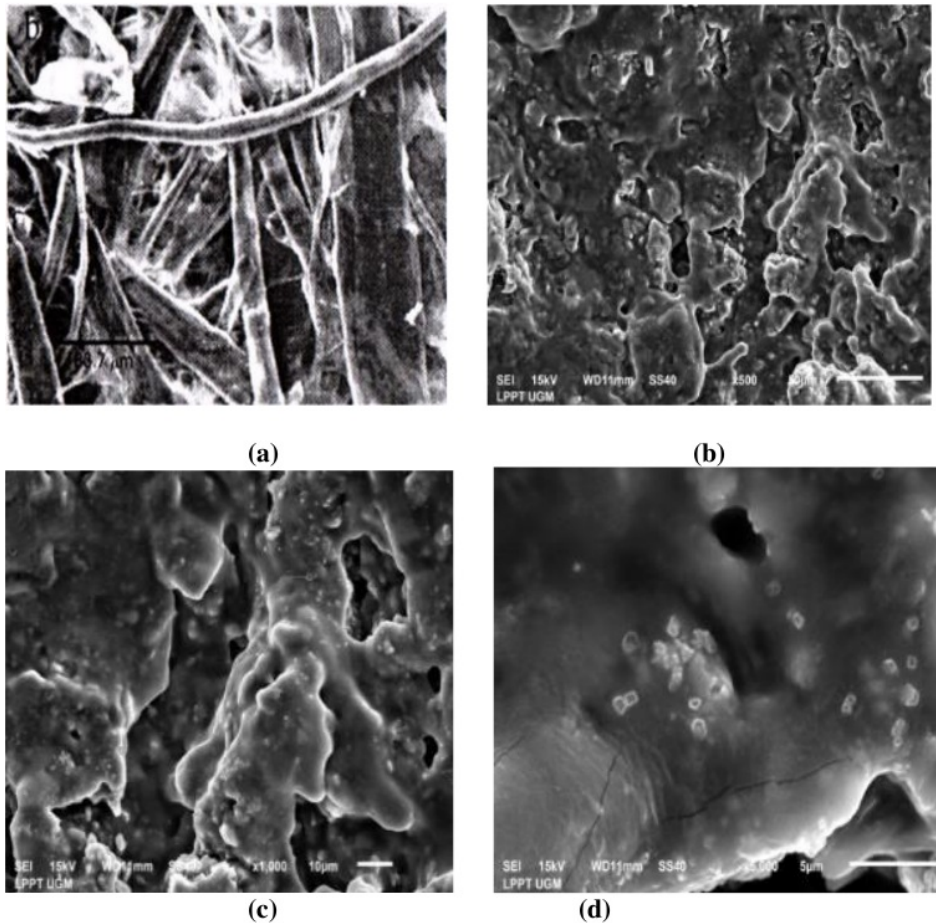


Figure 4. The results of SEM analysis (a) Cellulose, (b) CMC 500x magnification, (c) CMC 1000x magnification, and (d) CMC 5000x magnification

3.7. XRD analysis of carboxymethyl cellulose

Based on Figure 5, CMC products have three absorption peaks, namely, at 2θ 20° , 32° , and 45° . CMC compounds can be identified at absorption of 2θ 20° . This is in accordance with the results of the study of Huang et al. [25] which explained that the XRD CMC diffractogram was found at 2θ 20° . The CMC compound results of this study are not 100% pure; this is indicated by absorption at 2θ 32° and 45° which indicate there are still impurities in CMC compounds.

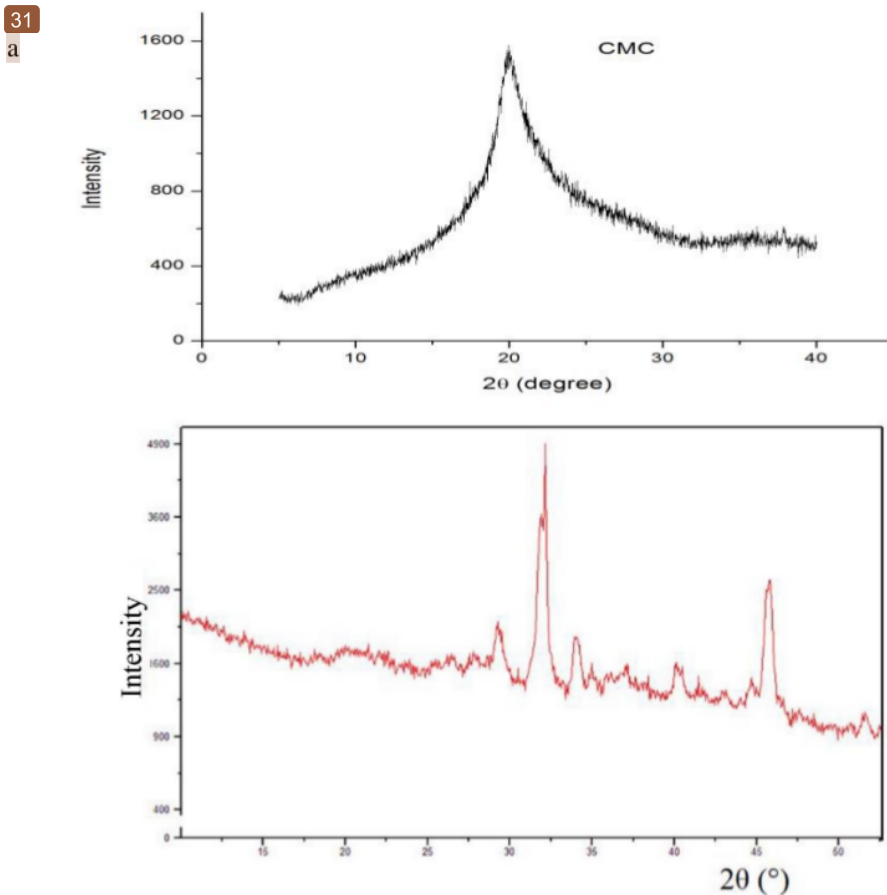


Figure 5. XRD diffraktrogram of (a) CMC standard, and (b) CMC research results.

4. Conclusions

Based on the results of our observations and experiments carried out, the following conclusions are obtained: (1) results of α -cellulose isolation from cassava peel using the delignification method obtained α -cellulose levels of 92.33%; (2) the optimum results for obtaining microcellulose were found in 49% H_2SO_4 concentrations, indicated by PSA analysis; and (3) in this study, CMC from cassava peel was successfully synthesized and characterized by FTIR (Fourier transform infrared), TGA (thermogravimetric analysis), SEM, and XRD.

6 **Acknowledgments:** The authors would like to thank to the Institute of Research and Community Services, Universitas Lampung that provided fund for this project to be undertaken through Penelitian Hilirisasi 2019. The authors would like to thank Enago (www.enago.com) for the English language proofread and review. 12

References

1. INDONESIAN STATISTICAL BUREAU (BPS). Statistical Yearbook of Indonesia in 2019. BPS-Statistic Indonesia, 2019, 84.
2. OLARU, N., OLARU, L., STOLERIU, A., TIMPU, D., Carboxymethylcellulose synthesis in organic media containing ethanol and/or acetone, *J. Appl. Polym. Sci.*, **67**(3), 1998, 481–486.

3. YAŞAR, F., TOĞRUL, H., ARSLAN, N., Flow properties of cellulose and carboxymethyl cellulose from orange peel, *J. Food. Eng.*, **8**(1), 2007, 187-199.
4. KOWALCZYK, D., KORDOWSKA, W. M., ZIEBA, E., BARANIAK, B., Effect of carboxymethylcellulose/candelilla wax coating containing potassium sorbate on microbiological and physicochemical attributes of pears, *Scientia Horticulturae*, **218**, 2017, 326-333.
5. ZHOU, H.Y., CAO, P.P., LI, J.B., ZHANG, F.L., DING, P.P., Preparation and release kinetics of carboxymethyl chitosan/cellulose acetate microspheres as drug delivery system, *J. Appl. Polym. Sci.*, **132**(26), 2015, 42152 (1-10).
6. SHEIKH, J., BRAMHECHA, I., TELI, M.D., Recycling of terry towel (cellulosic) waste into carboxymethyl cellulose (CMC) for textile printing, *Fiber Polym.*, **16**(5), 2015, 1113-1118.
7. PRICOP, M., URECHESCU, H., PRICOP, C., ROSU, S., PRICOP, N., JIVANESCU, A., Acrylic Obturator Prosthesis in Maxillary Defects - Is an Improvement After Denture Adhesive Application?, *Mater. Plast.*, **53**(3), 2016, 478-480.
8. PAVALOIU, R.D., STROESCU, M., PARVULESCU, O., DOBRE, T., Composite Hydrogels of Bacterial Cellulose - carboxymethyl Cellulose for Drug Release, *Rev. Chim.*, **65**(8), 2014, 948-951.
9. NEJNERU, C., VIZUREANU, P., SANDU, A.V., GRECU, A., CIMPOESU, N., Thermal Fatigue of Some Synthetic Hardening Environments with CMC, *Rev. Chim.*, **65**(2), 2014, 194-198.
10. ARIPIN, A.M., ANGZZAS, S.M.K., ZAWAWI, D., HATTA, M.Z.Z.M., Cassava peels for alternative fibre in pulp and paper industry: chemical properties and morphology characterization, *Int. J. Integrat. Eng.*, **5**(1), 2013, 30-33.
11. TOĞRUL, H., ARSLAN, N., Production of carboxymethyl cellulose from sugar beet pulp cellulose and rheological behaviour of carboxymethyl cellulose, *Carbohydr. Polym.*, **54**, 2003, 73-82.
12. ARUP, M., Isolation of nanocellulose from waste sugarcane bagasse (SCB) and its characterization, *Carbohydr. Polym.*, **86**, 2011, 1291-1299
13. PUSHPAMALAR, V., LANGFORD, S., AHMAD, M., LIM, Y.Y., Optimization of reaction conditions for preparing carboxymethyl cellulose from sago waste, *Carbohydr. Polym.*, **64**(2), 2006, 312-318.
14. SEGAL, L., CREEELY, J.J., MARTIN, Jr., A.E., An Empirical Method for Estimating the Degree of Crystallinity of Native Cellulose Using the X-Ray Diffractometer, *Textiles Res. J.*, **29**, 1959, 786-794.
15. INDONESIAN NATIONAL STANDARD TEST METHODS (SNI), Pulp-Test Methods of alpha, beta and gamma cellulose, SNI 0444, 2009. (in Indonesian)
16. AMERICAN SOCIETY OF TESTING AND MATERIALS (ASTM), Analytical method for determining degree of substitution in the product. Document CK-G06, Edition, 2005.05, D-1439-03.
17. YOKOYAMA, T., KADLA, K.F., CHANG, H.M., Microanalytical method for the characterization of fiber components and morphology of woody plants, *J. Agric. Food Chem.*, **50**, 2002, 1040-1044.
18. YUWONO, S.D., IRYANI, D.A., GUSTI, C., SUHARTO, BUHANI, SUHARSO, Production of Acetyl Cellulose from Agricultural Waste of Oil Palm Empty Fruit Bunches, *Asian J. Chem.*, **31**(12), 2019, 2725-2728.
19. KOLAKOVIC, R., LAAKSONEN, T., PELTONEN, L., LAUKKANEN, A., & HIRVONEN, J., Spray-dried nanofibrillar cellulose microparticles for sustained drug release, *Int. J. Pharm.*, **430**(1-2), 2012, 47-55.
20. TAGHIZADEH, M. T., SABOURI, N., Thermal Degradation Behavior of Polyvinyl Alcohol/Starch/Carboxymethyl Cellulose/Clay nanocomposites. *Univer. J. Chem.*, **1** (2), 2013, 21-29.

21. ADEL, A.M., ABOU-YOUSSEF, H., EL-GENDY, A.A., NADA, A.M., Carboximethylated Cellulose Hydrogel; Sorption Behavior and Characterization, *Nature and Science*. **8**(8), 2010, 244-256.
22. EL-SAYED, S., MAHMOUDA, K.H., FATAH, A.A., HASSEN, A., DSC, TGA and dielectric properties of carboxymethyl cellulose/polyvinyl alcohol blends, *Physica B*, **406**, 2011, 4068–4076
23. ELIZA, M.Y., SHAHRUDDIN, M., NOORMAZIAH, J., WAN ROSLI, D.W.D., Carboxymethyl Cellulose (CMC) from Oil Palm Empty Fruit Bunch (OPEFB) in the new solvent Dimethyl Sulfoxide (DMSO)/Tetrabutylammonium Fluoride (TBAF), *J. Phys.: Conf. Series*, **622**, 2015, 012026.
24. NAJAFPOUR, G.D., HEYDARZADEH, H.D., NAZARI-MOGHADDAM, A.A., Catalyst-Free Conversion of Alkali Cellulose to Fine Carboxymethyl Cellulose at Mild Conditions, *World Appl. Sci. J.*, **6**, 2009, 564-569.
25. HUANG, L.J., YANG, Y., CAI, Y.Y., LIU, M., XU, T., NONG, G.Z., WANG, S.F., Preparation of Superabsorbent Resin from carboxymethyl Cellulose Grafted with Acrylic Acid by Low-temperature Plasma Treatment, *Bioresources*, **9**(2), 2014, 2987-2999.

Characterization of Carboxymethyl Cellulose (CMC) Synthesized from Microcellulose of Cassava Peel

ORIGINALITY REPORT

18%

SIMILARITY INDEX

PRIMARY SOURCES

1	eprints.utar.edu.my Internet	70 words — 2%
2	www.mdpi.com Internet	68 words — 2%
3	Rodsamran, Patrathip, and Rungsinee Sothornvit. "Renewable cellulose source: isolation and characterisation of cellulose from rice stubble residues", <i>International Journal of Food Science & Technology</i> , 2015. Crossref	49 words — 1%
4	H Harahap, M Ridha, Halimatuddahlia, Taslim, Iriany. "Effect of cellulose nanocrystals from corn cob with dispersion agent polyvinyl pyrrolidone in natural rubber latex film after aging treatment", <i>IOP Conference Series: Materials Science and Engineering</i> , 2018 Crossref	47 words — 1%
5	jpsr.pharmainfo.in Internet	40 words — 1%
6	pt.scribd.com Internet	39 words — 1%
7	link.springer.com Internet	24 words — 1%
8	journal.biotrop.org Internet	24 words — 1%

-
- 9 www.researchgate.net 20 words — < 1%
Internet
-
- 10 www.omicsonline.org 20 words — < 1%
Internet
-
- 11 Tati Suhartati, Eka Epriyanti, Inggit Borisha, Yandri, Jhons F. Suwandi, Sripto D. Yuwono, Hardoko I. Qudus, Sutopo Hadi. "In Vivo Antimalarial Test of Artocarpin and in vitro Antimalarial Test of Artonin M Isolated from Artocarpus", *Revista de Chimie*, 2020 19 words — < 1%
Crossref
-
- 12 Sutopo Hadi, Noviany, Hardoko Insan Qudus, Pakorn Wattana-Amorn. "The Potency Study of Organotin(IV) 3-Nitrobenzoate Compounds as Antimalarial Agents", *Journal of Physics: Conference Series*, 2019 18 words — < 1%
Crossref
-
- 13 open.library.ubc.ca 17 words — < 1%
Internet
-
- 14 Hamidah Harahap, Nuim Hayat, Marfuah Lubis. "Preparation and application of nanocrystalline cellulose derived from sugarcane waste as filler modified alkanolamide on crosslink of natural rubber latex film", AIP Publishing, 2017 17 words — < 1%
Crossref
-
- 15 Halimahtussaddiyah Ritonga, Anugrah Nurfadillah, Fransiskus S. Rembon, L.O.A.N. Ramadhan, Muhammad Nurdin. "Preparation of Chitosan-EDTA hydrogel as soil conditioner for soybean plant (*Glycine max*)", *Groundwater for Sustainable Development*, 2019 16 words — < 1%
Crossref
-
- 16 A. Sonia, K. Priya Dasan. "Chemical, morphology and thermal evaluation of cellulose microfibers obtained from *Hibiscus sabdariffa*", *Carbohydrate Polymers*, 2013 15 words — < 1%
Crossref
-

- 17 Internet 15 words — < 1%
-
- 18 Reni Banowati Istiningrum, Toni Aprianto, Febria Lutfi Udin Pamungkas. "Effect of reaction temperature on biodiesel production from waste cooking oil using lipase as biocatalyst", AIP Publishing, 2017
Crossref 12 words — < 1%
-
- 19 pubs.rsc.org Internet 12 words — < 1%
-
- 20 Kose, D.A.. "A comparative examination of mono- and bis-chelate salicylatoborate complexes and the crystal structure of layered magnesium bis-salicylatoborate", Inorganica Chimica Acta, 20110901
Crossref 11 words — < 1%
-
- 21 Tawfik A. Khattab, Sawsan Dacrory, Hussein Abou-Yousef, Samir Kamel. "Development of microporous cellulose-based smart xerogel reversible sensor via freeze drying for naked-eye detection of ammonia gas", Carbohydrate Polymers, 2019
Crossref 11 words — < 1%
-
- 22 Luca Zoia, Alistair W. T. King, Dimitris S. Argyropoulos. "Molecular Weight Distributions and Linkages in Lignocellulosic Materials Derivatized from Ionic Liquid Media", Journal of Agricultural and Food Chemistry, 2011
Crossref 11 words — < 1%
-
- 23 tmdasfoundation.org Internet 11 words — < 1%
-
- 24 Nathalie Lavoine, Isabelle Desloges, Cécile Sillard, Julien Bras. "Controlled release and long-term antibacterial activity of chlorhexidine digluconate through the nanoporous network of microfibrillated cellulose", Cellulose, 2014
Crossref 11 words — < 1%
-
- 25 Peiqiang Yu, H. Block, Z. Niu, K. Doiron. "Rapid characterization of molecular chemistry, nutrient 10 words — < 1%

make-up and microlocation of internal seed tissue", Journal of Synchrotron Radiation, 2007

Crossref

26 Siew Chin Cheu, Helen Kong, Shiew Tien Song, Khairiraihanna Johari, Norasikin Saman, Mohd Azizi Che Yunus, Hanapi Mat. "Separation of dissolved oil from aqueous solution by sorption onto acetylated lignocellulosic biomass—equilibrium, kinetics and mechanism studies", Journal of Environmental Chemical Engineering, 2016

Crossref

27 Tog@?rul, H.. "Carboxymethyl cellulose from sugar beet pulp cellulose as a hydrophilic polymer in coating of mandarin", Journal of Food Engineering, 200405

Crossref

28 P.R.D. Weerasooriya, R. Nadhilah, F.A.T. Owolabi, R. Hashim et al. "Exploring the properties of hemicellulose based carboxymethyl cellulose film as a potential green packaging", Current Research in Green and Sustainable Chemistry, 2020

Crossref

29 [epdf.tips](#) 9 words — < 1%

Internet

30 [www.jiskha.com](#) 9 words — < 1%

Internet

31 [etd.auburn.edu](#) 8 words — < 1%

Internet

32 [etd.uovs.ac.za](#) 8 words — < 1%

Internet

33 Rani, Mohd, Siti Rudhziah, Azizan Ahmad, and Nor Mohamed. "Biopolymer Electrolyte Based on Derivatives of Cellulose from Kenaf Bast Fiber", Polymers, 2014.

Crossref

34 Duraikkannu Shanthana Lakshmi, Nitin Trivedi, C.R.K. Reddy.

"Synthesis and characterization of seaweed cellulose derived carboxymethyl cellulose", Carbohydrate Polymers, 2017
Crossref 8 words — < 1%

35 www.tsijournals.com
Internet 8 words — < 1%

36 Grace K. Dolan, Gleb E. Yakubov, George W. Greene, Nasim Amiralian, Pratheep K. Annamalai, Darren J. Martin, Jason R. Stokes. "Dip-and-Drag Lateral Force Spectroscopy for Measuring Adhesive Forces between Nanofibers", Langmuir, 2016
Crossref 8 words — < 1%

37 repositorium.sdum.uminho.pt
Internet 8 words — < 1%

38 www.revmaterialeplastice.ro
Internet 8 words — < 1%

39 Haleem, Noor, Muhammad Arshad, Muhammad Shahid, and Muhammad Ashraf Tahir. "Synthesis of carboxymethyl cellulose from waste of cotton ginning industry", Carbohydrate Polymers, 2014.
Crossref 6 words — < 1%

40 Pushpamalar, V.. "Optimization of reaction conditions for preparing carboxymethyl cellulose from sago waste", Carbohydrate Polymers, 20060511
Crossref 6 words — < 1%

41 M. Thoriq Al Fath, Halimatuddahlia Nasution. "Process optimization of manufacturing nanocrystalline cellulose from rattan biomass using sulfuric acid", AIP Publishing, 2018
Crossref 6 words — < 1%

42 Gregorius Nugroho Susanto, Supono, Fadhli Dzil Ikrom. "Sex reversal of juvenile freshwater crayfish (Cherax quadricarinatus) influenced by steroid extract of sea cucumber and 17 α -methyltestosterone hormone at different

temperatures", AIP Publishing, 2018

Crossref

EXCLUDE QUOTES

ON

EXCLUDE MATCHES

OFF

EXCLUDE
BIBLIOGRAPHY

ON