

Pandiangan_2019_J._Phys.__C onf._Ser._1338_012015

by Hanif Amrulloh

Submission date: 04-Jan-2021 01:38PM (UTC+0700)

Submission ID: 1482843543

File name: Pandiangan_2019_J._Phys.__Conf._Ser._1338_012015.pdf (1.78M)

Word count: 4052

Character count: 21660

PAPER • OPEN ACCESS

Characteristics and catalytic activity of zeolite-a synthesized from rice husk silica and aluminium metal by sol-gel method

4

To cite this article: K D Pandiangan *et al* 2019 *J. Phys.: Conf. Ser.* **1338** 012015

View the [article online](#) for updates and enhancements.



IOP | ebooks™

Bringing you innovative digital publishing with leading voices to create your essential collection of books in STEM research.

Start exploring the collection - download the first chapter of every title for free.

Characteristics and catalytic activity of zeolite-a synthesized from rice husk silica and aluminium metal by sol-gel method

K D Pandiangan¹, W Simanjuntak¹, E Pratiwi² and M Rilyanti¹


¹ Department of Chemistry, Faculty of Mathematics and Natural Science, Lampung University, Bandar Lampung-35145, Indonesia

² Departement of Physical Education, Faculty of Education and Teacher Training, Universitas Islam Negeri Raden Intan Lampung, Bandar Lampung-35131 Indonesia

Abstract. In this research, sol-gel process was applied to synthesize zeolite-A from rice husk silica and aluminum metal. For preparation of the zeolite, the specified amount of rice husk silica and aluminum metal was separately dissolved in NaOH solution, and both solutions were transferred in to a laboratory mixture for complete mixing and production of gel. The gel was converted into solid zeolite precursor by oven drying of the gel for 24 hours. The precursor was transformed into zeolite by subjecting to different calcination temperatures, and then characterized using different techniques. The zeolites were also tested as catalyst for transesterification of *Ricinius communis* oil. Development of structure of the zeolite was confirmed using FTIR and XRD techniques analyses, while SEM analysis revealed the characteristic of the samples as porous and multiphasic materials. The zeolites were found to exhibit good catalytic activity as revealed by the results of transesterification of *Ricinius communis* oil. Appreciable catalytic activities were also demonstrated by the reaction yields achieved which are in the range of 68 to 82%.

1. Introduction

Zeolite represents very important group of applied materials, due to their unique properties, capable of playing a variety of important roles such as adsorbents, ion exchangers, and catalysts. At present, one of catalytic reaction extensively investigated is transesterification of glycerides using low molecular weight alcohols, to convert the glycerides into their corresponding simpler alkyl esters, known as biodiesel. In the context of progressive increase of energy demand, biomass derived energy sources or biofuels, including biodiesel, continue to gain global interest [1-2].

In the manufacture of biodiesel, the catalyst is a major requirement, since glycerides and alcohol have very low reactivity toward each other, and therefore, without the aid of catalyst practically no reaction takes place. In the current practices for biodiesel manufacture, homogeneous catalysts remain as the most widely used [3-5], however heterogeneous catalysts continue to gain interest [6-8]. Heterogeneous catalysts offer a number of advantages over homogeneous catalysts, such as simple catalyst recovery, non-corrosive, as well as the possibility to reuse the catalyst [9]. With these various advantages they offered, the use of heterogeneous catalysts for transesterification of  different vegetable oils continue to progress. Apart from this progressive development, it should be



Content from this work may be used under the terms of the [Creative Commons Attribution 3.0 licence](https://creativecommons.org/licenses/by/3.0/). Any further distribution of this work must maintain attribution to the author(s) and the title of the work, journal citation and DOI.

Published under licence by IOP Publishing Ltd

acknowledged that detailed reaction mechanism of transesterification involving heterogeneous catalyst has not been fully understood and remain a scientific challenge.

Considering the advantages, they offered, various heterogeneous catalysts have been developed and tested, such as Al-loaded CaO [10] and several synthetic zeolites. The promising potential of synthetic zeolites to support different utilizations is clearly illustrated by continuous development of various synthetic zeolites [11-16]. For production of biodiesel, this type of catalyst has been used to treat different raw materials, such as waste cooking oil [14], microalga oil [15], palm oil [12], triglycerides [16], butter [17]. Utilization of modified catalyst, in which zeolite pellet was coated with γ -alumina, for transesterification of waste cooking oil has also been reported [18].

In the use of zeolites as catalyst for biodiesel production, it is generally acknowledged that the main feature which determines the catalytic activity of zeolite is the chemical composition. In this respect, the general findings have shown that different zeolites most likely will lead to different performances when they are applied to the same raw material. The possibility varied performances implies that selection of the most suitable catalyst for specific raw material should be taken into account. For this reason, in this study zeolite-A was tested for transesterification of *Ricinus communis* oil, with the main purpose to assess whether this type of zeolite possess the viable potential for further development.

Besides development of catalysts, the search for raw materials is another basic aspect of biodiesel industry, with the main focus on exploring production of biodiesel from waste oil [14, 18] and non-edible vegetable oils as alternative raw materials to coconut and palm oil which has been used as traditional raw material. The main advantage that can be derived from this type of raw materials is to avoid the competition between food and energy source. There are many species of plant that produce vegetable oil with the amount that is worth taking into account and have been converted into biodiesel, such as *Jatropha curcas* [9, 19], rubber or *Hevea brasiliensis* [7, 20], and Castor or *Ricinus communis* L. [21-22]. Generally, such crops can grow in the region of tropical and subtropical climates [23] with significantly lower cultivation cost than that required for edible vegetable oil producing plants. In addition non-edible oil producing plants do not require intensive care to grow well and deliver high oil yields [24]. *Ricinus communis* oil is a promising alternative raw material for production of biodiesel considering its abundant availability and its existence as non-edible vegetable oil. In addition, the chemical composition of the oil is much simpler compared to the others, in which ricinoleic acid exists as the main component with the contribution between 83.85 to 87.62%, with other components such as palmitic, stearic, oleic, linolic, linolenic, arachidic, and arachidonic acids, in small percentages [21]. To some extent, this simple composition is advantageous since the composition and, therefore, the characteristics of the biodiesel derived from the oil are also simpler than those of biodiesels derived from other raw materials.

Acknowledging the important roles of catalyst and raw material in biodiesel industry, in this present investigation, sol-gel method was applied to prepare zeolite-A from aluminum silicate and silica extracted from rice husk. The use of these raw materials is based on the solubility of rice husk silica and aluminum metal in NaOH solution. For sol-gel process, separately prepared rice husk silica solution and aluminum metal solution were mixed to produce the precursor of zeolite-A in the form of gel. The gel was dried and subsequently calcined at varied temperatures to transform the precursor into zeolite. The characteristics of zeolites were then evaluated in term of acidity using pyridine absorption method, functionality using FTIR, structure using XRD, and microstructure using SEM. The catalytic activity of the zeolites was tested in transesterification of *Ricinus communis* oil with methanol. The reaction product was analysed using GC-MS technique to examine whether the product composed of methyl esters which confirm that the zeolite-A synthesized functioned as catalyst.

20

2. Materials and methods

2.1. Materials

Sodium hydroxide and nitric acid from Aldrich, methanol from Merck, Al metal in the form of rods with diameter of 1 cm was from CV. Aluminum Jaya Perkasa Jakarta. A rice milling company in Bandar Lampung kindly provided rice husk sample.

The instruments used in this study are Fourier Transform Infrared Spectrophotometer (GX, Perkin-Elmer), Bruker D8 Advance for XRD instrument, FEI type Inspect S50 SEM equipped with EDAX AMETEK, and GCMS-QP2010 SE SHIMADZU.

2.2. Preparation of zeolite-A

The synthesis of zeolite-A was carried out adopting the method reported in previous study [12]. In brief, the preparation was conducted by first preparing a solution of 40 grams of NaOH pellets in 500 mL of distilled water. An aliquote of 250 mL of this solution was used to dissolve 27 grams of Al metal and the other 250 mL was utilized to dissolve 60 grams of rice husk silica [20]. To produce the zeolite precursor, both solutions were transferred into laboratory mixer for complete mixing of the raw materials. The gel obtained was placed in the oven at 90°C for 24 hour drying process to produce dry solid. Powder sample prepared by grinding the solid was then calcined at varying temperatures of 600, 700, 800, and 900°C for 6 hours. The four samples were then characterized and tested as catalyst.

2.3. Catalytic activity trial

To evaluate their catalytic activity, the four samples of zeolite-A were then used as catalyst for transesterification reaction of *Ricinus communis* oil with methanol. The experiment was conducted adopting the procedure used in previous studies [7, 12]. To run the experiment, the reaction mixture was prepared by transferring 25 mL of oil, 50 mL of methanol, and 2.5 g of catalyst into 500 mL round bottom flask placed in heating mantle apparatus. The flask was connected with a reflux condenser for water cooling, and the reaction was run for six hours at fixed temperature 70°C. After the reaction was completed, the mixture was allowed to cool and then the catalyst was recovered by filtering the mixture. The filtrate was left in the funnel to allow the separation of the biodiesel layer and residual methanol and unreacted oil. The biodiesel was collected to determine the reaction yield, and then analyzed using GC-MS equipped with MS Library System NIST62, Wiley 7 database for identification of biodiesel components.

2.4. Acidity determination

In this study, the acidity of the zeolites was determined using gravimetric method, based on the chemisorption of pyridine by the sample.

2.5. FTIR analysis

For functionality analysis using FTIR, the zeolite sample was scanned from 4000 – 400 cm⁻¹. Another purpose of this analysis was to evaluate the effect of calcination temperatures on the functionality of the samples.

2.6. XRD analysis

The X-ray diffractogram of the sample was produced using Cu K α radiation operated at 40 kV energy and 40 mA current, with angle (2 θ) in the range of 5–80° and the step of 2°/min.

2.7 SEM analysis

SEM analysis for microstructure evaluation was conducted on SEM instrument of FEI type Inspect S50 equipped with EDAX AMETEK.

28

3. Results and discussion

3.1. Acidity of zeolites

The acidity data of zeolites subjected to calcination at varied temperatures are shown in Table 1.

Table 1. Acidity of zeolit-A calcined at varied temperatures.

Calcination temperature (°C)	Acidity (mmol/g)
600	0.0451
700	0.0528
800	0.0829
900	0.0100

Experimental data in Table 1 reveal that the acidity of zeolites was quite significantly influenced by temperatures of calcination. It can be observed that increased temperature up to 800°C led to increased acidity, followed by sharp decrease for the sample calcined at 900°C. This decreased acidity is most probably associated with increased crystalline phase in the sample as demonstrated by the XRD results, thus reducing the capacity of the sample to absorb pyridine.

23. Functionality of zeolites

As can be observed in Figure 1, the FTIR spectra of the samples are basically similar regardless the calcination temperatures applied. The formation of bonds between O, Si, and Al is suggested by the appearance of distinctive peaks associated with the bonds between the three main elements of the samples.

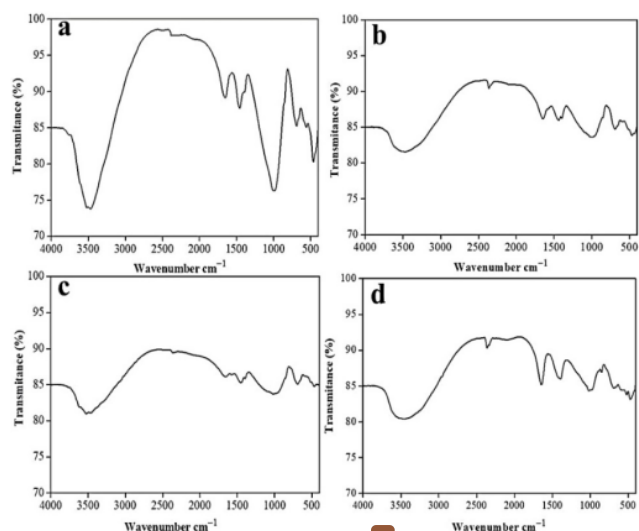


Figure 1. The FTIR spectra of zeolite-A samples calcined at 600 (a), 700 (b), 800 (c), and 900°C (d).

The Si-O-Si symmetric stretching is characterized by absorption bands in the area of about 1013 cm^{-1} and 465 cm^{-1} [25-27]. The peak at 3450 cm^{-1} is an indication of the presence of -OH group attached to the silica framework in the form of Si-OH, and absorbed water, which is confirmed by the peak at 1656 cm^{-1} . The formation of bond between Si and Al is characterized by the presence of peak located at around 691 cm^{-1} , assigned to stretching of Si-O-Al bond [28]. Absorption peak originated

from pyridine base is located at 1659 cm^{-1} which is related to the bending of N-H. The formation of a Lewis acid site, indicated by the peak in the position of approximately 1450 cm^{-1} , was observed in the samples calcined at 600°C (Figure 1a) and 800°C (Figure 1b). In the samples calcined at 700°C (Figure 1c) and 900°C (Figure 1d), on the other hand, this peak associated with Lewis acid disappears, but there is an indication that these two samples contain Brønsted acid site, suggested by the presence of absorption band at around 1640 cm^{-1} [29].

3.3. Structure of zeolites

The XRD diffractograms of the samples are presented in Figure 2. The diffractograms presented in Figure 2, clearly display that both amorphous and crystalline phases are present in all samples. This amorphous phase is in agreement with the nature of rice husk silica as amorphous material up to 900°C [27]. Crystalline phase identification was carried out using search and match procedure with the aid of software PCPDF for Window 1997. Using this computer program, several crystalline phases are identified, include cristobalite (PDF File: 39-1425), nepheline (PDF File: 35-0424), jadeite (PDF File: 22-1338), and albite (PDF File: 09-0466).

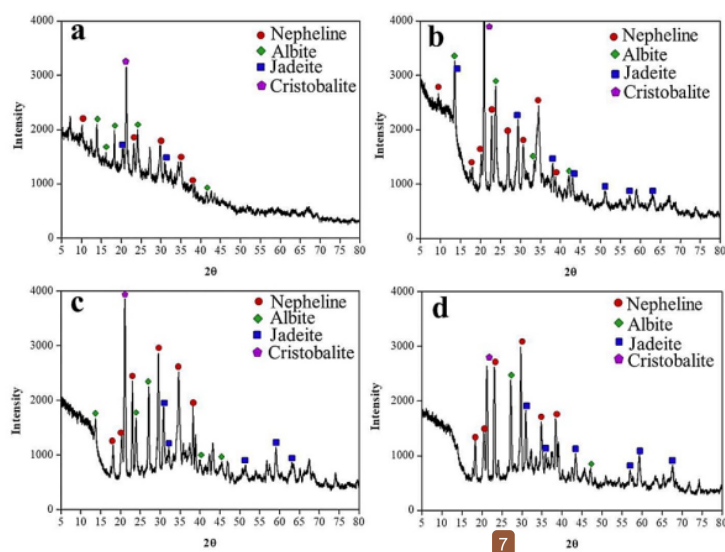


Figure 2. The X-ray diffractograms of zeolite-A samples calcined at 600°C (a), 700°C (b), 800°C (c), and 900°C (d).

The four diffractograms in Figure 2, suggest that to some extent, the formation of phases in the samples is influenced by the temperatures of calcination treatment applied. In the sample calcined at 600°C , cristobalite appears as the dominant phase, as suggested by significantly higher relative intensity of the peak representing this phase compared to those of the peaks representing the other phases.

The diffractograms also display that increased calcination temperatures resulted in gradual growth of crystalline phases, as indicated by increased intensities of the peaks. In addition, it can be seen that up to calcination temperature of 800°C , the cristobalite remains as the dominant phase, however significant change was observed in the sample calcined at 900°C , in which nepheline becomes the dominating phase. Overall, the XRD data reveal that the samples are multiphasic material, with cristobalite and nepheline as the most abundant phases.

3.4. Microstructure of zeolites

To assess the effect of calcination temperatures on microstructure, the micrographs of three samples, with 10000x magnification are compiled in Figure 3. The SEM images in Figure 3, clearly indicate the heterogeneous morphology of the surface of all samples, characterized by the formation of clusters having different shapes and sizes. The essence of the samples as porous materials is clearly reflected by the images, suggesting the potential use of the samples as catalyst. The images also display the presence of several crystalline phases as has also been indicated by the XRD results, include tetragonal-shaped cristobalite, hexagonal-shaped nepheline, monoclinic-shaped jadeite, and triclinic-shaped albite. In overall, characterization using SEM evidently suggests the existence of the samples as multiphase material.

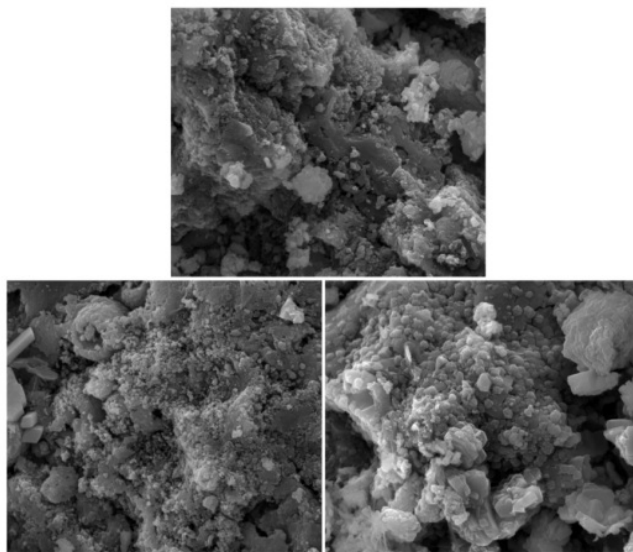


Figure 3. SEM images of zeolite-A samples calcined at 700 (a), 800 (b), and 900°C (c).

3.5. Analysis of transesterification product

The products of transesterification reaction using the zeolites were analyzed with GC-MS spectroscopy, and an example of GC chromatogram is shown in Figure 4.

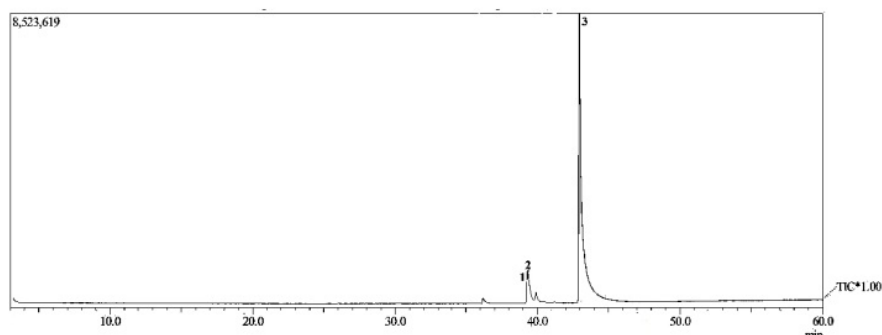


Figure 4. The GC chromatogram of *Ricinus communis* oil transesterification product.

Figure 4 shows the existence of 3 separate peaks in the chromatogram, indicating that the sample composed of three different compounds. With the aid of NIST62 Library System, the three compounds were identified as methyl linoleate, methyl elaidate, and methyl ricinoleate. These three compounds are methyl esters of glycerides contained in *Ricinius communis* oil commonly reported in literatures [30-31]. Formation of these methyl esters confirmed that transesterification took place confirming the catalytic activity of the zeolites synthesized. The relative composition of the sample was calculated by dividing the relative area of each of the peaks with the total area of all peaks. Using this calculation method, it was found that methyl ricinoleate contributes 87.21%, methyl elaidate contributes 6.7%, and methyl linoleate contributes 4.12%, to the sample. Another finding related to the activity tests is the achievement of reaction yields of 69 to 82%, which also support the existence of zeolite-A as a potential solid catalyst to support biodiesel industry.

4. Conclusions

This study demonstrates that zeolite-A could be prepared using silica extracted from rice husk and aluminum metal, through sol-gel process. Development of zeolite-A structure was revealed by the FTIR and XRD analyses, and the existence of the samples as porous and multiphasic materials by SEM analysis. The zeolites were found to exhibit catalytic activity as revealed by the results of transesterification of *Ricinius communis* oil. Conversion of glycerides contained in *Ricinius communis* oil into methyl esters with appreciable reaction yields indicate that zeolite-A synthesized exhibits good activity as catalyst for transesterification reaction.

Acknowledgment

The authors sincerely appreciate The Directorate of Research and Community Service, The Ministry of Research, Technology, and Higher Education, Republic of Indonesia, for grant in research scheme of Penelitian Berdampak Terapan 2017, contract number: 1638/UN26.21/KU/2017. The authors also appreciate the Integrated Laboratory and Center for Technology Innovation (LTSIT) University of Lampung for facility and data analysis.

References

- [1] Popp J, Lakner Z, Harangi-Rákos M and Fári M, 2014 The effect of bioenergy expansion: Food, energy, and environment *Renew Sust Energ Rev* **32** 559
- [2] Poltronieri P 2016 Alternative energies and fossil fuels in the bioeconomy era: what is needed in the next five years for real change *Challenges* **7** 1
- [3] Ridha B, Youssef S, Bezzarga M and Abderrabba M 2015 Waste frying oil with high levels of free fatty acids as one of the prominent sources of biodiesel production *J Mater Environ Sci* **6** 1178
- [4] Agarwal M, Chauhan G, Chaurasia S P and Singh K 2012 Study of catalytic behavior of KOH as homogeneous and heterogeneous catalyst for biodiesel production *J Taiwan Inst Chem E* **43** 89
- [5] Saydut A, Kafadar A B, Aydin F, Erdogan S, Kaya C, and Hammaci C 2016 Effect of homogenous alkaline catalyst type on biodiesel production from soybean [*Glycine Max* (L.) Merrill] oil *Indian J Biotechnol* **15** 596
- [6] Olivia R, Jamarun N, Arif S and Sirin Y A 2017 The utilization of dolomite as catalyst in biodiesel production *Rasayan J. Chem* **10** 160

- [7] Pandiangan K D, Jamarun N, Arief S, Simanjuntak W and Rilyanti M 2016 The effect of calcination temperatures on the activity of CaO and CaO/SiO₂ heterogeneous catalyst for transesterification of rubber seed oil in the presence of coconut oil as a co-reactant *Oriental J. Chem* **32** 3021
- [8] Lee F, Bennett J A, Manayil J C and Wilson K 2014 Heterogeneous catalysis for sustainable biodiesel production via esterification and transesterification *Chem Soc Rev* **43** 7887
- [9] Endalew K, Kiros Y and Zanzi R 2011 Heterogeneous catalysis for biodiesel production from *Jatropha curcas* oil (JCO) *Energy* **36** 2693
- [10] Takata T, Nakagoe O and Tanabe S 2012 Effect of Al loading on CaO catalysts for biodiesel production *ICRERA* doi 10.1109_ICRERA.2012.6477355
- [11] Doyle M, Albayati T M, Abbas A S and Alismael Z T 2016 Biodiesel production by esterification of oleic acid over zeolite Y prepared from kaolin *Renew Energ* **97** 19
- [12] Pandiangan K D, Jamarun N, Arief S and Simanjuntak W 2017 Synthesis of zeolite-x from rice husk silica and aluminum metal as a catalyst for transesterification of palm oil *J Mater Environ Sci* **8** 1797
- [13] Piraján J C M and Giraldo L 2013 Catalytic conversion process of methanol-to propylene (mtp) with zeolites *Rasayan J. Chem* **6** 172
- [14] Hassani M, Najafpour G D, Mohammadi M and Rabiee M 2014 Preparation, characterization and application of zeolite-based catalyst for production of biodiesel from waste cooking oil *J Sci Ind Res India* **73** 129
- [15] Carrero A, Vicente G, Rodríguez R, Linares M and Peso G D L 2011 Hierarchical zeolites as catalysts for biodiesel production from *Nannochloropsis* microalga oil *Catal Today* **167** 148
- [16] Wang Y, Wang H, Chuang T, Chen B and Lee D 2014 Biodiesel produced from catalyzed transesterification of triglycerides using ion-exchanged zeolite Beta and MCM-22 *Energy Procedia* **61** 933
- [17] Alaba P A, Sani Y M, Mohammed I Y, Abakr Y A and Daud W M A W 2016 Synthesis and application of hierarchical mesoporous HZSM-5 for biodiesel production from shea butter *J Taiwan Inst Chem E* **59** 405
- [18] Hassani M, Najafpour G D and Mohammadi M 2016 Transesterification of waste cooking oil to biodiesel using γ -alumina coated on zeolite pellets *J Mater Environ Sci* **7** 1193
- [19] Shrestha K, Ghimire J R and Gewali M B Biodiesel production from *Jatropha curcas* (L.) oil of Nepal by transesterification process 2013 **3** 603
- [20] Pandiangan K D, Jamarun N, Arief S, Simanjuntak W and Rilyanti M 2017 Influence of kinetic variables on rubber seed oil transesterification using bifunctional catalyst CaO-MgO/SiO₂ *Oriental J. Chem* **33** 2891

- [21] Huang F L, Zhu G L, Chen Y S, Meng F J, Peng M, Chen X F, He Z B, Zhang Z Y and Chen Y J 2015 Seed characteristics and fatty acid composition of castor (*Ricinus communis* L.) varieties in Northeast China *Phyton-Int J Exp Bot* **84** 26
- [22] Pandiangan K D, Jamarun N, Arief S and Simanjuntak W 2016 Transesterification of castor oil using MgO/SiO₂ catalyst and coconut oil as co-reactant *Orient J. Chem* **32** 385
- [23] Atabani E, Silitonga A S, Badruddin I A, Mahlia T M I, Masjuki H H and Mekhilef S 2012 A comprehensive review on biodiesel as an alternative energy resource and its characteristics *Renew Sust Energ Rev* **16** 2070
- [24] Bankovi'c-Ili'c B, Stamenkovi'c O S and Veljkovi'c V B 2012 Biodiesel production from non-edible plant oils *Renew Sust Energ Rev* **16** 3621
- [25] Simanjuntak W, Sembiring S, Manurung P, Situmeang R T M and Low I M 2013 Characteristics of aluminosilicates prepared from rice husk silica and aluminum metal *Ceram Inter* **39** 9369
- [26] Radev L, Michailova I, Georgiev H and Zaimova D 2016 Carbonate apatite formation on novel multiphase CaO-SiO₂-P₂O₅-MgO glass-ceramics in TRIS-HCl buffer *Process Appl Ceram* 2016 **10** 57
- [27] Simanjuntak W, Sembiring S, Pandiangan K D, Syani F and Situmeang R T M 2016 The use of liquid smoke as a substitute for nitric acid or extraction of amorphous silica from rice husk through sol-gel route *Orient J. Chem* **32** 2079
- [28] Mozgawa W, Krol M and Barackz K 2011 FT-IR studies of zeolites from different structural groups *Chemik* **65** 667
- [29] Tanabe K, Misono M, Hattori H and Ono Y 1990 *New Solid Acids and Bases 1st ed* Elsevier Science
- [30] Figueroa R, Carrillo P O, Paneque M, Nereo F J P and Medina J Q 2016 High-yield production of biodiesel by non-catalytic supercritical methanol transesterification of crude castor oil (*Ricinus communis*) *Energy* **107** 165
- [31] Silitonga S, Masjuki H H, Mahlia T M I, Ong H C, Chong W T and Boosroh M H 2013 Overview properties of biodiesel diesel blends from edible and non-edible feedstock *Renew Sust Energ Rev* **22** 346

Paper Number-first author-Part of title

example: 1570477829-Kamisah Delilawati Pandiangan-Implementation of New Features.pptx

Subject: '[ICASMI'18] Power Point #Paper Number'.

ORIGINALITY REPORT

20%

SIMILARITY INDEX

9%

INTERNET SOURCES

16%

PUBLICATIONS

3%

STUDENT PAPERS

PRIMARY SOURCES

1

Asmaa Fadel, Nasruddin Hassan. "Separation axioms of bipolar soft topological space", Journal of Physics: Conference Series, 2019

Publication

4%

2

W. Simanjuntak, S. Sembiring, P. Manurung, R. Situmeang, I.M. Low. "Characteristics of aluminosilicates prepared from rice husk silica and aluminum metal", Ceramics International, 2013

Publication

2%

3

Submitted to City University

Student Paper

2%

4

M Yanis, A S Mohruni, S Sharif, I Yani, A Arifin, B Khona'ah. "Application of RSM and ANN in Predicting Surface Roughness for Side Milling Process under Environmentally Friendly Cutting Fluid", Journal of Physics: Conference Series, 2019

Publication

1%

5

I . Herlina, W . Simanjuntak, M . Rilyanti, E. R.

Safitra. "PHYSICAL CHARACTERISTICS AND CATALYTIC ACTIVITY OF SULFATED SUGARCANE BAGASSE SILICA ($\text{SiO}_2/\text{SO}_3\text{-H}^+$) FOR COCONUT OIL TRANSESTERIFICATION", Rasayan Journal of Chemistry, 2019

Publication

1%

6

biodieseleducation.org

Internet Source

1%

7

www.jmcs.org.mx

Internet Source

1%

8

tel.archives-ouvertes.fr

Internet Source

1%

9

Netti Aryani, Saberina Hasibuan, Ainul Mardiah, Hafrijal Syandri. "Morphometric Characteristics of Asian Catfish, *Hemibagrus wyckii* (Bleeker, 1858) (Bagridae), from the Riau Province of Indonesia", Pakistan Journal of Biological Sciences, 2017

Publication

1%

10

Ziwei Song, Wei Jin, Faming Gao, Xin Jin. "Recent Advances in Catalyst Development for Transesterification of Dialkyl Carbonates with Phenol", Industrial & Engineering Chemistry Research, 2020

Publication

1%

11

Holmgreen, E.M.. "Pd-based sulfated zirconia prepared by a single step sol-gel procedure for lean NO_x reduction", Journal of Molecular Catalysis. A, Chemical, 20070601

Publication

<1 %

12

Submitted to The University of Manchester

Student Paper

<1 %

13

Ashutosh Agarwal, Seong-Jae Park, Jeong-Hun Park. "Upgrading of Kraft Lignin-Derived Bio-Oil over Hierarchical and Nonhierarchical Ni and/or Zn/HZSM5 Catalysts", Industrial & Engineering Chemistry Research, 2019

Publication

<1 %

14

Indika Thushari, Sandhya Babel, Chanatip Samart. "Biodiesel production in an autoclave reactor using waste palm oil and coconut coir husk derived catalyst", Renewable Energy, 2019

Publication

<1 %

15

Soo-Young No. "Application of Liquid Biofuels to Internal Combustion Engines", Springer Science and Business Media LLC, 2019

Publication

<1 %

16

Y Ambarwati, L Septiani, S Bahri, Yandri, S Hadi, N D Kesumaningrum. " Antidiabetic Bioactivity Test Of Chromium(III) And Copper(II) Complex Compounds On Mice ", IOP Conference Series: Earth and Environmental

<1 %

17

El Shafei, G.M.. "Fractal analysis of hydroxyapatite from nitrogen isotherms", Journal of Colloid And Interface Science, 20040915

Publication

<1 %

18

Arif Hidayat, Bachrun Sutrisno. "Free Fatty Acids Esterification on Palm Oil Sludge using Zirconia-supported Indonesia Natural Zeolite as Heterogeneous Catalyst", Oriental Journal of Chemistry, 2018

Publication

<1 %

19

www.frontiersin.org

Internet Source

<1 %

20

www.hindawi.com

Internet Source

<1 %

21

worldwidescience.org

Internet Source

<1 %

22

Ying-Chen Chen, Dai-Ying Lin, Bing-Hung Chen. "Transesterification of acid soybean oil for biodiesel production using lithium metasilicate catalyst prepared from diatomite", Journal of the Taiwan Institute of Chemical Engineers, 2017

Publication

<1 %

23

Simon Sembiring. "STRUCTURAL AND PHYSICAL PROPERTIES OF REFRACTORY

<1 %

CORDIERITE PRECURSORS PREPARED FROM RICE HUSK SILICA WITH DIFFERENT M g O ADDITION", Ceramics - Silikaty, 2018

Publication

24

www.techscience.com

Internet Source

<1 %

25

sintadev.ristekdikti.go.id

Internet Source

<1 %

26

Yao, W.F.. "Photocatalytic property of perovskite bismuth titanate", Applied Catalysis B, Environmental, 20040915

Publication

<1 %

27

dx.doi.org

Internet Source

<1 %

28

www.empa.ch

Internet Source

<1 %

29

www.imedpub.com

Internet Source

<1 %

30

espace.curtin.edu.au

Internet Source

<1 %

31

Valentina I. Loganina, Marija E. Sadovnikova, Walery Jezierski, Dorota Małaszkiwicz. "Modification of Lime Mortars with Synthesized Aluminosilicates", IOP Conference Series: Materials Science and Engineering, 2017

Publication

<1 %

32

Qiuyun Zhang, Yutao Zhang, Taoli Deng,
Fangfang Wei, Jiaying Jin, Peihua Ma.
"Sustainable production of biodiesel over
heterogeneous acid catalysts", Elsevier BV,
2020

Publication

<1%

Exclude quotes On

Exclude bibliography On

Exclude matches Off