

## Journal of The Korean Wood Science and Technology

Vol. 45 No. 4

July 2017

## CONTENTS-II

- Effects of Lignocellulosic Growing Media to The Prevention of Forest Soil Erosion  
Jong-Soo Jo, Si Young Ha, Ji Young Jung, Ji-Su Kim, Jeong Bin Nam, Jae-Kyung Yang ..... 419
- Bonding Performance of Maltodextrin and Citric Acid for Particleboard Made From Nipa Fronds  
Mahdi Santoso, Ragil Widyorini, Tibertius Agus Prayitno, Joko Sulisty ..... 432
- Effect of Panel Density and Resin Content on Properties of Medium Density Fiberboard  
Min-Kug Hong, Muhammad Adly Rahandi Lubis, Byung-Dae Park ..... 444
- Phenolic Compounds from Japanese anise (*Illicium anisatum* L.) Twigs  
Hee-Jeong Min, Young-Soo Bae ..... 456
- Anatomical Characteristics and Air-dry Density of Young Trees of Teak Clones Planted in Indonesia  
Fanny Hidayati, Futoshi Ishiguri, Sri Nugroho Marsoem ..... 463
- Effect of Analytical Parameters of Gel Permeation Chromatography on Molecular Weight Measurements of Urea-Formaldehyde Resins  
Bora Jeong, Byung-Dae Park ..... 471

## Journal of The Korean Wood Science and Technology

Vol. 45 No. 4

July 2017

## CONTENTS-I

- Qualitative and Quantitative Anatomical Characteristics of Four Tropical Wood Species from Moluccas, Indonesia  
Wahyu Hidayat, Yun Ki Kim, Woo Seok Jeon, Ju Ah Lee, Ah Ran Kim, Se Hwi Park, Rohny S Maail, Nam Hun Kim ..... 369
- Effect of Moisture Content of Sawdust and Ratio of Length to Diameter of a Hole in Flat-die Pelletizer on The Fuel Characteristics of Wood Pellets Produced with *Quercus mongolica*, *Pinus densiflora*, *Pinus rigida* and *Larix kaempferi*  
In Yang, Seong-ho Kim, Gyu-Seong Han ..... 382
- Partial Least Squares Analysis on Near-Infrared Absorbance Spectra by Air-dried Specific Gravity of Major Domestic Softwood Species  
Sang-Yun Yang, Yonggun Park, Hyunwoo Chung, Hyunbin Kim, Se-Yeong Park, In-Gyu Choi, Ohkyung Kwon, Kyu-Chae Cho, Hwanmyeong Yeo ..... 399
- Performance of Melamine-Urea-Formaldehyde Resin Adhesives at Various Melamine Contents for Bonding Glued Laminated Timber Under High Frequency Heating  
Min-Kug Hong, Byung-Dae Park, Keon-Ho Kim, Kugbo Shim ..... 409

## Journal of The Korean Wood Science and Technology

### Aims and Scope

The *Journal of The Korean Wood Science and Technology (JKWST)* launched in 1973 as an official publication of The Korean Society of Wood Science and Technology has been served as a core of knowledges on wood science and technology. The Journal acts as a medium for the exchange of research in the area of science and technology related to wood, and publishes results on the biology, chemistry, physics and technology of wood and wood-based products. Research results about applied sciences of wood-based materials are also welcome. The Journal is published bimonthly, and printing six issues per year. Supplemental or special issues are published occasionally.

The abbreviated and official title of the journal is '*J. Korean Wood Sci. Technol.*'. All submitted manuscripts written in Korean or English are peer-reviewed by more than two reviewers. The title, abstract, acknowledgement, references, and captions of figures and tables should be provided in English for all submitted manuscripts. All articles are indexed in SCOPUS and Korea Citation Index (KCI).

All manuscripts should be submitted to the editorial office via the on-line system at <https://jwst.jams.or.kr>. The website of the Journal is either <http://kswst.or.kr/>, or <https://jwst.jams.or.kr/> where full text is available. The website of the Society is <http://www.kswst.or.kr/>. This journal was supported by the Korean Federation of Science and Technology Societies (KOFST) Grant funded by the Korean Government.

## Journal of The Korean Wood Science and Technology

Volume 45, Number 4, Printed on July 25, 2017

© All rights are reserved for The Korean Society of Wood Science and Technology.

Published by and Subscription Order to:  
The Korean Society of Wood Science and Technology  
c/o Department of Forest Products  
National Institute of Forest Science (NIFoS)  
2nd Floor, Namu Byungwon-dong  
57 Hoegi-ro, Dongdaemun-Gu  
Seoul 02455, Republic of Korea  
E-mail : [wood@kswst.or.kr](mailto:wood@kswst.or.kr)  
There is a charge for the subscription.

Printed by:  
Green Pine Media Inc.  
Tel: (02)2274-1128, Fax: (02)2266-4427

## Qualitative and Quantitative Anatomical Characteristics of Four Tropical Wood Species from Moluccas, Indonesia<sup>1</sup>

Wahyu Hidayat<sup>2,3</sup> · Yun Ki Kim<sup>2</sup> · Woo Seok Jeon<sup>2</sup> · Ju Ah Lee<sup>2</sup> ·  
Ah Ran Kim<sup>2</sup> · Se Hwi Park<sup>4</sup> · Rohny S Maail<sup>5,†</sup> · Nam Hun Kim<sup>2,†</sup>

### ABSTRACT

The objective of this study was to compare the wood anatomical characteristics of local tree species in Moluccas, Indonesia *i.e.*, Moluccan ironwood (*Intsia bijuga*), linggua (*Pterocarpus indicus*), red meranti (*Shorea parvifolia*), and gofasa (*Vitex cofassus*). Qualitative evaluation was conducted by observing the anatomical structure in cross, radial, and tangential sections of each sample. For the quantitative evaluation, the dimensions of vessels, rays, and fibers were measured. Qualitative evaluation showed that crystals were observed in Moluccan ironwood, linggua, and gofasa, while resin canals were only observed in red meranti. Tyloses were frequently observed in gofasa but infrequently observed in linggua and red meranti. Quantitative evaluation showed that Moluccan ironwood with the higher density had thicker fiber wall, higher quantity of ray number, and wider rays than the other species. Red meranti had higher values of ray height and fiber length than the other three species. The results also revealed that linggua showed the highest values of relative crystallinity and crystallite width. Red meranti and gofasa showed similar values of relative crystallinity and crystallite width, while Moluccan ironwood showed the lowest values. The basic qualitative and quantitative anatomical characteristics discussed could provide useful information for further utilizations of such wood species.

**Keywords** : anatomical characteristics, *Intsia bijuga*, Moluccan woods, *Pterocarpus indicus*, *Shorea parvifolia*, *Vitex cofassus*

### 1. INTRODUCTION

Moluccas (Indonesian Maluku) is located in the east part of Indonesia. In the Dutch era it was also known as the Spice Islands where nut-

meg, mace, cloves and several other valuable spices were grown. Moluccas forest areas cover 5% (6.43 million ha) of the permanent forest (128.22 million ha) of Indonesia (Ministry of Environment and Forestry, Republic of

<sup>1</sup> Date Received March 10, 2017, Date Accepted April 18, 2017

<sup>2</sup> College of Forest and Environmental Sciences, Kangwon National University, Republic of Korea

<sup>3</sup> Department of Forestry, Faculty of Agriculture, Lampung University, Indonesia

<sup>4</sup> Department of Forest Products, Faculty of Forestry, Bogor Agricultural University, Indonesia

<sup>5</sup> Faculty of Forestry, University of Pattimura, Indonesia

† Corresponding author: Rohny S Maail (e-mail: rohny\_maail@yahoo.com)

† Corresponding author: Nam Hun Kim (e-mail: kimnh@kangwon.ac.kr)

Indonesia, 2015). The permanent forest areas of Moluccas are classified based on their main functions, *i.e.* conservation forest of 0.64 million ha, protection forest of 1.21 million ha, production forest of 2.69 million ha and conversion forest of 1.89 million ha (Ministry of Environment and Forestry, Republic of Indonesia, 2015). The forests in Moluccas are the home of valuable woods from the family of *Fabaceae*, *Calophyllaceae*, *Ebenaceae*, *Dipterocarpaceae*, *etc.*

Moluccan ironwood (*Intsia bijuga*), linggua (*Pterocarpus indicus*), red meranti (*Shorea parvifolia*), and gofasa (*Vitex cofassus*) are some of the important wood species in Moluccas. Moluccan ironwood is a slow growing hardwood tree which produces valuable timbers due to its beautiful color and texture (Soerianegara and Lemmens, 1993; Hu *et al.*, 2012). The wood is dense and has excellent durability, dimensional stability, and strength properties making it ideally suited for use as wood flooring and other outdoor applications (Marler, 2015; Hsiao *et al.*, 2016; Liao *et al.*, 2016). The ironwood trees are also planted in soil conservation projects due to its ability to fix nitrogen even in a highly saline mangrove environment (Eganathan *et al.*, 2000).

Linggua trees grow extensively in Philippines, New Guinea, Malaysia, and Indonesia. In Indonesia it is distributed in Moluccas, Java, Sulawesi, Bali, West and East Tenggara, and Papua (Orwa *et al.*, 2009). The tree is adaptable to a wide range of soil types including infertile, alkaline, stony soils to deep, fertile,

loamy, alluvial soils (Lim, 2014). The wood has straight or irregularly wavy grain and sometimes forms a rare and valuable burl form known as Amboyna burl that is often used for high-class furniture, cabinets and decorative sliced veneer. The wood contains antifungal compounds but the resistance against termite is considered low to moderately resistant (Kusuma *et al.*, 2004; Febrianto *et al.*, 2015).

Red meranti is a native tree species of Southeast Asia occurring in the rainforests of Malaysia, Indonesia and the Philippines (Appanah and Turnbull, 1998). The tree is a relatively slow growing species. In intensively managed forest plantations, the annual diameter increment in red meranti is between 1.17-1.20 cm hence a rotation of 30 years is feasible for the production of commercial logs (Appanah and Weinland, 1993). The species is one of the most economically important woods in the *Dipterocarpaceae* family which is often used to make furniture, veneers, plywood, and other high value wood products (Widiyatno *et al.*, 2016).

Gofasa is native to Fiji, Indonesia, Malaysia, Papua New Guinea, Thailand, Vietnam (Orwa *et al.*, 2009). The wood is very strong and durable but difficult to treat with preservatives. Gofasa tree produces highly valued timber that is generally used for house construction, boats and domestic utensils such as bowls and platters.

Our previous investigations have reported the anatomical characteristics of fast growing species from Indonesia (Kim *et al.*, 2012), includ-

**Table 1.** General information on wood samples

Common name	Scientific name	Botanical family	Density (g/cm <sup>3</sup> )	Shrinkage (%)	
				R	T
Moluccan ironwood	<i>Intsia bijuga</i> (Colebr.) Kuntze	Fabaceae	1.02	4.30	7.70
Linggua	<i>Pterocarpus indicus</i> Willd.	Fabaceae	0.64	2.90	5.00
Red meranti	<i>Shorea parvifolia</i> Dyer	Dipterocarpaceae	0.51	3.20	9.70
Gofasa	<i>Vitex cofassus</i> Reinw. ex Blume	Lamiaceae	0.79	4.20	8.00

Notes: R= radial direction, and T= tangential direction.

ing the physical, mechanical, combustion, natural durability, and weathering properties (Kim *et al.*, 2014; Park *et al.*, 2015; Febrianto *et al.*, 2015; Park *et al.*, 2016; Hidayat *et al.*, 2017). In this paper we discuss the qualitative and quantitative anatomical characteristics of four slow growing species from Indonesia as Moluccan ironwood, linggua, red meranti, and gofasa. The information and technical reports on the anatomical characteristics of the four wood species are available in some publications and online database (Soerianegara and Lemmens, 1993; Hillis, 1996; Richter and Dallwitz, 2000; Ogata *et al.*, 2008). However, they mostly discussed the qualitative anatomical characteristics of the woods. Therefore this study is important in providing the information on both the qualitative and quantitative anatomical characteristics of the woods for further development of woody bio-resources.

## 2. MATERIALS and METHODS

### 2.1. Materials

Four tropical hardwood species *i.e.* Moluccan ironwood, linggua, red meranti, and gofasa

were used for this study. The scientific names, botanical families and some physical properties of the specimens used in this study are given in Table 1. The samples of the four wood species were obtained from the forest in Moluccas Island, Indonesia (3°42'18"S 128°10'12"E). The samples were conditioned at room temperature of 25°C and a relative humidity of 65% for 2 weeks prior to evaluation of their properties.

### 2.2. Methods

#### 2.2.1. Anatomical Characteristics

For the evaluation of anatomical characteristics, the wood samples were cut into small blocks. The blocks were then sliced using a sliding microtome (Nippon Optical works, Japan.) in cross, radial, and tangential sections with the thickness of 10-15 µm. The wood slices were then stained with safranin-astra blue according to the methods in the previous study (Qi *et al.*, 2016). After staining, slices were dehydrated by a series of alcohol (50%, 70%, 90%, 95% and 99%). Then, mounted sections with Canada balsam were observed by an optical microscope (Nikon Eclipse, E600).

For the qualitative evaluation, the wood struc-

tures in cross, radial, and tangential sections of each sample were observed. For the quantitative evaluation, the anatomical characteristics such as number and diameters of vessels, number, width, and height of rays, fiber wall thickness and length were measured and compared with the IAWA hardwood feature list (Wheeler *et al.*, 1989) using Total Imaging Isolation (IMT, I-solution Lite). Thirty random measurements were taken for each character to obtain a mean value.

For SEM observation, samples were cut with dimension of  $5 \times 5 \times 5 \text{ mm}^3$ , air-dried and coated with gold using a Gressington sputter coater (ULVAC G-50DA, Japan) and observed with a scanning electron microscope (JSM-5510, Japan).

#### 2.2.2. Crystalline Characteristics

An X-ray diffractometer (Rigaku DMAX2100V, Japan) equipped with a Cu target ( $\lambda = 0.1542 \text{ nm}$ ) was used for measuring the crystalline properties, at 40 kV and 40 mA. The relative crystallinity and crystallite width were calculated by Segal's method (Segal *et al.*, 1959) and Scherrer's equations (Alexander *et al.*, 1969), respectively.

### 3. RESULTS and DISCUSSION

#### 3.1. Qualitative Anatomical Characteristics


##### 3.1.1. Moluccan Ironwood

Moluccan ironwood had diffuse-porous with the vessels of solitary or radial multiples of 2-3 cells (Fig. 1A). The axial parenchyma aliform

and confluent with broad wings and crystal-liferous cells were present in the periphery of axial parenchyma (Fig. 1B). In radial section large amounts of crystals were observed in axial parenchyma (Fig. 1C), similar to the observation by Hillis (1987). Hillis (1996) also reported that the crystals contained in some vessels are a unique feature of the genus of *Intsia*, including *Intsia bijuga* and *Intsia palembanica*. In addition, the specific crystals were reported as yellow crystals of pure robinetin (a flavonol). Ray cells mostly displayed the procumbent form. Vessel perforation plates were simple with alternated intervessel pits (Fig. 1D). The wood rays consisted mostly of 1-2- or 1-4-seriate cells (Fig. 1E). Inclusions were also found in the vessels on cross, radial, and tangential sections (Fig. 1B, D, F). The characteristics of Moluccan ironwood are in complete agreement with those observed in previous studies (Richter and Dallwitz, 2000; Ogata *et al.*, 2008).

##### 3.1.2. Linggua

Linggua showed diffuse-porous and/or semi-ring porous (Fig. 2A). Axial parenchymas were present with bands or without bands. Vessels were solitary and radial multiple of 2-3 vessels. Tyloses were observed in the vessels but were infrequent (Fig. 2B). Ogata *et al.* (2008) also reported that tyloses were infrequently observed in the vessels of linggua. Crystals were observed in the axial parenchyma (Fig. 2C, D). Richter and Dallwitz (2000) reported the existence of crystals in the apo-

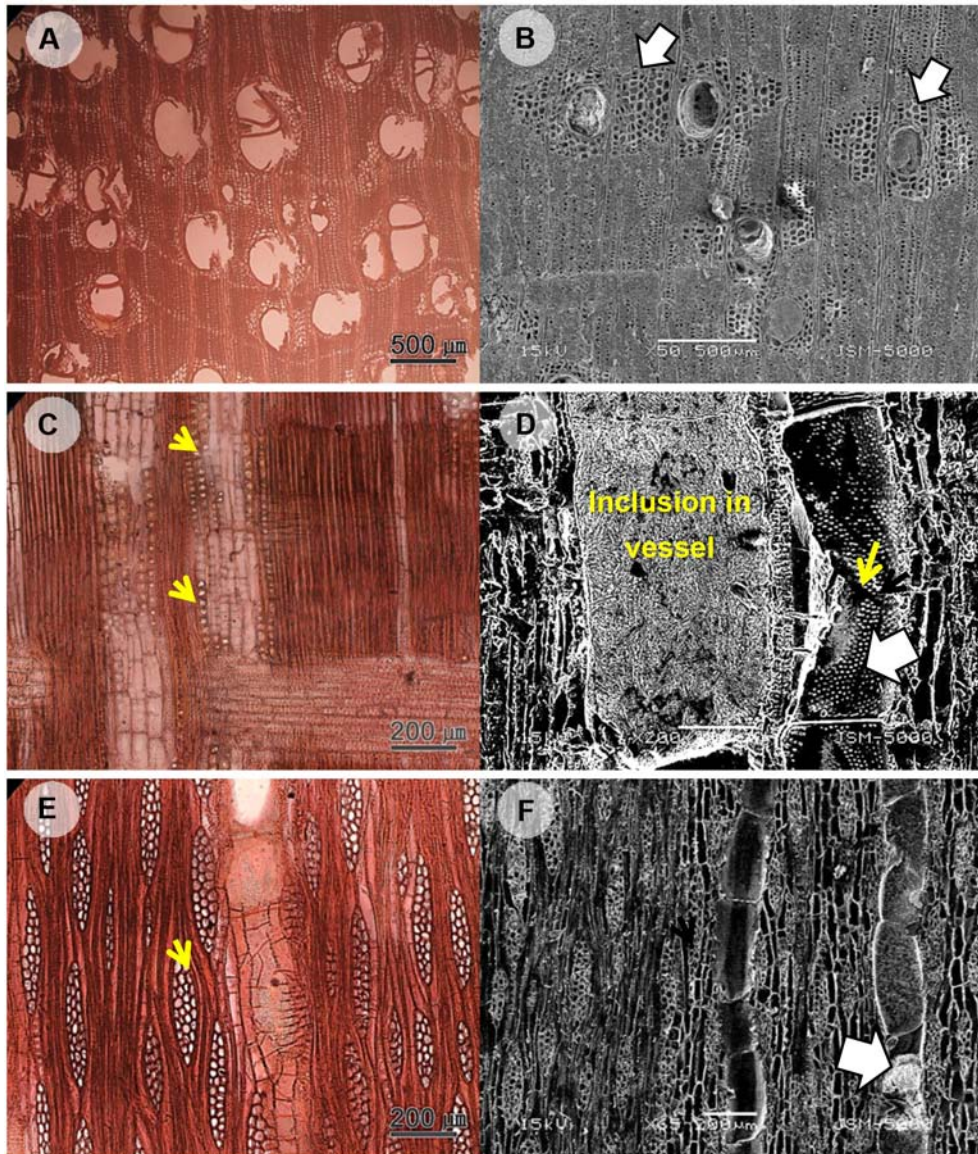


**Fig. 1.** Optical (left) and scanning electron micrographs (right) of Moluccan ironwood: (A) diffuse-porous; (B) arrows show axial aliform and confluent parenchyma with broad wings; (C) arrows show crystals in axial parenchyma; (D) inclusion in vessel; simple perforation (white arrow) and alternated intervessel pits (yellow arrow); (E) rays composition; (F) arrow shows inclusion in vessel.

trachealaxial parenchyma. Ogata *et al.* (2008) also observed crystals in chambered axial parenchyma cells and scattered crystals among fi-

bers and parenchyma. However they could not observe crystals in rays. Ray cells were of the procumbent form (Fig. 2C). Ray width was ex-



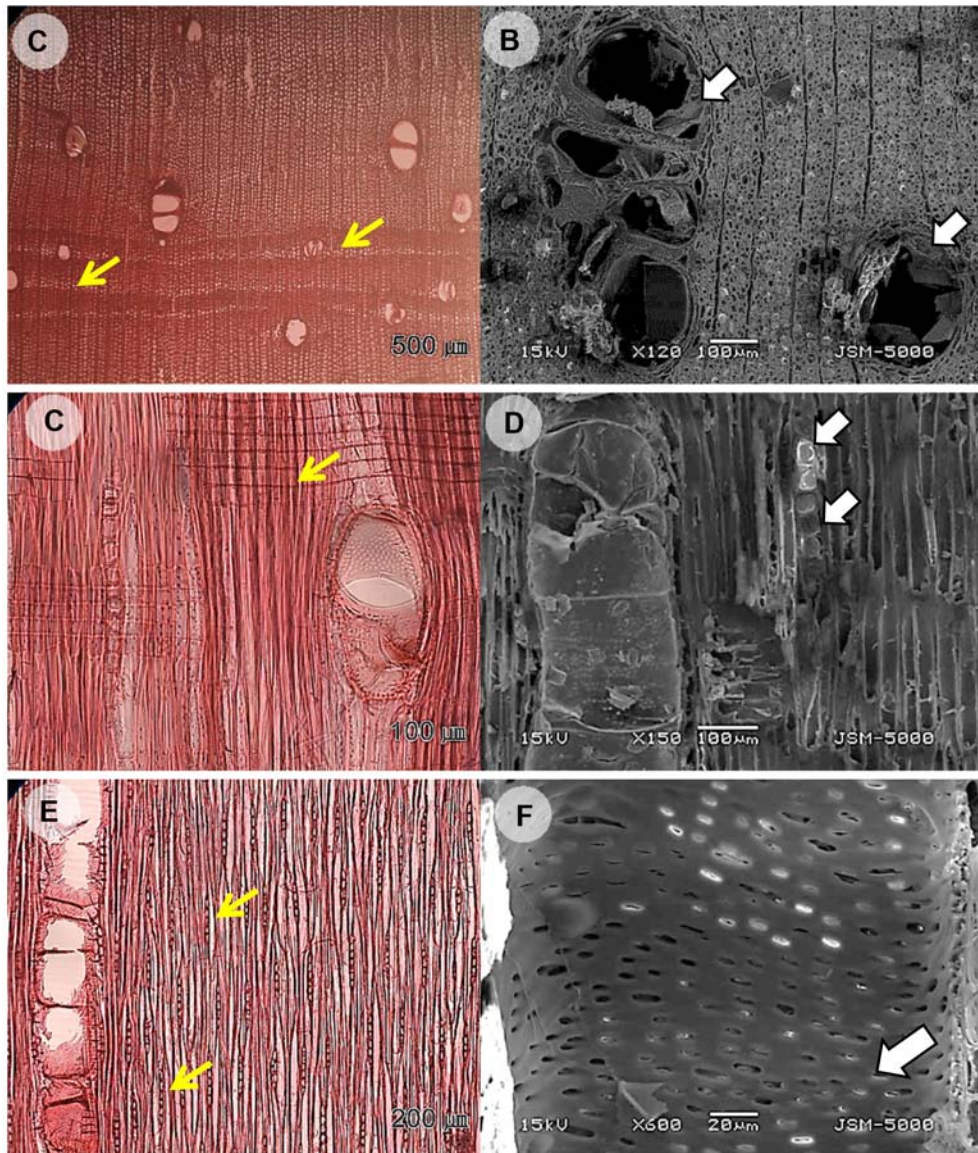


**Fig. 2.** Optical (left) and scanning electron micrographs (right) of lingua: (A) banded axial parenchyma (arrows); (B) tyloses in the vessels; (C) procumbent form of ray cells; (D) arrows show crystals in axial parenchyma; (E) ray composition exclusively uniseriate; (F) arrows show alternated intervessel pits with coalescent apertures.

clusively uniseriate (Fig. 2E). Perforation plates were simple with alternated intervessel pits (Fig. 2D, F).

### 3.1.3. Red Meranti

Red meranti had diffuse-porous with the vessels were arranged in no specific pattern; some



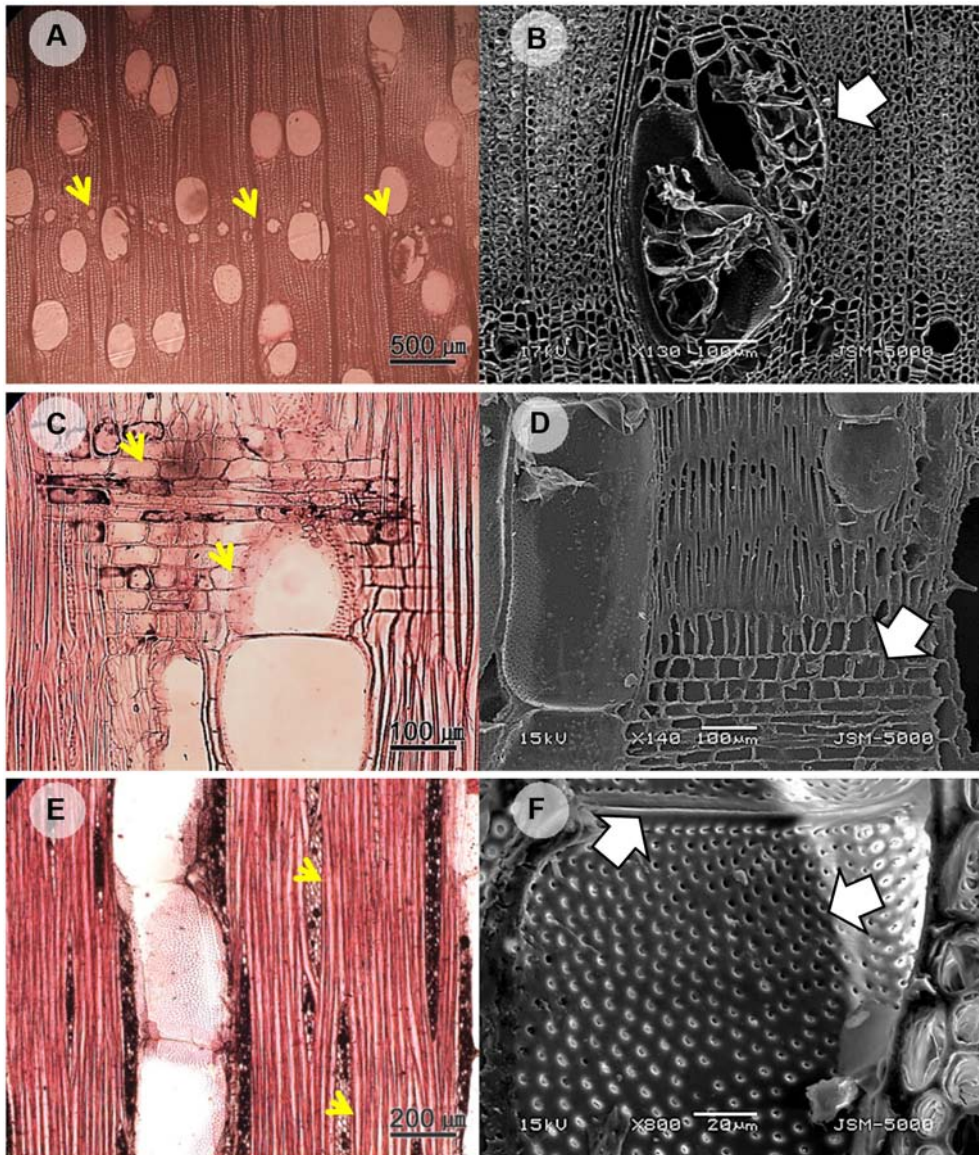

**Fig. 3.** Optical (left) and scanning electron micrographs (right) of red meranti: (A) axial resin canals in a concentric line; (B) tyloses in the vessels; (C, D) ray composition in radial section; (E) arrows show rays with 2-6-seriate cells; (F) simple vessel perforation with alternated intervessel pits.

were solitary and radial multiples of 2-3 cells (Fig. 3A, 3B). Axial resin canals in a concentric line were observed. Sass *et al.* (1995) also observed similar characteristics in *Shorea*

*leprosula*. They observed abundant resin canals mostly in tangential bands together with parenchyma, thus giving the impression of growth boundaries. Ray cells displayed the procumbent

**Table 2.** Quantitative anatomical characteristics of the four Moluccan wood species

Characteristics	Species				IAWA list
	Moluccan ironwood	Linggua	Red meranti	Gofasa	
Vessel number/mm <sup>2</sup>	2.2 (0.9)*	1.9 (0.8)*	2.0 (0.8)*	16.3 (2.4)**	*Feature 46: ≤ 5 per mm <sup>2</sup> **Feature 47: 5-20 per mm <sup>2</sup>
Vessel diameter (µm)	223.5 (19.3)**	196.4 (16.4) *	249.8 (16.6)**	143.8 (24.2)*	*Feature 42: 100-200 µm **Feature 43: ≥ 200 µm
Ray number/mm <sup>2</sup>	9.5 (1.5)**	4.8 (1.2)**	2.4 (0.9)*	9.6 (1.7)**	*Feature 114: ≤ 4 per mm <sup>2</sup> **Feature 115: 4-12 per mm <sup>2</sup>
Ray width (µm)	65.6 (7.1)	12.7 (2.3)	52.7 (3.7)	37.5 (6.2)	-
Ray width	1-3**	uniseriate*	2-6***	1-3**	*Feature 96: ray exclusively uniseriate **Feature 97: 1 to 3 cells ***Feature 98: 4- to 10-seriate
Ray height (µm)	421.9 (88.9)	160.1 (15.6)	760.1 (137.7)	321.1 (100.6)	-
Fiber wall thickness (µm)	10.2 (1.9)	7.1 (3.2)	8.1 (2.4)	8.7 (1.6)	-
Fiber length (µm)	1318.6 (90.8)	901.8 (75.7)	1457.4 (94.8)	1108.6 (47.9)	Feature 72: 900-1600 µm

and square form (Fig. 3C). Tyloses were present but infrequently observed (Fig. 3D). The wood rays were 2-6 cells wide (Fig. 3E). Vessel perforation plates were simple with alternated intervessel pits (Fig. 3F).

#### 3.1.4. Gofasa


Gofasa had diffuse-porous (Fig. 4A). The vessels were arranged in no specific pattern, including solitary and radial multiples of 2-4 cells. Abundant tyloses were observed in vessels (Fig. 4B). Tyloses affected the permeability of wood which resulted in difficulty drying and preservative impregnation (Shmulsky and Jones, 2011). The existence of tyloses is the reason why gofasa is preferred for traditional boat building in Sulawesi, Indonesia (Kurniawan, 2013). Ray cells displayed the procumbent form

(Fig. 4C). Radial section also showed the presence of small crystals in ray cells (Fig. 4D), which had also been observed in the previous studies (Richter and Dallwitz, 2000; Ogata *et al.*, 2008). The wood rays consisted of 1-2- to 1-3-seriate (Fig. 4E, F). Vessel perforation plates were simple with alternated intervessel pits.

### 3.2. Quantitative Anatomical Characteristics

The quantitative anatomical characteristics of the four wood species are summarized in Table 2. Gofasa had the most vessel number per mm<sup>2</sup>, while Moluccan ironwood, linggua, and red meranti had a similar vessel number. Moluccan ironwood, linggua, and red meranti also had similar values of vessel diameter which were



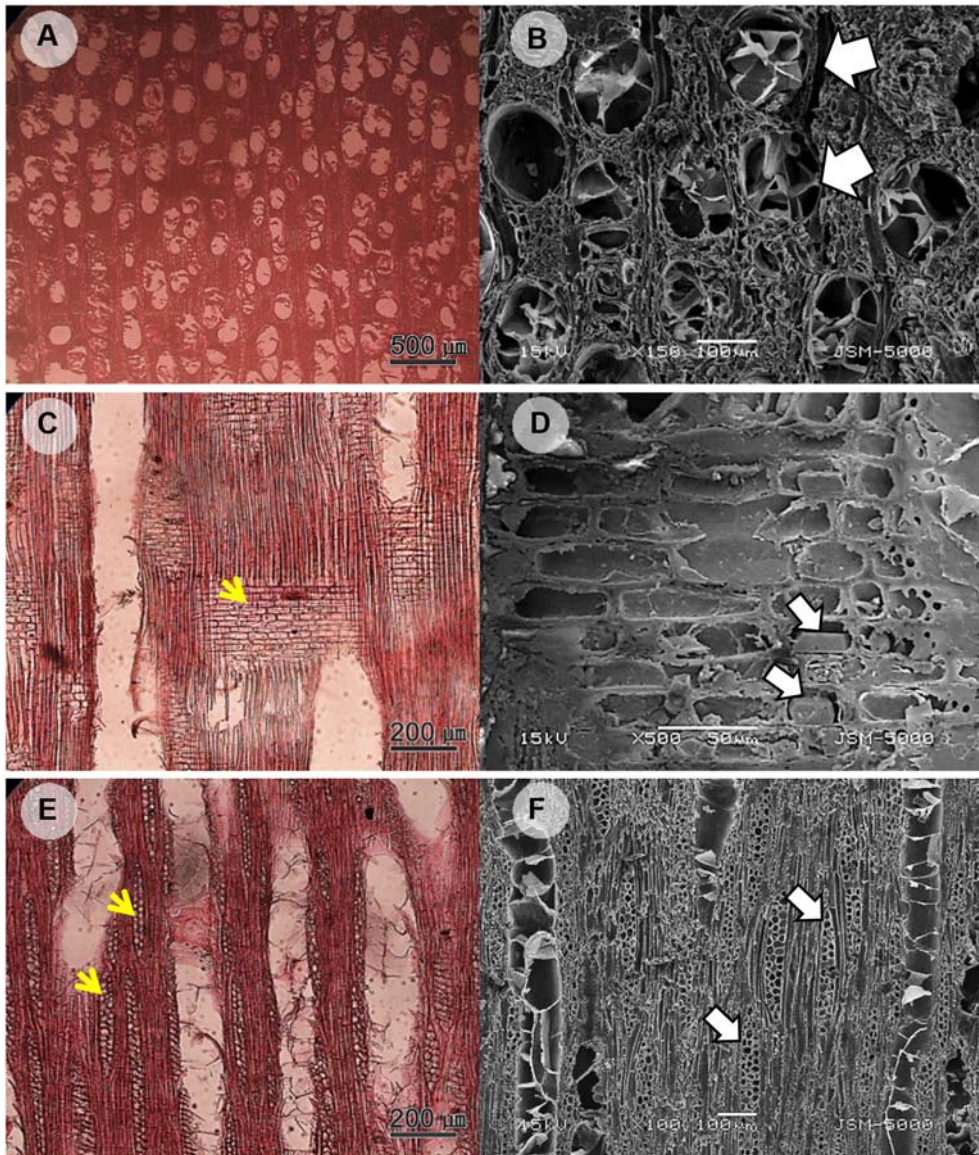

**Fig. 4.** Optical (left) and scanning electron micrographs (right) of gofasa: (A) diffuse-porous; (B) tyloses in the vessels; (C) procumbent form of ray cells; (D) arrow shows crystals in ray cells; (E, F) rays composition in tangential section.

significantly higher than gofasa. The Moluccan ironwood with higher density had thicker fiber wall, higher quantity of ray number, and wider rays than the other species, while red meranti

had higher values of ray height and fiber length than the other three species. The fiber length of Moluccan ironwood varies a little from earlier descriptions by Baar *et al.* (2013) who reported

**Table 3.** Crystalline characteristics of the four Moluccan wood species


Species	Relative crystallinity (%)	Crystallite width (nm)
Moluccan ironwood	50.1	2.76
Linggua	71.7	3.27
Red meranti	68.3	3.02
Gofasa	64.4	2.89

an average dimensions of 1392  $\mu\text{m}$ . However, the ray height and ray width varies significantly from the results of Baar *et al.* (2013), they reported average dimensions of 273  $\mu\text{m}$  and 27.4 for ray height and ray width, respectively. Fiber length is an important wood quality attribute for the pulp and paper industry, in which longer fibers are necessary to make stronger paper (Shmulsky and Jones, 2011).

### 3.3. Crystalline Characteristics

The crystalline characteristics of the four wood species are shown in Table 3 and the associated X-Ray diffractograms are shown in Fig. 5. Linggua had the highest values of relative crystallinity of 71.7% and crystallite width of 3.27 nm. Red meranti and gofasa had comparable values of relative crystallinity and crystallite width, while the lowest values were observed in Moluccan ironwood with of 50.1% of relative crystallinity and 2.76 nm of crystallite width. In Figure 5, we can find the peaks from calcium crystals at  $2\theta = 15, 21$  and  $24$  degree.

The relative crystallinity correlated with the physical, chemical and mechanical properties of cellulosic materials. Lee (1961), and Wang and Chu (1990) reported the effects of crystallinity on the wood properties, *i.e.* Young's modulus,

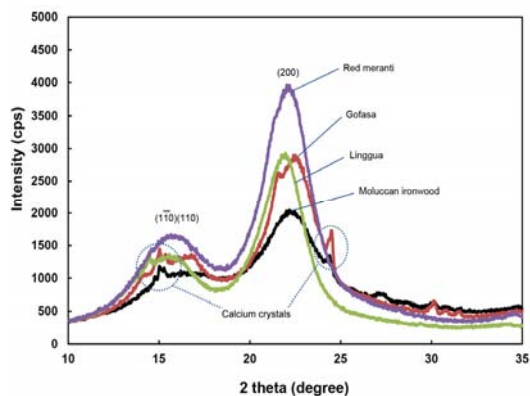**Fig. 5.** X-Ray diffractograms of the four Moluccan wood species.

hardness, density and dimensional stability increased and moisture adsorption, flexibility and chemical reactivity decreased with increasing crystallinity. However, beside crystallinity, the strength properties of wood are also affected by other factors and the complex combination of the affecting factors such as density, moisture content, slope of grain, knots, reaction wood, extractive, etc (Shmulsky and Jones, 2011). The exception among the four species can be seen in Moluccan ironwood. The wood had higher mechanical properties such as Young's modulus and hardness compared to the other three species (Richter and Dallwitz, 2000), but had the lowest crystallinity in this study.

#### 4. CONCLUSION

The four tropical woods from Moluccas, Indonesia showed some qualitative and quantitative differences on anatomical characteristics. The inclusions in vessels were only found in Moluccan ironwood. The crystals were observed in Moluccan ironwood, linggua, and gofasa, while resin canals were only displayed in red meranti. Tyloses were frequently observed in gofasa, but infrequently observed in linggua and red meranti. Moluccan ironwood with the higher density had thicker fiber wall, higher quantity of ray number, and wider rays than the other species, while red meranti had higher values of ray height and fiber length than the other three species. Linggua showed the highest values of relative crystallinity and crystallite width. Red meranti and gofasa showed similar values, while Moluccan ironwood showed the lowest relative crystallinity and crystallite width.

#### ACKNOWLEDGEMENT

This study was supported by 2016 Research Grant from Kangwon National University (No. 520160149).

#### REFERENCES

- Alexander, L.E. 1969. X-ray diffraction in polymer science. Wiley-Interscience, Amsterdam. pp: 23 ~424.
- Appanah, S., Weinland, G. 1993. Planting quality timber trees in Peninsular Malaysia. Malayan Forest Record No. 38. Forest Research Institute Malaysia, Kuala Lumpur.
- Appanah, S., Turnbull, J.W. 1998. A review of dipterocarps: taxonomy, ecology and silviculture. Center for International Forestry Research (CIFOR), Indonesia.
- Baar, J., Tippner, J., Gryc, V. 2013. The relation of fibre length and ray dimensions to sound propagation velocity in wood of selected tropical hardwoods. *IAWA Journal* 34(1): 49~60.
- Eganathan, P., Rao, C.S., Anand, A. 2000. Vegetative propagation of three mangrove tree species by cuttings and air layering. *Wetlands Ecology and Management* 9: 281~286.
- Febrianto, F., Pranata, A.Z., Septiana, D., Arinana, Gumilang, A., Hidayat, W., Jang, J.H., Lee, S.H., Hwang, W.J., Kim, N.H. 2015. Termite resistance of the less known tropical woods species grown in West Java, Indonesia. *Journal of the Korean Wood Science and Technology* 43(2): 248~257.
- Hidayat, W., Qi, Y., Jang, J.H., Febrianto, F., Lee, S.H., Chae, H.M., Kondo, T., Kim, N.H. 2017. Carbonization Characteristics of Juvenile Woods from Some Tropical Trees Planted in Indonesia. *J. Fac. Agr., Kyushu Univ.* 62(1): 145~152.
- Hillis, W.E. 1987. Heartwood and tree exudates. Springer Verlag, Berlin.
- Hillis, W.E. 1996. Formation of Robinetin Crystals in Vessels of *Intsia* Species. *IAWA Journal* 17(4): 405~419.
- Hsiao, N.C., Chang, T.C., Hsu, F.L., Chang, S.T. 2016. Environmentally benign treatments for inhibiting the release of aqueous extracts from merbau heartwood. *Wood Science and Technology* 50: 333~348.
- Hu, C., Jiang, G., Xiao, M., Zhou, J., Yi, Z. 2012. Effects of heat treatment on water-soluble extractives and color changes of merbau heartwood. *Journal of Wood Science* 58: 465~469.
- Kim, J.H., Jang, J.H., Kwon, S.M., Febrianto, F., Kim, N.H. 2012. Anatomical properties of major



- planted and promising species growing in Indonesia. *Journal of the Korean Wood Science and Technology* 40(4): 244~256.
- Kim, J.H., Jang, J.H., Ryu, J.Y., Febrianto, F., Hwang, W.J., Kim, N.H. 2014. Physical and mechanical properties of major planted and promising species grown in Indonesia (I). *Journal of the Korean Wood Science and Technology* 42(4): 467~476.
- Kurniawan, E. 2013. Breeding methods of gofasa (*Vitex cofassus Reimw*). *Info teknis EBONI* 10(1): 58~67 (in Bahasa Indonesia).
- Kusuma, I.W., Azuma, M., Darma, T., Itoh, K., Tachibana, S. 2004. Isolation and identification of antifungal compounds from amboyna wood. *Holzforschung* 59: 170~172.
- Lee, C., L. 1961. Crystallinity of wood cellulose fibers studies by X-ray methods. *Forest Products Journal* 11(2): 108~112.
- Liao, Y., Wang, J., Lu, Z., Gu, J., Hu, C. 2016. Effects of heat treatment on durability of merbau heartwood. *BioResources* 11(1): 426~438.
- Lim, T.K. 2014. *Edible Medicinal and Non-Medicinal Plants Volume 7, Flowers*. Springer Netherlands. pp. 1102.
- Marler, T.E. 2015. Balancing growth and wood quality of *Intsia bijuga* under management: Complexity of silviculture conservation decisions. *Journal of Tropical Forest Science* 27(3): 427~432.
- Ministry of Environment and Forestry, Republic of Indonesia. 2015. Ministry of Environment and Forestry Statistics 2014. [http://www.menlhk.go.id/download.php?file=STATISTIK\\_2014.pdf](http://www.menlhk.go.id/download.php?file=STATISTIK_2014.pdf)
- Ogata, K., Fujii, T., Abe, H., Baas, P. 2008. Identification of the timbers of Southeast Asia and the Western Pacific. Kaiseisha Press. Japan.
- Orwa, C., Mutua, A., Kindt, R., Jamnadass, R., Anthony, S. 2009. *Agroforestry tree database: a tree reference and selection guide version 4.0*.
- Park, S.H., Jang, J.H., Hidayat, W., Qi, Y., Febrianto, F., Kim, N.H. 2015. Combustion properties of major wood species planted in Indonesia. *Journal of the Korean Wood Science and Technology* 43(6): 768~776.
- Park, S.H., Jang, J.H., Qi, Y., Hidayat, W., Hwang, W.J., Febrianto, F., Kim, N.H. 2016. Color change of major wood species planted in Indonesia by ultraviolet radiation. *Journal of the Korean Wood Science and Technology* 44(1): 9~18.
- Qi, Y., Jang, J.H., Hidayat, W., Lee, A.H., Park, S.H., Lee, S.H., Kim, N.H. 2016. Anatomical Characteristics of *Paulownia tomentosa* Root Wood. *Journal of the Korean Wood Science and Technology* 44(2): 157~165.
- Richter, H.G., Dallwitz, M.J. 2000 onwards. *Commercial timbers: descriptions, illustrations, identification, and information retrieval*. In English, French, German, Portuguese, and Spanish. Version: 25th June 2009 (<http://delta-intkey.com>).
- Sass, U., Killmann, W., Eckstein, D. 1995. Wood formation in two species of Dipterocarpaceae in peninsular Malaysia. *IAWA Journal* 16(4): 371~384.
- Shmulsky, R., Jones, P.D. 2011. *Forest Products and Wood Science: An Introduction*, 6th Ed., Wiley-Blackwell, England.
- Segal, L., Creely, J.J., Martin, A.E., Conrad, C.M. 1959. An empirical method for estimating the degree of crystallinity of native cellulose using the X-ray diffractometer. *Textile Research Journal* 29(10): 786~794.
- Soerianegara, I., Lemmens, R.H.M.J. 1993. *Plant resources of southeast Asia No 5(1) Timber trees: major commercial timbers*. Pudoc Scientific Publishers, Wageningen.
- Wang, S.Y., Chiu, C.M. 1990. The wood properties of Japanese cedar originated by seed and vegeta-

- tive reproduction in Taiwan IV. The variation of the degree of crystallinity of cellulose. *Mokuzai Gakkaishi* 36(11): 909~916.
- Wheeler, E., Baas, P., Gasson, P.E. (Eds.). 1989. IAWA list of microscopic features for hardwood identification. *IAWA Bull.n.s.* 10(3): 219~332.
- Widiyatno, Indrioko, S., Na'iem, M., Uchiyama, K., Numata, S., Ohtani, M., Matsumoto, A., Tsumura, Y. 2016. Effects of different silvicultural systems on the genetic diversity of *Shorea parvifolia* populations in the tropical rainforest of Southeast Asia. *Tree Genetics & Genomes* 12: 73.

# Journal of The Korean Wood Science and Technology

## (Vol. 45, No. 4)

---

<b>Editor-in-Chief</b>	PARK, Byung-Dae (Kyungpook National University)
<b>Associate Editor</b>	ROH, Jung-Kwan (Gyeongnam National University of Science and Technology)
<b>Editorial Board Members</b>	JEONG, Gi Young (Chonnam National University) KANG, Seog Goo (Chungnam National University) KIM, Birm-June (Kookmin University) LEE, Seung-Hwan (Kangwon National University) LEE, Sun-Young (Forest Research Institute, Korea) LEE, Yang Soo (Chonbuk National University) PARK, Han-Min (Gyeongsang National University) PARK, Joo-Saeng (Forest Research Institute, Korea) SHIN, Soo-Jeong (Chungbuk National University) YEO, Hwanmyeong (Seoul National University)
<b>Editorial Assistant</b>	SUR, Sang-Hee (The Korean Society of Wood Science and Technology)
<b>Editing Manager</b>	PARK, Pyeong (Green Pine Media Inc.)
<b>International Editorial Board Member</b>	DUFRESNE, Alain (Grenoble Institute of Technology, France) DUNKY, Manfred (Kronospan GmbH Lampertwalde, Germany) ENDO, Takashi (National Institute of Advanced Industrial Science and Technology, Japan) EVANS, Philip (University of British Columbia, Canada) FRIHART, Chuck R. (Forest Products Laboratory, USA) HADI, Yusuf Sudo (Bogor Agricultural University, Indonesia) LABBE, Nicole (University of Tennessee, USA) NIEMZ, Peter (Swiss Federal Institute of Technology (ETH), Switzerland) RAGAUSKAS, Arthur (Georgia Institute of Technology, USA) SAKA, Shiro (Kyoto University, Japan) SCHMITT, Uwe (Johann Heinrich von Thunen Institute (vTI), Germany) SINGH, Adya P. (SCION, New Zealand) SMITH, Greg (University of British Columbia, Canada) SUGIYAMA, Junji (Kyoto University, Japan) TOHMURA, Shin-ichiro (Forestry and Forest Products Research Institute, Japan) WONG, Andrew (University Malaysia Sarawak, Malaysia) YIN, Yafang (Chinese Academy of Forestry, China)

---

This work was supported by the Korean Federation of Science and Technology Societies(KOFST) grant funded by the Korean government.